

Title	Indium-doped TiO ₂ photocatalysts with high-temperature anatase stability
Authors	Kumaravel, Vignesh;Rhatigan, Stephen;Mathew, Snehamol;Bartlett, John;Nolan, Michael;Hinder, Steven J.;Sharma, Preetam K.;Singh, Anukriti;Byrne, J. Anthony;Harrison, John;Pillai, Suresh C.
Publication date	2019-08-05
Original Citation	Kumaravel, V., Rhatigan, S., Mathew, S., Bartlett, J., Nolan, M., Hinder, S. J., Sharma, P. K., Singh, A., Byrne, J. A., Harrison, J. and Pillai, S. C. (2019) 'Indium-doped TiO ₂ photocatalysts with high-temperature anatase stability', The Journal of Physical Chemistry C, 123 (34), pp.21083-21096. doi: 10.1021/acs.jpcc.9b06811
Type of publication	Article (peer-reviewed)
Link to publisher's version	10.1021/acs.jpcc.9b06811
Rights	2019, American Chemical Society. This document is the Accepted Manuscript version of a Published Work that appeared in final form in The Journal of Physical Chemistry C, copyright © American Chemical Society after peer review and technical editing by the publisher. To access the final edited and published work see https://pubs.acs.org/doi/10.1021/acs.jpcc.9b06811
Download date	2024-10-06 21:20:25
Item downloaded from	https://hdl.handle.net/10468/12187



UCC

University College Cork, Ireland
Coláiste na hOllscoile Corcaigh

C: Surfaces, Interfaces, Porous Materials, and Catalysis

Indium Doped TiO Photocatalysts with High Temperature Anatase Stability

Vignesh Kumaravel, Stephen Rhatigan, Snehamol Mathew, John Bartlett, Michael Nolan, Steven J. Hinder, Preetam K. Sharma, Anukriti Singh, John Anthony Byrne, John Harrison, and Suresh C. Pillai

J. Phys. Chem. C, **Just Accepted Manuscript** • DOI: 10.1021/acs.jpcc.9b06811 • Publication Date (Web): 05 Aug 2019

Downloaded from pubs.acs.org on August 12, 2019

Just Accepted

“Just Accepted” manuscripts have been peer-reviewed and accepted for publication. They are posted online prior to technical editing, formatting for publication and author proofing. The American Chemical Society provides “Just Accepted” as a service to the research community to expedite the dissemination of scientific material as soon as possible after acceptance. “Just Accepted” manuscripts appear in full in PDF format accompanied by an HTML abstract. “Just Accepted” manuscripts have been fully peer reviewed, but should not be considered the official version of record. They are citable by the Digital Object Identifier (DOI®). “Just Accepted” is an optional service offered to authors. Therefore, the “Just Accepted” Web site may not include all articles that will be published in the journal. After a manuscript is technically edited and formatted, it will be removed from the “Just Accepted” Web site and published as an ASAP article. Note that technical editing may introduce minor changes to the manuscript text and/or graphics which could affect content, and all legal disclaimers and ethical guidelines that apply to the journal pertain. ACS cannot be held responsible for errors or consequences arising from the use of information contained in these “Just Accepted” manuscripts.

Indium Doped TiO₂ Photocatalysts with High Temperature Anatase Stability

Vignesh Kumaravel ^{a,b,*}, Stephen Rhatigan ^c, Snehamol Mathew ^{a,b}, John Bartlett ^{a,b}, Michael Nolan ^{c,*}, Steven J. Hinder ^d, Preetam K. Sharma ^e, Anukriti Singh ^e, J. Anthony Byrne ^e, John Harrison ^f, Suresh C. Pillai ^{a,b*}

^a Nanotechnology and Bio-Engineering Research Group, Department of Environmental Science, School of Science, Institute of Technology Sligo, Ash Lane, Sligo, Ireland.

^b Centre for Precision Engineering, Materials and Manufacturing Research (PEM), Institute of Technology Sligo, Ash Lane, Sligo, Ireland.

^c Tyndall National Institute, University College Cork, Lee Maltings, Dyke Parade, Cork, Ireland.

^d The Surface Analysis Laboratory, Faculty of Engineering and Physical Sciences, University of Surrey, Guildford, Surrey, United Kingdom.

^e NIBEC, Ulster University, Shore Road, Newtownabbey, United Kingdom.

^f InnoTech Centre, South West College, Burn Road, Cookstown, United Kingdom.

E-mail: Kumaravel.Vignesh@itsligo.ie; Pillai.Suresh@itsligo.ie; michael.nolan@tyndall.ie

Abstract:

The thermal stability of anatase titanium dioxide (TiO₂) is a prerequisite to fabricate photocatalyst coated indoor building materials for use in antimicrobial and self-cleaning applications under normal room light illumination. Metal doping of TiO₂ is an appropriate way to control the anatase to rutile phase transition (ART) at high processing temperature. In this present work, ART of indium (In) doped TiO₂ (In-TiO₂) was investigated in detail in the range of 500 °C – 900 °C. In-TiO₂ (In mol % = 0 to 16) was synthesized *via* a modified sol-gel approach. These nanoparticles were further characterized by means of powder X-ray diffraction (XRD), Raman, photoluminescence (PL), transient photocurrent response, and X-ray photoelectron spectroscopy (XPS) techniques. XRD results showed that the anatase phase was maintained up to 64 % by 16-mol % of In doping at 800 °C of calcination temperature. XPS results revealed that the binding energies of Ti⁴⁺ (Ti 2p_{1/2} and Ti 2p_{3/2}) were red-shifted by In doping. The influence of In doping on the electronic structure and oxygen vacancy formation of anatase TiO₂ was studied using density functional theory corrected for on-site Coulomb interactions (DFT+U). First principles results showed that the charge compensating oxygen vacancies form spontaneously at sites adjacent to the In dopant. DFT+U calculations revealed the formation of In - 5s states in the band gap of the anatase host. The formation of

In₂O₃ at the anatase surface was also examined using a slab model of the anatase (101) surface modified with a nanocluster of composition In₄O₆. The formation of a reducing oxygen vacancy also has a moderate energy cost and results in charge localisation at In ions of the supported nanocluster. PL and photocurrent measurements suggested that the charge carrier recombination process in TiO₂ was reduced in the presence of In dopant. The photocatalytic activity of 2 % In-TiO₂ calcined at 700 °C is more comparable with that of pure anatase.

Keywords: Photocatalysis; Titania; Dopant; Phase stability; Nanomaterials

1. Introduction:

Titanium dioxide (TiO₂) is one of the most popular nano-materials in recent decades for its energy (solar cell ¹, water splitting ², CO₂ conversion/reduction ³) and environmental (antimicrobial ⁴, self-cleaning ⁵, removal of toxic air/water pollutants ^{6, 7}) applications under UV/visible light illumination ⁸. Pure TiO₂ is commonly photo-activated by UV light owing to its wide band gap (3.2 eV for anatase and 3.0 eV for rutile phase TiO₂) ^{7, 9}. Surface decoration ^{10, 11} or inclusion of appropriate materials ¹²⁻¹⁴ in TiO₂ can favour its visible light absorption for practical applications. Among the three crystalline phases of TiO₂ (such as anatase, rutile and brookite), the anatase phase shows maximum photocatalytic activity ¹⁵. The lifetime of photo-generated charge carriers in the anatase phase is longer than that of rutile and brookite phases ¹⁶. However, many of the commercial TiO₂ products available in the market have a mixture of ~80 % anatase and ~20 % rutile phases (*e.g.* Degussa P25) ^{17, 18}. It is perceived that a mixed phase composition of TiO₂ with a high percentage of anatase (more than ~ 60 %) would reduce the charge carrier recombination process and enhance the photocatalytic efficiency ¹⁹. Therefore, TiO₂ anatase could be used as an excellent additive in the manufacturing of building materials (especially ceramic tiles sanitary ware, and glass) for indoor air purification, antimicrobial coatings and self-cleaning surfaces under normal room light illumination ²⁰⁻²². However, most of these indoor building materials are processed and manufactured at high temperatures in the range of 600 °C to 1000 °C. Usually, the anatase phase of TiO₂ is thermodynamically not stable over 600 °C, due to its low surface free energy ²³⁻²⁵. At high temperatures, the photoactive TiO₂ anatase phase will be converted into the less photoactive rutile phase TiO₂. Kinetic studies have revealed that the complete transition of anatase to rutile of TiO₂ occurs in the temperature range of 673 °C - 728 °C ²⁶. Therefore, a thermally stable TiO₂ anatase photocatalyst is required for applications in indoor building materials ²⁰, where the high temperature processing is used. ART temperature generally relies

1
2
3 on various factors, such as the synthesis method, existence of impurities/dopants, and
4 atmosphere²³. Doping of TiO₂ using metal/non-metal ions is one of the most convenient and
5 cost-effective approaches to tune the band-gap energy for visible light absorption and to
6 control the ART at high temperatures^{19, 27-35}. ART of metal doped TiO₂ is influenced by the
7 ionic radius, oxidation state and bonding nature of the dopant²³.

8
9
10 Recently, the ART of cobalt doped TiO₂ (Co-TiO₂) was studied at a single calcination
11 temperature of 600 °C and a dopant (Co) concentration in the range of 0 % to 4 mol %³⁶. The
12 results revealed that ART of TiO₂ was promoted by Co doping. 4 % of Co doping in anatase
13 produced a mixture of 78 % rutile and 22 % anatase at 600 °C. In another study, the ART of
14 TiO₂ was studied using silicon (Si) dopant³⁷. The anatase phase of TiO₂ was well maintained
15 until 800 °C by 0.25% Si doping, with 90 % anatase and 10 % rutile. ART of TiO₂ has been
16 shown to be promoted by tungsten (W)³⁸ and vanadium (V) doping³⁹. The phase
17 transformation was promoted up to 50 ppm of W⁶⁺ and it was inhibited thereafter (> W⁶⁺ 50
18 ppm; calcination 500 °C) [37]. 100 % rutile was formed by the addition of 6 at.% of V at a
19 calcination temperature of 550 °C [38]. In a recent study, it was observed that the anatase
20 phase of TiO₂ nanowires was well retained with Ti³⁺ self-doping up to a calcination
21 temperature of 800 °C⁴⁰.

22
23
24 Indium (In) is a transition metal with 5s² 5p¹ electronic configuration and it generally
25 takes a +3 oxidation state. It has the tendency to create oxygen vacancies in TiO₂^{41, 42}.
26 Indium is considered as an effective dopant for TiO₂, owing to its electronic properties and
27 low toxicity^{42, 43}. Doping of such metal ions into TiO₂ would be beneficial to enrich the
28 photocatalytic activity⁴⁴ *via* inhibiting the photo-generated charge-carrier recombination and
29 promoting the adsorption of microbes/pollutants on the active sites of photocatalyst^{42, 45}. In
30 doped TiO₂ was studied for the photocatalytic reduction of carbon dioxide (CO₂) under UV
31 light irradiation^{42, 46}. The dopant concentration was examined in the range of 0 wt % to 20 wt
32 % and the calcination temperature was fixed at 500 °C for 5 h. The results revealed that no
33 phase transition occurred in In-TiO₂ during this calcination step. The CO₂ reduction
34 efficiency was increased significantly for the In-doped samples as compared to pure TiO₂.
35 The efficiency of 10 wt % In-TiO₂ was 7.9 fold higher than that of un-doped TiO₂. Wang *et*
36 *al.*⁴⁷ reported the visible light assisted photocatalytic efficiency of In-TiO₂ for the
37 degradation of 4-chlorophenol. In was studied in the range of 3 mol % to 15 mol % and the
38 calcination temperature was fixed at 450 °C for 2.5 h. These results suggest that the electron-
39 hole recombination was minimized and the photocatalytic activity was enhanced by In
40 doping, which helps to stabilize the anatase phase.

1
2
3 First principle studies of In-doped TiO₂ are sparse in the literature. Wang *et al.*
4 reported the visible light assisted photocatalytic activity for In-TiO₂ anatase, which was
5 attributed to the presence of a surface species, O-In-Cl_x (x = 1 or 2)⁴⁷. This species
6 introduced a surface state energy level at 0.3 eV below the TiO₂ CB. This work was followed
7 with a study of TiO₂ co-modified with N and In, which included DFT calculations of the
8 electronic band structure and density of states (DOS) for In-TiO₂⁴⁸. While details of the exact
9 computational set-up are lacking, the authors reported that In-derived states emerge at 0.5 eV
10 below the TiO₂ CB, in their generalized gradient approximation (GGA) calculations. Charge
11 compensation *via* oxygen vacancy formation in In-TiO₂ rutile was previously studied using
12 standard DFT, DFT+U and hybrid DFT⁴⁹. A recent GGA study presented an analysis of the
13 band structure and DOS for stoichiometric and charge compensated In-TiO₂ anatase⁵⁰. The
14 details regarding the oxidation states, oxygen vacancy formation, reduction and charge
15 localization were not provided.

16
17 There are no comprehensive or systematic studies available in the literature on the
18 ART of In-TiO₂. In this paper, we study the ART of In doped TiO₂ (In-TiO₂) nanoparticles
19 calcined for 2 h temperatures in the range of 500 °C to 900 °C; this includes temperature at
20 which undoped anatase transforms to rutile. In-TiO₂ was synthesized using a sol-gel
21 technique with different mol percentages of In (0 %, 2 %, 4 %, 8 % and 16 %). The
22 calculations of the energetics involved in the formation of charge compensating and
23 subsequent oxygen vacancies, the DOS of the ground state and reduced system, and charge
24 localization after reducing oxygen vacancy formation were investigated through DFT. ART
25 was studied in detail by DFT, XRD, XPS, PL and Raman spectroscopy techniques. The
26 anatase phase of TiO₂ is well maintained by the In dopant till 800 °C. The charge carrier
27 recombination is highly minimized *via* the formation of In 5s states between the conduction
28 band (CB) and valance band (VB) of TiO₂.

29
30 The formation energies of charge compensating and reducing oxygen vacancies in In-
31 TiO₂ were computed through the DFT model. There is no impact on the bandgap due to In-
32 doping in the charge compensated system, however, after localisation of charge in the
33 vicinity of the In-dopant after the formation of a reducing oxygen vacancy, occupied states
34 emerge in the bandgap of TiO₂. A model of a nanocluster of composition In₄O₆ at the anatase
35 (101) surface (denoted In₄O₆-a101) was considered to examine the impact of In₂O₃ formation
36 at high calcination temperatures.

2. Materials and methods

All the materials used were of analytical grade and they were used as received without further purification. Double distilled water was used in the experiments.

2.1. Synthesis of indium doped TiO_2 (In- TiO_2):

2 mol % In- TiO_2 was synthesized through a sol-gel technique as follows: In a typical experiment, 38 ml of titanium isopropoxide (TTIP) was taken in 200 ml of isopropanol and the mixture was stirred for 15 min at RTP (solution A). 0.786 g of indium nitrate ($\text{In}(\text{NO}_3)_3 \cdot x\text{H}_2\text{O}$) was dissolved separately in 200 ml of double distilled water (solution B) at RTP. Then, solution B was added drop wisely into solution A under constant stirring for 30 min. The resulting gel was dried in an oven at 100 °C for 24 h. Afterwards, the powders were calcined in a muffle furnace at various temperatures (500 °C, 600 °C, 700 °C, 750 °C, 800 °C, 850 °C and 900 °C) at a ramp rate of 10 °C/min for 2 h. The samples were synthesized using various mol % of In. The as-synthesized samples such as such as 0 mol % In- TiO_2 , 2 mol % In- TiO_2 , 4 mol % In- TiO_2 , 8 mol % In- TiO_2 and 16 mol % In- TiO_2 were labelled as TiIn-0, TiIn-2, TiIn-4, TiIn-8 and TiIn-16, respectively. Pure TiO_2 was synthesized using the same procedure without the addition of In precursor.

2.2. Density functional theory (DFT) studies:

DFT calculations were carried out using the VASP5.4^{51, 52} code with projector augmented wave^{53, 54} (PAW) potentials to account for the core-valence interaction. Titanium (Ti) is described with 12 valence electrons, oxygen (O) with six and indium (In) with 13. The energy cut-off for the plane wave basis set is 400 eV and the convergence criterion for electronic relaxations is 10^{-5} eV. Indium (In) was substitutionally doped onto two Ti sites in a $(2 \times 2 \times 1)$ anatase supercell, to give a dopant concentration of 12.5 at.%. A previous study⁴⁹ revealed that interstitial sites have higher formation energies relative to substitutional doping. Therefore, interstitial sites were not considered in this study. The bulk lattice parameters of the anatase unit cell were computed as: $a = 3.791 \text{ \AA}$ and $b = 9.584 \text{ \AA}$.

After substituting two In ions for Ti, two relaxations were performed; the first in which only the ionic positions were relaxed (supercell with dimensions fixed to those of pure anatase) and in the second a full relaxation of both ionic positions and supercell parameters. After the latter relaxation, the lattice dimensions expand in response to In-doping; the unit cell parameters of In-doped TiO_2 are $a = 3.830 \text{ \AA}$ and $c = 9.999 \text{ \AA}$, corresponding to an

increase of 1% and 4%, respectively. These changes in the lattice dimensions are small and any impact on the computed properties is expected to be negligible.

A $(4 \times 4 \times 4)$ k-point sampling grid was used and structures were relaxed until forces were less than 0.01 eV/Å. Calculations were spin-polarized and no symmetry constraints were imposed. The calculations include an on-site Hubbard correction (DFT+U)^{55, 56} to describe the partially filled Ti 3*d* state; $U = 4.5$ eV is applied to Ti 3*d* states, with this choice for U informed by previous studies⁵⁷⁻⁶¹.

Oxygen vacancy formation is the mechanism of charge compensation in response to the substitution of In^{3+} for Ti^{4+} ions. To study this, multiple oxygen sites of the most stable In-doped structure were considered and the energy of formation was calculated via:

$$E^{vac} = E(\text{In}_x\text{Ti}_{1-x}\text{O}_{2-y}) + 1/2E(\text{O}_2) - E(\text{In}_x\text{Ti}_{1-x}\text{O}_2) \quad (1)$$

where $E(\text{In}_x\text{Ti}_{1-x}\text{O}_{2-y})$ is the total energy of In-doped TiO_2 with a charge compensating oxygen vacancy and $E(\text{In}_x\text{Ti}_{1-x}\text{O}_2)$ is the total energy of In-doped TiO_2 . The formation energy is referenced to half the total energy of O_2 . A negative value for E^{vac} indicates that the vacancy will form spontaneously at 0 K. The energy cost to produce a second, reducing oxygen vacancy is computed similarly using:

$$E^{vac} = E(\text{In}_x\text{Ti}_{1-x}\text{O}_{2-y'}) + 1/2E(\text{O}_2) - E(\text{In}_x\text{Ti}_{1-x}\text{O}_{2-y}) \quad (2)$$

where $E(\text{In}_x\text{Ti}_{1-x}\text{O}_{2-y'})$ is the total energy of In doped TiO_2 with two oxygen vacancies. The oxidation states were analysed through Bader charge analysis⁶² and computed spin magnetizations

To examine the presence of In_2O_3 , a nanocluster of In_4O_6 composition at the anatase (101) surface (denoted as $\text{In}_4\text{O}_6\text{-a101}$) was considered. The anatase (101) support is modelled as a 12 atomic layer thick slab with a (1×4) surface expansion and a vacuum gap of 20 Å. For these calculations, k-point sampling was performed at the gamma-point and the remaining computational parameters are consistent with those described above for the bulk calculations. The adsorption energy of the In_4O_6 nanocluster at the anatase (101) surface is computed as follows:

$$E^{ads} = E(\text{In}_4\text{O}_6\text{-a101}) - E(\text{a101}) - E(\text{In}_4\text{O}_6) \quad (3)$$

where the first, second and third terms on the right-hand side refer to the total energy of nanocluster-surface composite, bare anatase (101) and the gas phase In_4O_6 nanocluster,

1
2
3 respectively. The formation energies of a single and reducing oxygen vacancy in the
4 supported nanocluster were computed using the following equation:
5

$$6 \quad E^{vac} = E(\text{In}_4\text{O}_5 - a101) + 1/2E(\text{O}_2) - E(\text{In}_4\text{O}_6 - a101) \quad (4)$$

7 8 9 10 **2.3. Characterization:**

11 ART and the TiO₂ crystalline phases were studied with the help of X-ray diffraction
12 (XRD) using Cu K α radiation ($\lambda = 0.15418$ nm) in the 2θ range of $10^\circ - 80^\circ$ in a Siemens
13 D500 XRD instrument. The percentages of TiO₂ anatase and rutile were calculated through
14 the Spurr equation^{25, 63}:
15

$$16 \quad F_R = \frac{1}{1 + 0.8[I_A(101)/I_R(110)]} \quad (5)$$

17 Where F_R is the quantity of rutile phase; $I_A(101)$ and $I_R(110)$ are the intensities of anatase
18 and rutile peaks, respectively. The average crystallite size was determined using the Scherrer
19 equation^{11, 64}. ART was also analyzed *via* Raman spectroscopy (Horiba Jobin Yvan
20 LabRAM HR 800) with a grating of 300 gr/mm. The acquisition time of Raman analysis was
21 3 seconds. The oxidation state of elements and the bonding interactions of In-TiO₂ were
22 examined by an X-ray photoelectron spectroscopy (XPS; ThermoFisher Scientific
23 Instruments (East Grinstead, UK) with K-Alpha⁺ spectrometer). The charge carrier
24 recombination process was studied in terms of photoluminescence (PL) spectroscopy with an
25 excitation wavelength of 350 nm. The photocatalytic activity (0.5 g/L) was evaluated using
26 0.5 g/L of nanoparticles for hydrogen (H₂) production in a 230 ml stainless steel reactor with
27 a quartz window. The experiments were carried out using 115 ml of double distilled water
28 under simulated solar light irradiation (300 W ozone free Xe lamp). Glycerol (10 %) was
29 used as a sacrificial agent. H₂ gas was analysed through an Agilent gas chromatography (GC)
30 with thermal conductivity detector (TCD) and flame ionization detector (FID). Carboxen-
31 1000 packed column was used in the GC.
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48

49 **2.4. Photocurrent measurements:**

50 The nanoparticles were sonicated in methanol followed by spray coating on a clean
51 titanium foil⁶⁵. The spray-coated samples were annealed at 400 °C (ramp 2 °C min⁻¹ up, 2 °C
52 min⁻¹ down) to enhance the adhesion and inter-particle cohesion. The final loading of the
53 samples was 1 mg.cm⁻² on a 2 cm² photoactive area. Electrical contact to the Ti foil was made
54 with copper wire using silver epoxy. The contact and any are not coated with TiO₂ were
55 insulated by SU8 (MicroChem) photoresist. The photocurrent measurements were performed
56
57
58
59
60

1
2
3 using an Autolab PG30 electrochemical workstation coupled with the irradiation source of
4 450 W Xe lamp. The measurements under irradiated and dark conditions were obtained using
5 a Uniblitz chopper in front of the irradiation source. Electrochemical measurements were
6 performed in a three-electrode cell using platinum mesh as counter electrode and saturated
7 calomel as reference electrode. The electrochemical cell was equipped with a quartz window
8 to irradiate the working electrode. 0.1 M perchloric acid was used as an electrolyte and all
9 potentials are reported relative to saturated calomel electrode (SCE). The photocurrent
10 responses were measured at a fixed potential of +1.0 V.
11
12
13
14
15
16
17
18

19 3. Results and Discussion


20 The impact of In doping on the ART of TiO₂ samples synthesized at various calcination
21 temperatures: 500 °C, 600 °C, 700 °C, 750 °C, 800 °C, 850 °C and 900 °C, were examined
22 by XRD. The changes in the lattice parameters of TiO₂ by In doping was studied by Raman
23 spectroscopy. The bonding interactions, formation of new energy levels and oxygen
24 vacancies of In-TiO₂ framework were investigated through DFT and XPS. The results were
25 compared with pure TiO₂ anatase and rutile.
26
27
28
29
30
31

32 *Density functional theory (DFT) calculations:*

33 Fig. 1 (a) shows the (2 × 2 × 1) anatase supercell and the local atomic structure in the
34 vicinity of In dopants. The most favourable dopant configuration is that in which both In ions
35 are incorporated at Ti sites in the same Ti (001) sub-lattice plane, as shown in Fig. 1.
36 However, a number of other configurations were very close in energy (within 0.2-6.0 meV
37 per TiO₂ unit). The geometry about the dopant sites is symmetric. In-O distances are 2.22 Å
38 for apical (O_{ap}) and 2.03 Å for equatorial (O_{eq}) oxygen sites. These values compare with
39 values of 2.00 Å and 1.94 Å for equivalent Ti-O distances in un-doped anatase. Replacing
40 two Ti⁴⁺ with two In³⁺ ions means a deficit of two valence electrons and, in this
41 computational set up, the excess charge is distributed over all O ions in the supercell as
42 shown in Fig.1 (b).
43
44
45
46
47
48
49
50

51 Applying the GGA+U to the O 2p states, with U = 5.5 eV, yields a solution in which the
52 excess charge is distributed only over the O ions found at apical positions relative to the In-
53 dopants. Bader charges for these sites decrease from 7.2 to 7.1 electrons and computed spin
54 magnetizations are 0.3 μ_B. After this localization of charge each In-O_{ap} distance increases to
55 2.24 Å. If we now distort the initial structure about the dopant sites to break the symmetry,
56
57
58
59
60

1
2
3 the geometry relaxes to an asymmetric solution, which is more favourable than the symmetric
4 solution by 0.34 eV (Fig. 1(c)). In this configuration, the excess charge localizes
5 predominantly on a single apical oxygen site neighbouring each In-dopant. The computed
6 Bader charges decrease from 7.2 to 6.8 electrons and the computed spin magnetizations are
7 0.7 μ_B for these oxygen sites, indicating the formation of oxygen polarons (O^-)^{30, 49}. It is this
8 localization of charge which produces the asymmetric geometry distortion. In- O^- distances
9 are 2.31 Å, In- O_{ap} distances are 2.19 Å and In- O_{eq} distances are 2.02-2.05 Å.

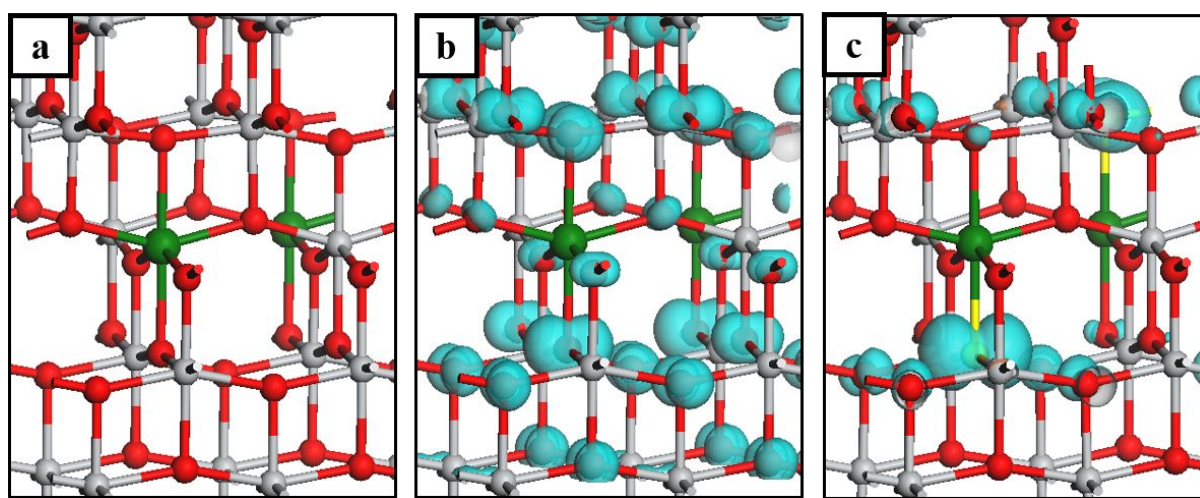

17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33 **Fig. 1** Panel (a) shows the positions of In-dopant in the anatase lattice. Panel (b) shows the excess
34 spin density plot for the computational set up with no +U correction on the O 2p states. Panel (c)
35 shows the excess spin density plot for the computational set up with an additional +U correction on
36 the O 2p states and for which the geometry was distorted from symmetry prior to relaxation. Ti is
37 represented by grey spheres, O by red spheres, In by green spheres and the oxygen hole polarons (O^-)
38 are highlighted in yellow. The blue iso-surface encloses spin densities up to 0.02 electrons/Å².

43
44 Oxygen vacancy formation is the mechanism by which the charge mismatch that results
45 from substitution of Ti ions with lower valent In-dopants is compensated⁴⁵. The computed
46 formation energies for a single compensating oxygen vacancy were in the range -0.24 eV to
47 +0.84 eV, depending on the O site considered. The negative oxygen vacancy formation
48 energy confirms that the charge compensated structure is favourable. Formation of the most
49 stable vacancy was more favourable than the next most stable by 0.12 eV and the resulting
50 geometry is shown in the top panels of Fig. 2. The most stable oxygen vacancy in the fully
51 relaxed structure has a formation energy of -0.11 eV, which shows that oxygen vacancy
52 formation takes place to charge balance the In dopant. The removed O ion was in an
53 equatorial position relative to the In-dopant and, after formation of a vacancy at this site, the
54
55
56
57
58
59
60

neighbouring Ti and In sites are five-fold coordinated. The Ti ions move off their lattice sites by 0.2 Å away from the vacancy and the Ti-O distances opposite the vacancy are shortened by 0.10-0.14 Å relative to the bond lengths prior to vacancy formation. The In-dopant moves 0.2 Å closer to the vacancy and, since there are no oxygen polarons after charge compensation, the In-O_{ap} distances are shortened to 2.09 and 2.15 Å. The remaining In-O_{eq} distances are 2.00-2.08 Å. For the second In-dopant, away from the vacancy site, the In-O_{ap} distances are 2.14 and 2.19 Å and the In-O_{eq} distances are 2.02-2.12 Å.

Formation of a second, reducing oxygen vacancy, which is implicated in the ART, was considered, and the computed formation energies lie in the range of 3.80-5.84 eV. Energies at the lower end of this range mean that the In-doped system is reducible, with moderate energy costs, and, given the elevated preparation temperatures, such reducing oxygen vacancies will be expected to form. In the fully relaxed super cell, the most stable reducing oxygen vacancy forms with an energy cost of 4.41 eV. While this cost is larger than that in the fixed supercell, it is still moderate when compared with an energy cost of 5.2 eV to produce a single, reducing oxygen vacancy in the (2 × 2 × 1) un-doped anatase supercell, computed with the same input parameters. The most stable site for the formation of a reducing vacancy is an equatorial site of the second In-dopant, as shown in the bottom panels of Fig. 2. In this instance, the In-dopants move 0.4 Å off the lattice site and towards the vacancy sites, while the Ti ions move 0.1-0.3 Å outwards from the vacancy sites. The geometry in the vicinity of both In-dopant is similar; the In-O_{ap} distances are 2.18 Å, two In-O_{eq} distances are 2.10 Å and the third, opposite the vacancy, is longer, at 2.22 Å.


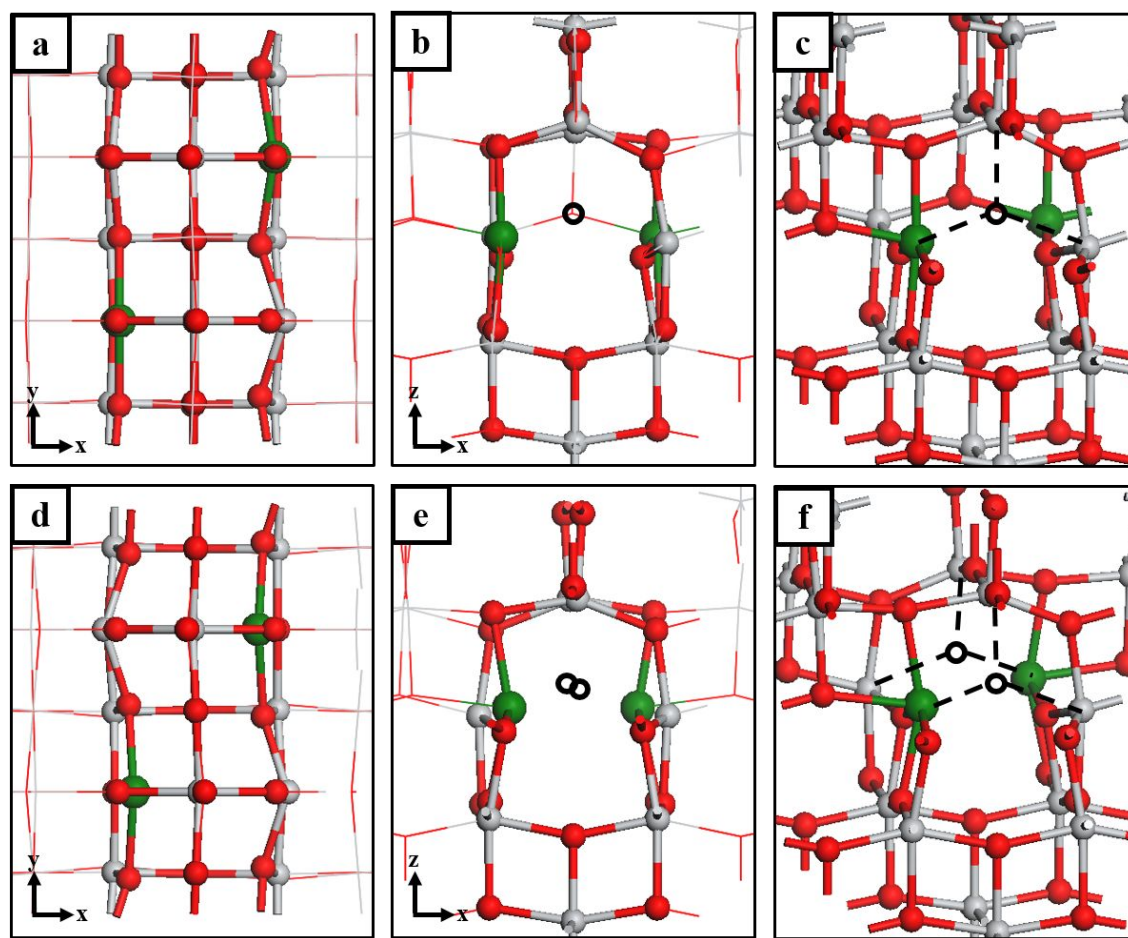


Fig. 2. The top panels display distortions to the lattice of In-doped anatase TiO_2 in response to the charge compensating oxygen vacancy. Bottom panels show the atomic structure after formation of a second, reducing oxygen vacancy. The xy-plane geometry, shown in (a) and (d), and the xz-plane geometry, shown in (b) and (e), highlight the movement of the In-dopants towards the vacancy sites and the movement of Ti ions away from the vacancies, represented by black circles. Panel (c) and (f) indicate the cations to which the removed oxygen ions were bound.

With two oxygen vacancies in In-doped anatase, there is an excess of two electrons and the computed Bader charges reveal that some of this charge is distributed over the cations to which the removed oxygen ions were bound. For the In-dopants the Bader charges increase from 11.0 to 11.5 electrons and these sites have spin magnetizations of $0.2 \mu_B$. For the Ti sites, the Bader charges increase from 9.6 to 9.7/9.8 electrons, where the vacancy sits in an equatorial/apical position relative to the Ti ion. Similarly, these Ti sites have computed spin magnetizations of $0.1/0.2 \mu_B$. These values, in particular those for the spin magnetization,

1
2
3 indicate that the excess electrons are not fully localized. The excess spin density plots in Fig.
4 3 show that the charge is distributed over site of the removed oxygen atom, similar to an F-
5 centre, and with some localisation onto neighbouring Ti and In sites.
6
7

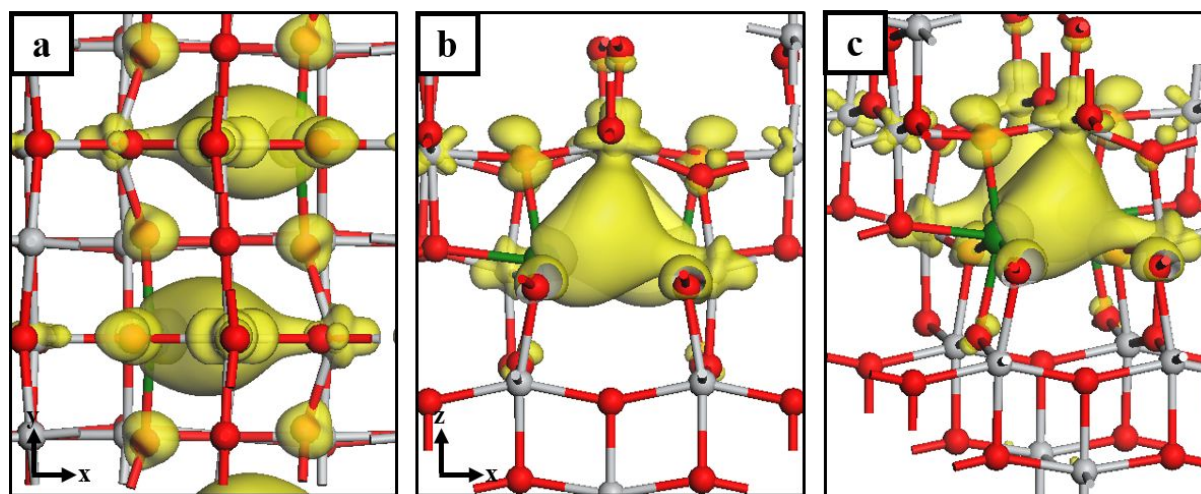

8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25 **Fig. 3** Excess spin density plot showing the localization of electrons after formation of a
26 second, reducing oxygen vacancy in In-doped anatase TiO₂. Panels (a), (b) and (c) display
27 the geometry in the xy-plane, xz-plane and from an angled view. The yellow isosurface
28 encloses spin densities up to 0.02 electrons/Å²
29
30
31
32

33
34 The energy cost to produce a third oxygen vacancy is in the range of 5.1-5.9 eV,
35 depending on the vacancy site. This can be compared with an energy cost of 5.2 eV to
36 produce a single, reducing oxygen vacancy in the (2 × 2 × 1) un-doped anatase supercell,
37 computed with the same input parameters. Thus, In doping can lead to less favourable
38 vacancy formation, although the precise details of the ART mechanism is reported to be more
39 complex than oxygen vacancy formation^{66,67}.
40
41
42
43

44 The projected electronic density of states (PEDOS) plots are shown in Fig. 4 for (a) un-
45 doped anatase, (c) the ground state In-doped system, with a single, compensating oxygen
46 vacancy, and (d) the reduced In-doped system, with two oxygen vacancies. For reference, the
47 computed PEDOS for In-doped anatase prior to charge compensation is shown in Fig. 4 (b).
48 However, as this does not represent a physical system, due to oxygen vacancies forming
49 spontaneously at 0 K, it is included only for completeness.
50
51
52
53

54 For the ground state In-doped system, the PEDOS plot in Fig. 4 (c) yields a band gap of
55 2.44 eV, which compares with a value of 2.70 eV for the un-doped system. For the PEDOS
56 plot in Fig. 4 (d), the titania-derived band gap is 2.49 eV and states emerge in this gap which
57 arise due to cation reduction in response to formation of a second, reducing oxygen vacancy
58
59
60

and are associated with the spin density as shown in Fig. 3. The first peak emerges at 1.59 eV above the valence band max (VBM) of the TiO_2 host and is associated with the singly-occupied, $5s$ orbitals of the In-dopants. The next states lie higher in energy, at 2.17 eV above the TiO_2 VBM, and are derived from the empty $5s$ orbitals of the In-dopants.

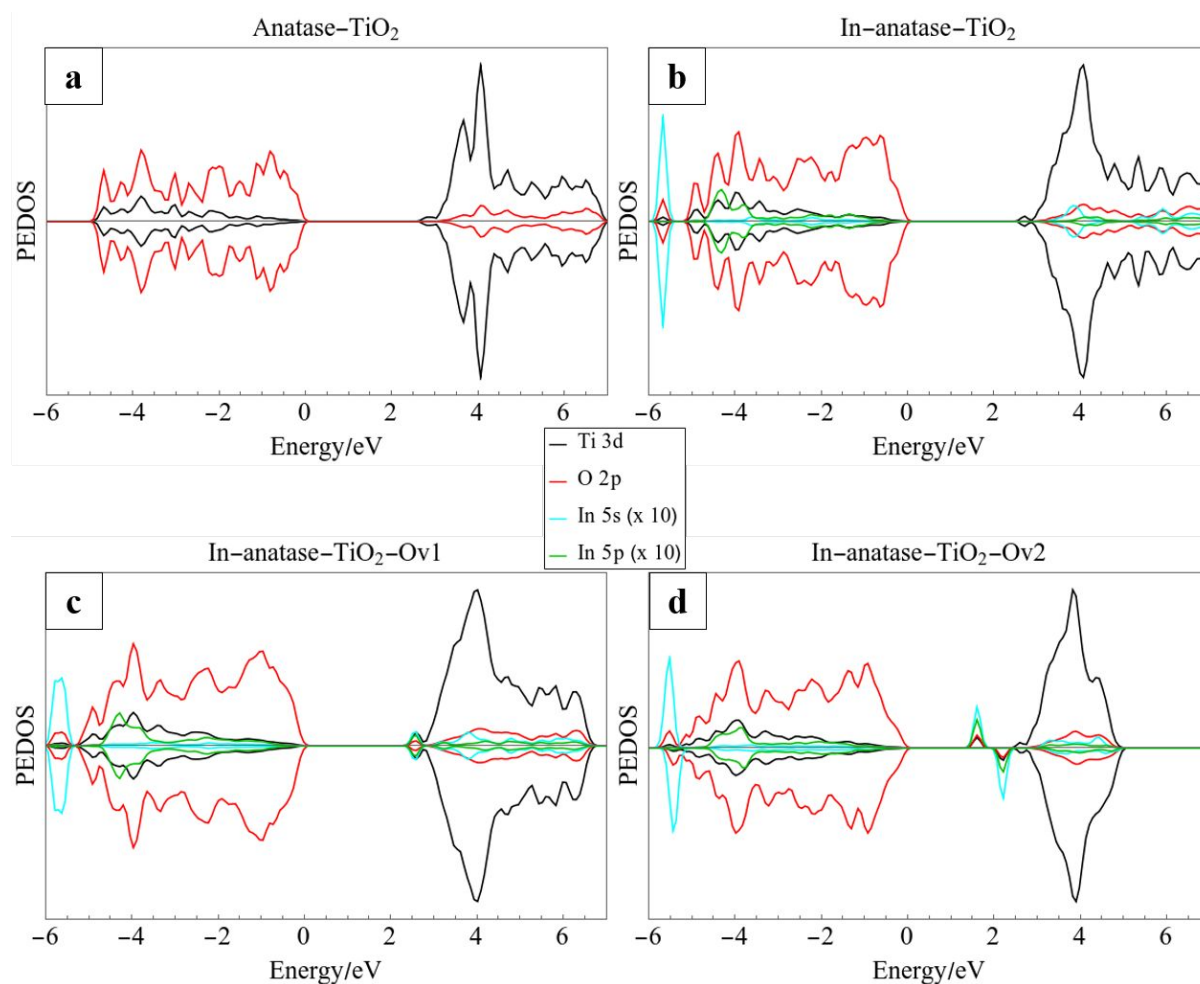


Fig. 4. Projected electronic density of states (PEDOS) computed for (a) undoped anatase and (b) In-doped anatase with no oxygen vacancies are included for reference. The PEDOS of the ground state structure, with a single, charge compensating oxygen vacancy and the reduced system with two oxygen vacancies are shown in panels (c) and (d).

To examine the influence of In_2O_3 on the properties of In-doped anatase, a model of an In_4O_6 nanocluster modifying the anatase (101) surface (In_4O_6 -a101) was implemented. The computed adsorption energy is -3.42 eV, showing that the cluster-surface interaction is favourable. However, at high calcination temperatures, it is possible that the nanoclusters will desorb or migrate and aggregate at the surface to form larger nanoclusters. The latter eventuality would lead to enhanced In_2O_3 signals in the XRD spectrum.

1
2
3 The relaxed structure of stoichiometric In_4O_6 -a101 is shown in Fig. 5 (a). In_4O_6 binds to
4 the surface *via* the formation of three In-O and three Ti-O bonds. Three In ions are four-fold
5 coordinated and the fourth In ion is three-fold coordinated; In-O bond lengths are in the range
6 1.96-2.19 Å. Three cluster O ions are three-fold coordinated and the remaining three O ions
7 are doubly coordinated. The interfacial Ti-O distance is 1.86-2.08 Å. The computed Bader
8 charges for In ions in the stoichiometric cluster are 11.2-11.3 electrons, to which we ascribe
9 an oxidation state of In^{3+} .

10
11 The formation energy for the most stable oxygen vacancy in the supported In_4O_6
12 nanocluster is computed as 2.19 eV. The relaxed structure of In_4O_5 -a101 is shown in Fig. 5
13 (b). In this configuration, there are seven interfacial bonds (four In-O and three Ti-O bonds);
14 In-O distances are in the range 2.06-2.36 Å and interfacial Ti-O distances are 1.88-1.96 Å.
15 Two electrons are released after the formation of a neutral oxygen vacancy and these localise
16 at In ions, as shown in the excess spin density plot (Fig. 5 (b)); the Bader charges for these
17 sites increase from 11.2 and 11.3 electrons to 11.8 electrons. Electron localisation is further
18 confirmed by computed spin magnetisations of 0.3 and 0.4 μ_B . Based on these results, and
19 given the moderate oxygen vacancy formation energy, should In_2O_3 form at the anatase
20 surface, In ions will be present in a mixture of oxidation states. In particular, localisation of
21 charge at In ions at the surface will contribute to the photocatalytic activity.

22
23 The PEDOS of In_4O_6 -a101 and In_4O_5 -a101 are shown in Fig. 6 (a) and 6 (b), respectively.
24 For In_4O_6 -a101, states derived from cluster O ions extend to 0.2 eV above the VBM of
25 titania. In addition, In-derived states emerge in the bandgap at 0.5 eV below the CBM. For
26 the reduced system (In_4O_5 -a101), cluster O $2p$ -derived states persist to 0.4 eV above the
27 VBM and additional In-derived occupied states emerge in the titania bandgap at 1.3 eV above
28 the VBM. For both stoichiometric In_4O_6 -a101 and reduced In_4O_5 -a101 systems, these
29 features suggest a red-shift in the light absorption edge and could enhance the lifetime of
30 charge carriers on the photocatalyst surface as compared to bare anatase (101).
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

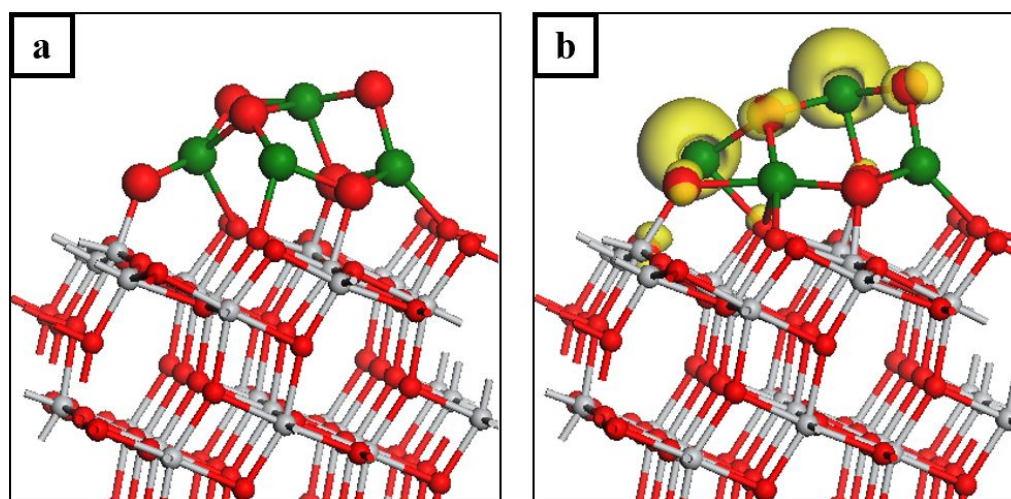


Fig. 5. The relaxed atomic structure of (a) stoichiometric $\text{In}_4\text{O}_6\text{-a101}$ and (b) reduced $\text{In}_4\text{O}_5\text{-a101}$. The yellow iso-surface encloses spin densities up to $0.02 \text{ electrons}/\text{\AA}^2$.

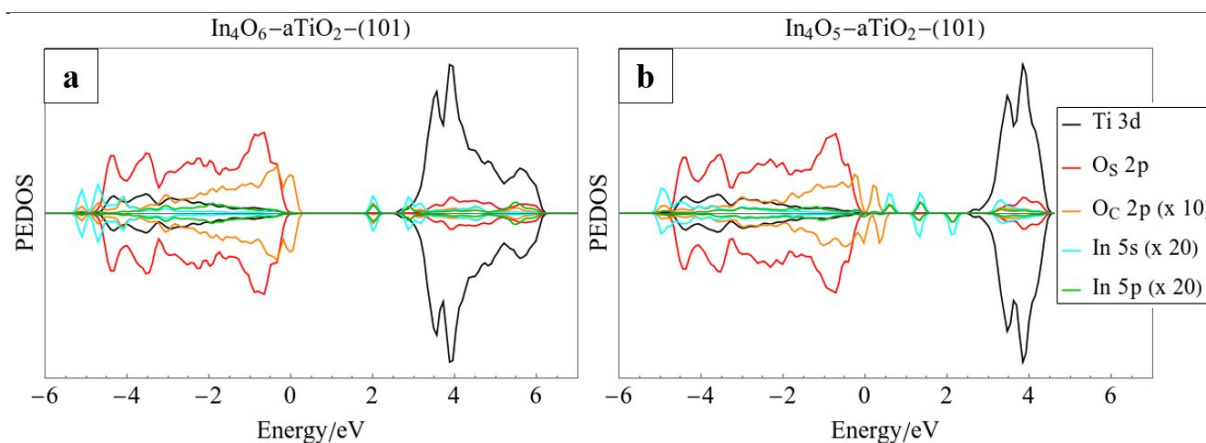
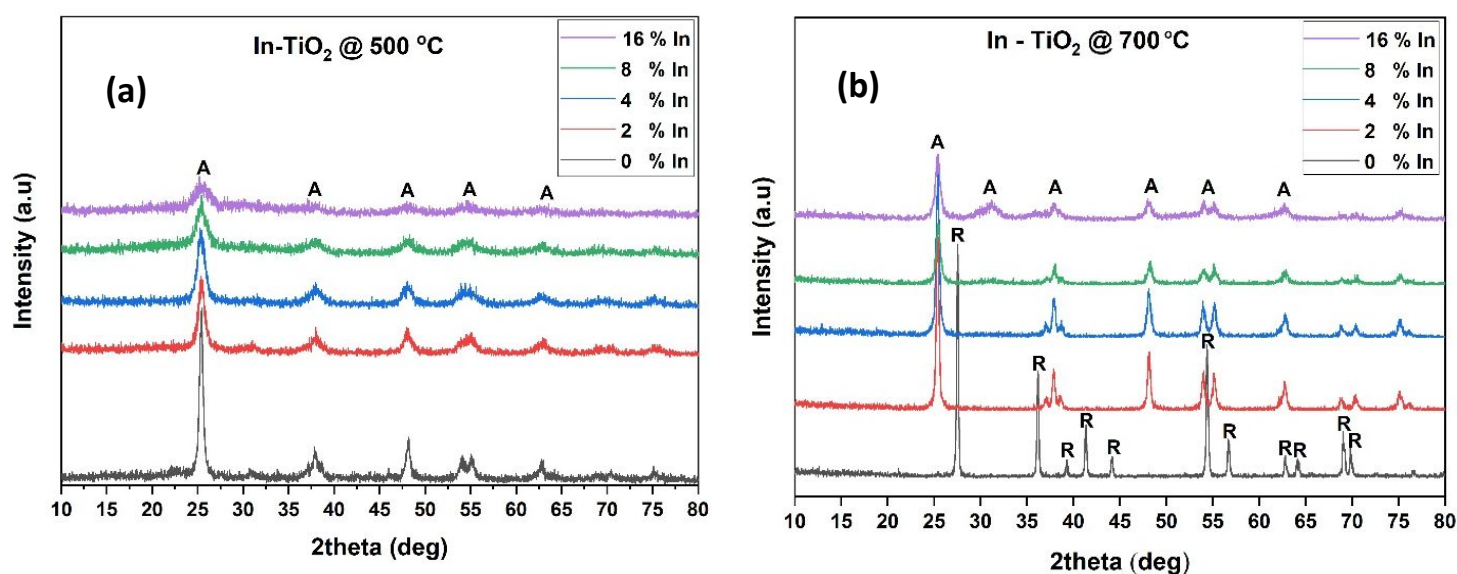


Fig. 6. Projected electronic density of states (PEDOS) computed for (a) stoichiometric $\text{In}_4\text{O}_6\text{-a101}$ and (b) reduced $\text{In}_4\text{O}_5\text{-a101}$.

X-ray diffraction:

XRD patterns of pristine TiO_2 and In-TiO_2 calcined at 500°C , 700°C , 800°C and 900°C are shown in Fig. 7. The percentages of anatase and rutile phases in In-TiO_2 samples are given in Table 1. At 500°C , the diffraction peaks of all samples are matched with the anatase phase TiO_2 . Undoped TiO_2 is almost transformed into the rutile phase (90 % rutile and 10 % anatase) when the calcination temperature is increased to 600°C . Nevertheless, the anatase phase is well retained for In-TiO_2 samples up to 700°C . A mixture of anatase and rutile phases is formed for In-TiO_2 samples at 800°C (Fig. 8 (a)). Moreover, some additional peaks also appear, due to the formation of indium trioxide (In_2O_3). The peak intensities for indium oxide are increased with increase of In dopant concentration. All samples completely transform to rutile at 900°C calcination temperature. For In-TiO_2 (especially at 600°C , 700°C

1
2
3 °C and 800 °C), the (101) anatase peak is slightly shifted after In doping, suggesting the
4 substitution of Ti^{4+} ions by In^{3+} ions in the crystal lattice of TiO_2 ^{68, 69}. This is ascribed to the
5 fact that the lattice parameters and cell volume of In-TiO_2 being larger than pure anatase
6 TiO_2 . TiIn-2 (at 800 °C) and TiIn-16 (at 800 °C) samples showed remarkable anatase and
7 rutile percentages with respect to commercial TiO_2 p25. The crystallite size of TiO_2 is
8 gradually reduced with increase of In content (Fig. 8 (b)). This is ascribed to the
9 crystallization and agglomeration of TiO_2 being retarded by In doping ⁷⁰⁻⁷². TiO_2 crystal
10 framework may be stressed by the substitution of Ti^{4+} or superficial O_2 ions by In^{3+} ions and
11 the O-Ti-OH surface bonds are affected by In doping⁴⁷. Wang *et al.* ⁴⁸ suggested that the
12 increase of In concentration (from 5 to 10 %) in TiO_2 favours the rutile formation in small
13 amounts at the calcination temperature of 450 °C. However, in this present work, the rutile
14 formation is highly restricted up to 700 °C by In doping. Hinojosa-Reyes *et al.* ⁷⁰ found that
15 the anatase phase could be retained up to 1000 °C by In doping with a decreased calcination
16 time of 30 min. These results suggest that the calcination time can also play a role in the ART
17 of In-TiO_2 . Moreover, the calcination time of 2 h is sufficient for the complete transformation
18 of anatase to rutile. The lattice constants (a and c) and cell volume (V) were calculated for the
19 samples (0 % In-TiO_2 @500 °C, 2 % In-TiO_2 @750 °C, 4% In-TiO_2 @750 °C and 16 % In-
20 TiO_2 @800 °C) with high anatase content (Table S1). The cell volume (from 135.4 to 135.8)
21 and lattice constant ' c ' (from 9.48 to 9.50) of pure TiO_2 anatase are slightly increased after
22 doping with In. The results revealed that the impact of In doping on the anatase lattice
23 parameters are negligible.
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41



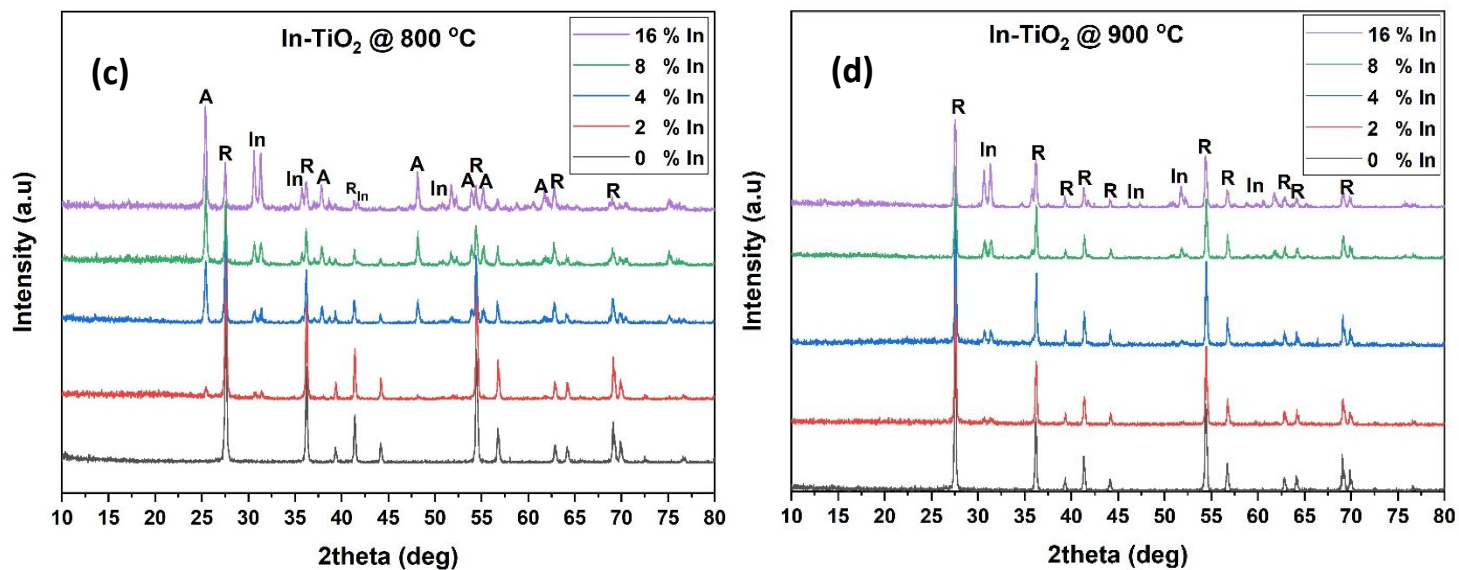


Fig. 7. XRD patterns of In-TiO₂ calcined at (a) 500 °C (b) 700 °C (c) 800 °C and (d) 900 °C

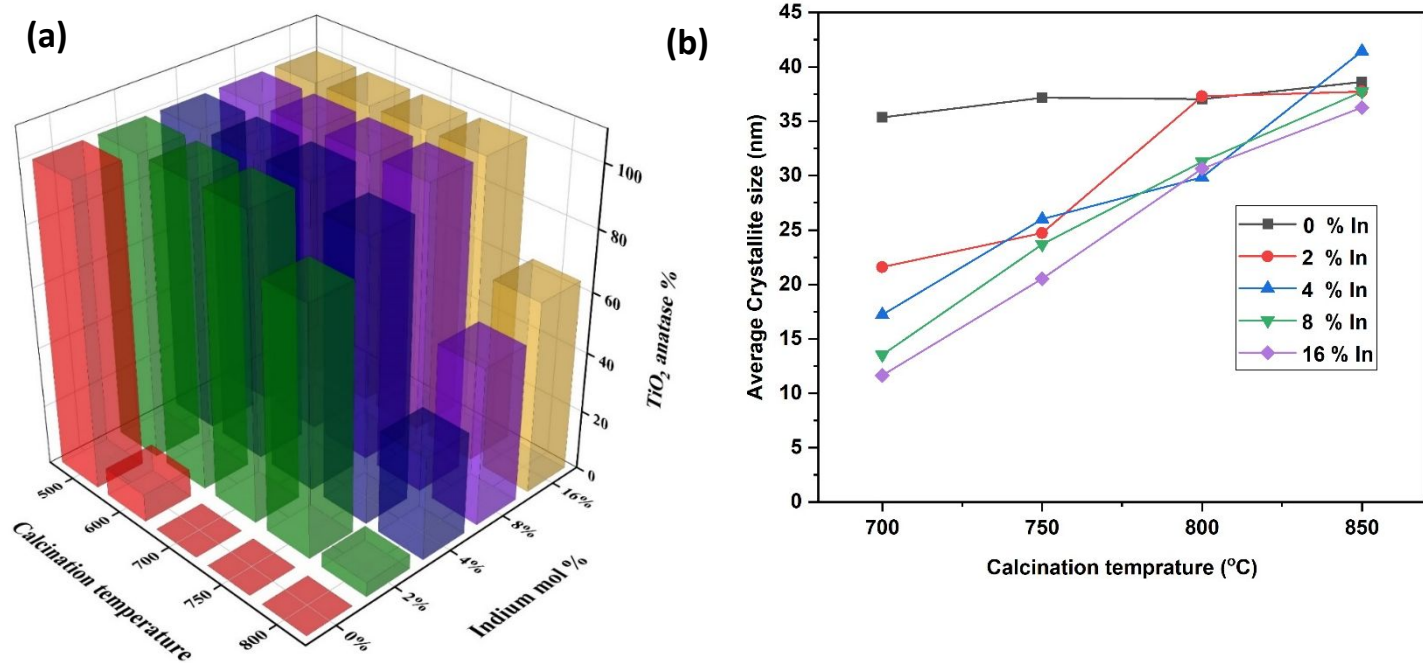


Fig. 8. (a) The anatase phase percentage of In-TiO₂ samples at various calcination temperature (b) the average crystallite size of In-TiO₂ at various calcination temperatures

Table. 1. Anatase and rutile percentages of In-TiO₂ samples at various calcination temperatures

Samples	500 °C		600 °C		700 °C		750 °C		800 °C		850 °C		900 °C	
	A	R	A	R	A	R	A	R	A	R	A	R	A	R
0 % In-TiO ₂	100	-	9.31	90.69	-	100	-	100	-	100	-	100	-	100
2 % In-TiO ₂	100	-	100	-	100	-	81.94	18.06	4.87	95.13	-	100	-	100
4 % In-TiO ₂	100	-	100	-	100	-	92.58	7.42	34.27	65.73	-	100	-	100
8 % In-TiO ₂	100	-	100	-	100	-	100	-	52.49	47.51	-	100	-	100
16 % In-TiO ₂	100	-	100	-	100	-	100	-	63.73	36.27	-	100	-	100

*A= Anatase; R = Rutile

Raman spectroscopy:

Raman spectra of TiO₂ anatase (0 % In-TiO₂ @ 500 °C), TiO₂ rutile (0 % In-TiO₂ @ 700 °C) and In-TiO₂ samples (at 750 °C and 800 °C) are shown in Fig. 9. Raman modes of TiO₂ anatase such as E_g, B_{1g}, A_{1g} or B_{1g} and E_g are noted around 135.11 cm⁻¹, 390.36 cm⁻¹, 510.65 cm⁻¹ and 632.54 cm⁻¹, respectively^{25, 39}. The distinctive Raman modes of TiO₂ rutile such as B_{2g} and 3E_g are observed around 439.98 cm⁻¹ and 602.94 cm⁻¹, respectively^{25, 39}. The anatase peaks of In-TiO₂ are slightly blue-shifted, as compared to pure TiO₂. This is ascribed to the generation of defects and oxygen vacancies in TiO₂ by In doping^{73, 74}. The bond between O-Ti-O is modified by In doping in the crystal lattice of TiO₂⁷³. It is also suggested that a high concentration of In³⁺ may induce a stress in the TiO₂ framework⁷⁰. This is also evidenced by the variations in the average crystallite size from the XRD results. Raman peaks In₂O₃ are not clearly differentiated in the In-TiO₂ samples. This is ascribed to the low concentration of In and the peaks of In₂O₃ (e.g. 133 cm⁻¹ - stretching vibration of In-O bond of InO₆ unit) are coincided well with the TiO₂ anatase peaks (E_g at 135.11 cm⁻¹)^{75, 76}.

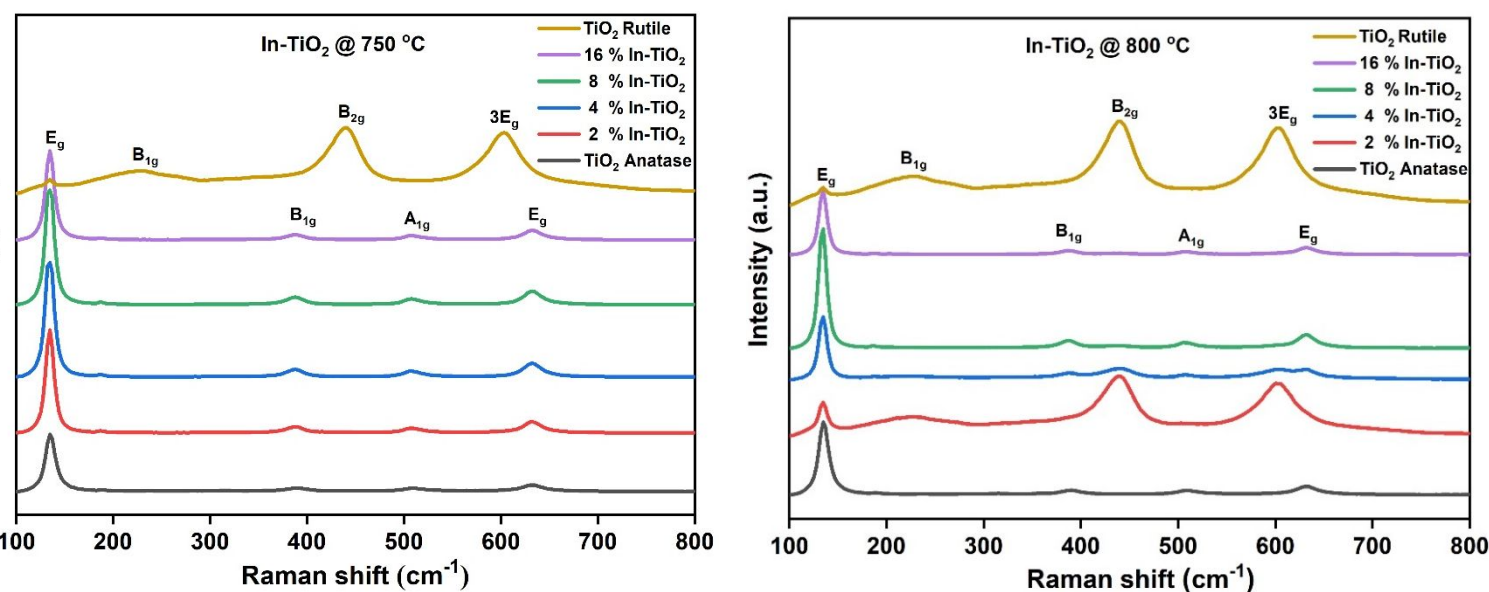


Fig. 9. Raman spectra of In-TiO₂ samples at (a) 750 °C and (b) 800 °C

Moreover, the variations in Raman peak intensity and area perfectly endorse the differences in anatase and rutile TiO₂ percentages (Table 1) by In doping.

X-ray photoelectron spectroscopy (XPS):

The chemical oxidation states of the elements in In-TiO₂ are examined by XPS and the results are displayed in Fig. 10. The survey spectrum of 16 % In-TiO₂ (800 °C) is displayed in Fig. 10 (a). The peaks of oxygen, titanium and indium are clearly noted at their corresponding binding energies. As shown in Fig. 10 (b), the electron binding energies of Ti 2p_{3/2} and Ti 2p_{1/2} are observed at 458.78 eV and 464.45 eV respectively, suggesting titanium is in +4 oxidation state (Ti⁴⁺)⁴⁶. There are no peaks observed for Ti³⁺ and Ti²⁺ states. The electronegativity of In³⁺ (1.78) is higher than that of Ti⁴⁺ (1.54), which may cause an electron transfer from Ti⁴⁺ and O²⁻ to In³⁺⁶⁹. This kind of electron transfer could make an electron deficiency in Ti⁴⁺ and O²⁻ and therefore the binding energies of Ti 2p and O 1s are increased. Moreover, In ions may be doped into TiO₂ crystal lattice through substitutional mode (*i.e.* lattice metal ions are substituted by the dopant metal ions) because the ionic radius of In³⁺ (0.08 nm) is higher than that of Ti⁴⁺ (0.06 nm)⁴⁷. Therefore, new energy levels could be incorporated below the CB of TiO₂ *via* In doping^{77, 78}. O 1s spectrum of In-TiO₂ is comprised of three component peaks at 530.01 eV, 531.62 eV and 532.32 eV, respectively. The main peak at 530.01 eV is ascribed to lattice oxygen (O²⁻) in TiO₂. The additional peaks at 531.62 eV and 532.32 eV are attributed to In-O and surface free hydroxyl groups, respectively^{69, 72}. Fig 10 (e) clearly shows that the impact of In dopant concentration on the surface hydroxyl groups and oxygen vacancies of TiO₂ crystal lattice. The presence of more surface hydroxyl groups is favourable to improving the photocatalytic activity⁴⁶ through the formation of hydroxyl radicals. In³⁺ peaks for In 3d_{5/2} and In 3d_{3/2} are observed at 444.74 eV and 452.29 eV (Fig. 10 (d)), respectively⁷⁴, indicating In is existed in the form of indium oxide. Fig 10 (f) shows that the binding energy values of In 3d peaks are decreased with increase of In dopant concentration. The existence of a small C 1s peak is attributed to adventitious carbon from the synthesis and calcination processes⁷².

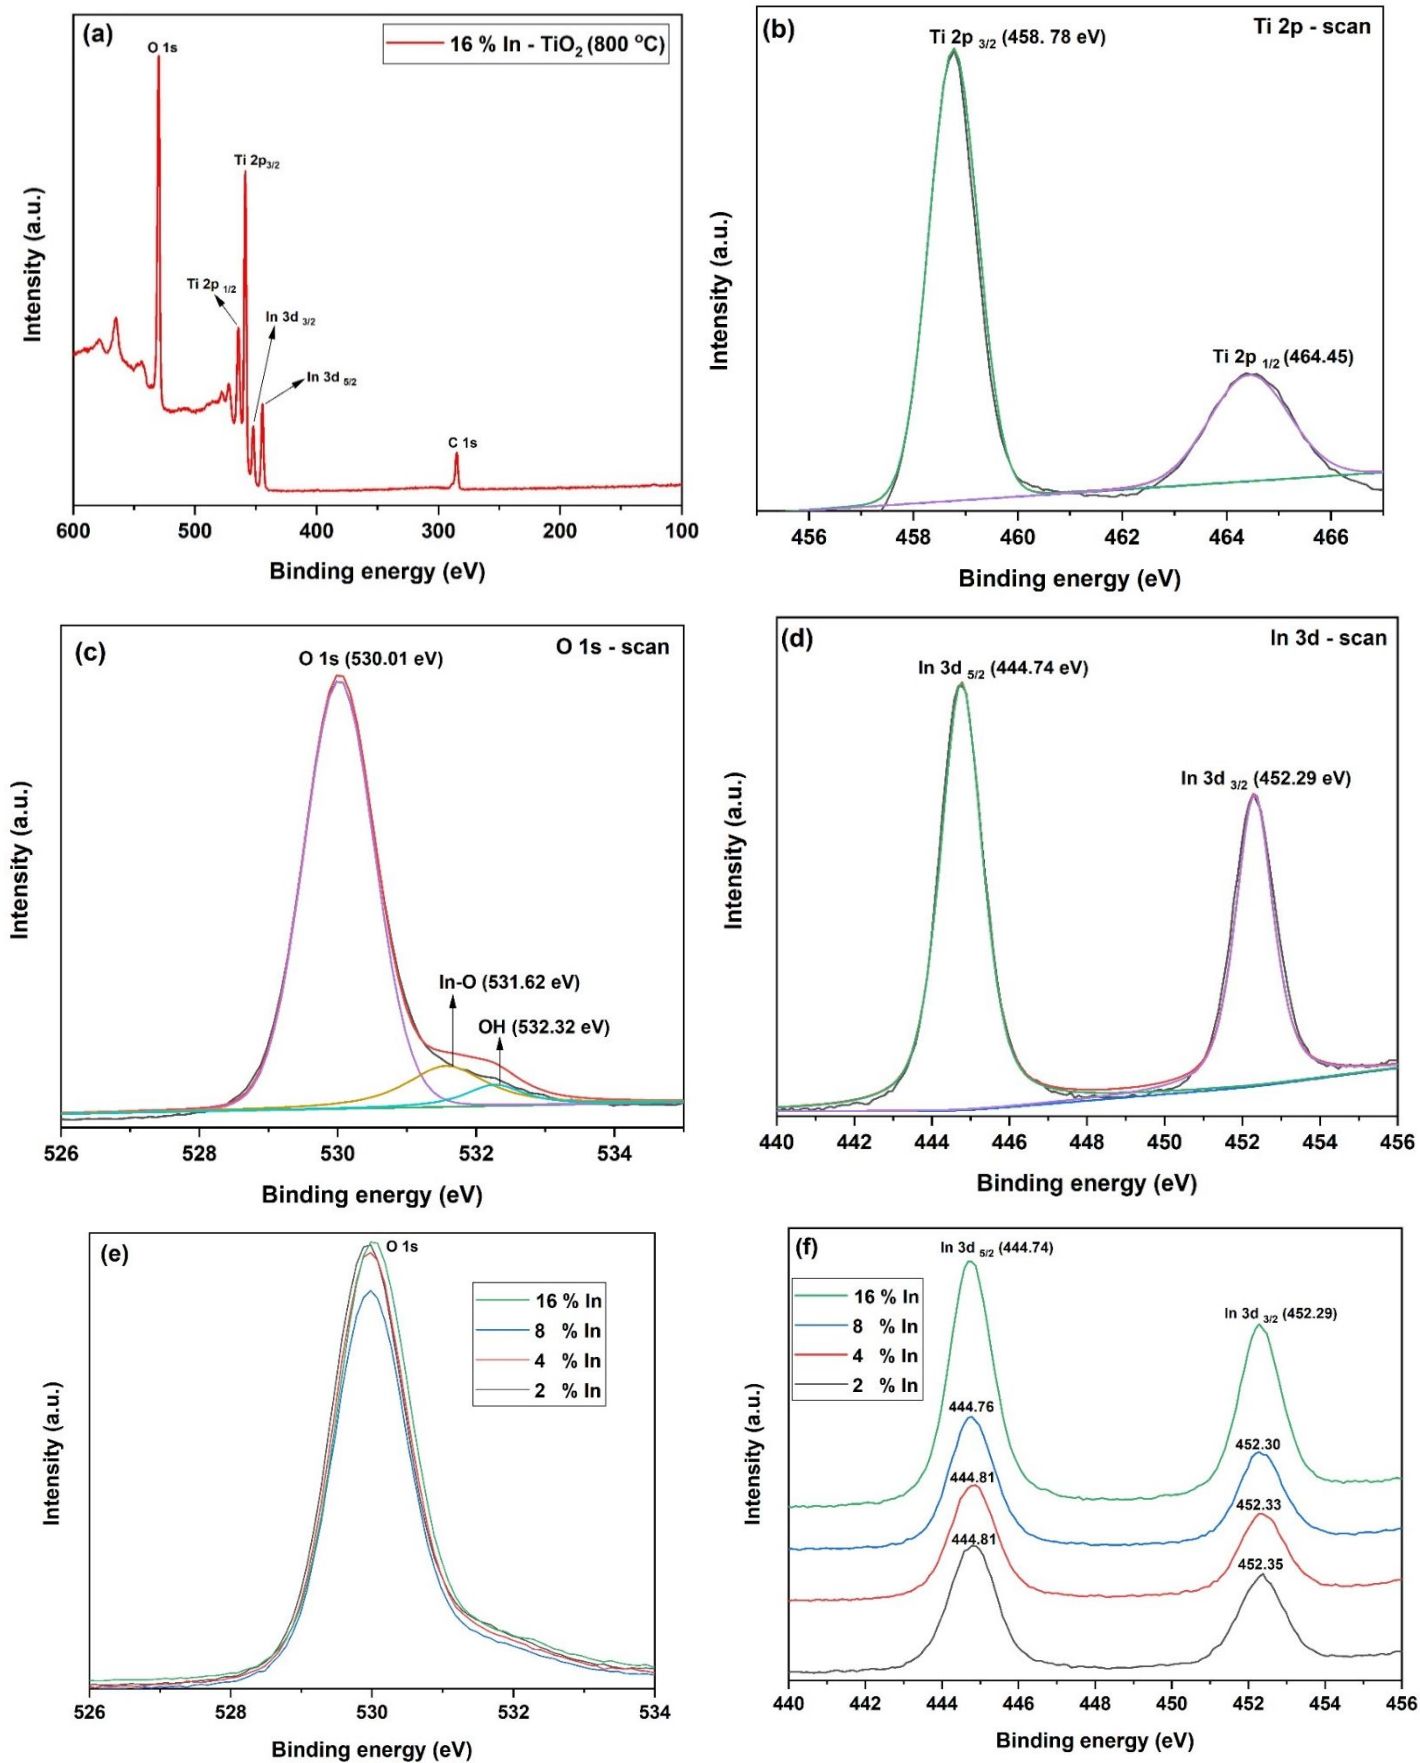


Fig. 10. XPS spectra of In-TiO₂ at 800 °C (a) survey spectrum (b) Ti 2p (c) O 1s (d) In 3d (e) O 1s of 2, 4, 8 and 16 % In-TiO₂ (f) In 3d of 2, 4, 8 and 16 % In-TiO₂

Photoluminescence (PL):

PL spectra of pure TiO₂ anatase (0 % In-TiO₂ @ 500 °C) and In-TiO₂ (800 °C) are shown in Fig. 11. PL emission spectra are accredited to the recombination of electron-holes *via* a non-irradiative process inside TiO₂⁴⁷. PL signals are mainly attributed to the existence of surface states and defects⁷⁴. The peaks noticed at 461 nm are associated with TiO₂ anatase^{46, 68}. A peak noted at 423 nm is related to the formation of oxygen vacancies in TiO₂ during In doping. The peaks observed at 485 nm and 527 nm are ascribed to the transition of electrons (two trapped and one trapped) from the oxygen vacancies to the VB of TiO₂⁴⁷.

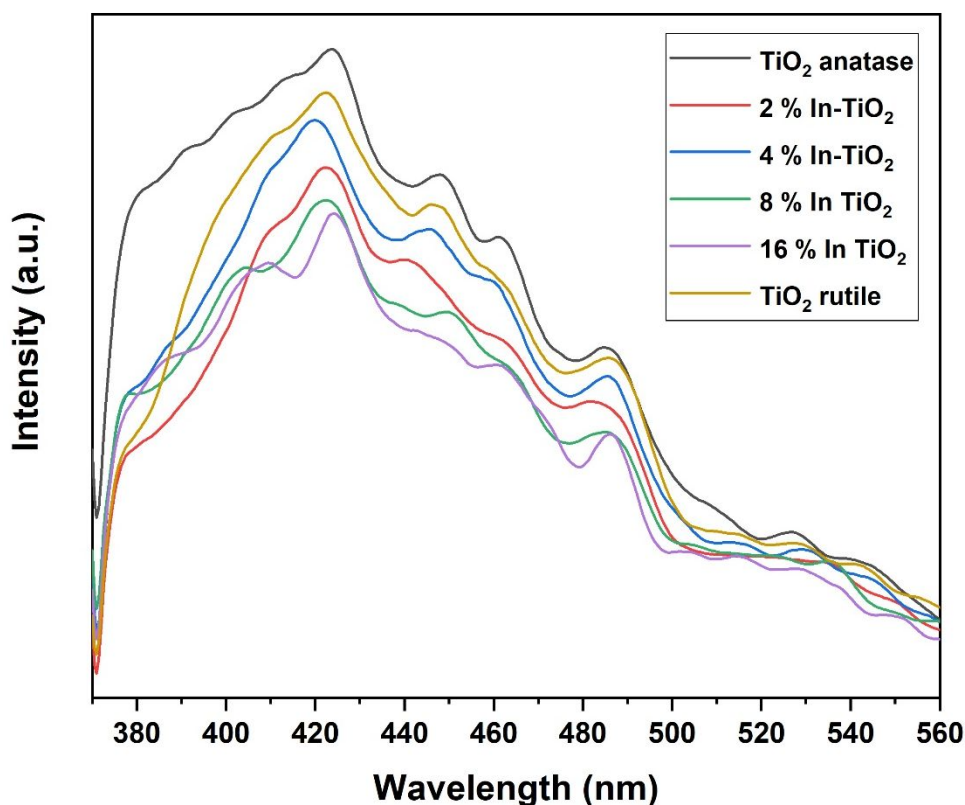


Fig. 11. PL spectra of TiO₂ anatase, TiO₂ rutile and In-TiO₂ samples

The energy of levels of two oxygen vacancies are positioned around 0.51 eV and 0.82 eV⁴⁷. For the electron-hole recombination process, the photo-generated electrons could be transferred first from the CB to the oxygen vacancies (non-radiative process) and then to the VB (fluorescence emission) of TiO₂. Fig 11 shows that the emission intensity of PL peaks is significantly decreased with an increase in In dopant concentration. This indicates that the transition of electrons from the CB of TiO₂ to the oxygen vacancies is suppressed by the creation of new energy levels through In doping. The surface state energy level of In might be positioned between the CB of TiO₂ and energy level of oxygen vacancies⁴⁷. The formation of In-derived states in the band gap is consistent with the results from the DFT+U

calculations showing In $5s$ states between the VB and CB of TiO_2 . PL results show that the photo-generated electron hole recombination process on TiO_2 can be effectively suppressed by In doping, leading to a higher photocatalytic activity^{68, 75, 79}.

Photocurrent response analysis:

PL results were further supported by the transient photocurrent measurements. Fig. 12 (a) shows the transient photocurrent response of anatase, rutile and In- TiO_2 samples at +1.0 V vs SCE. Upon irradiation of the TiO_2 electrode, a significant increase in the anodic current was observed due to the photoexcitation of electrons to the conduction band. The difference in current of the TiO_2 working electrode between dark and light conditions is termed as photocurrent. The anodic photocurrent observed on nano-particulate electrodes is due to the diffusion of majority charge carriers through the particulate film to the supporting contact electrode. The current-time response is shown in Fig. 12 (a) under chopped irradiation. The steady-state photocurrent densities from the samples at +1.0 V are shown in Fig. 12 (b). The photocurrent densities of most of the In- TiO_2 samples are higher than that of anatase and rutile electrodes. This correlates with the DFT studies whereby new intra-band gap states due to In doping give rise to a greater charge carrier density under irradiation and therefore improved anodic photocurrent. The best photocurrent density is observed with the 16 % In- TiO_2 annealed at 800 °C. The photocurrent density of 8 % In- TiO_2 annealed at 800 °C is much lower than the other samples. This may be ascribed to the similar percentages of anatase (52.49 %) and rutile (47.51 %).

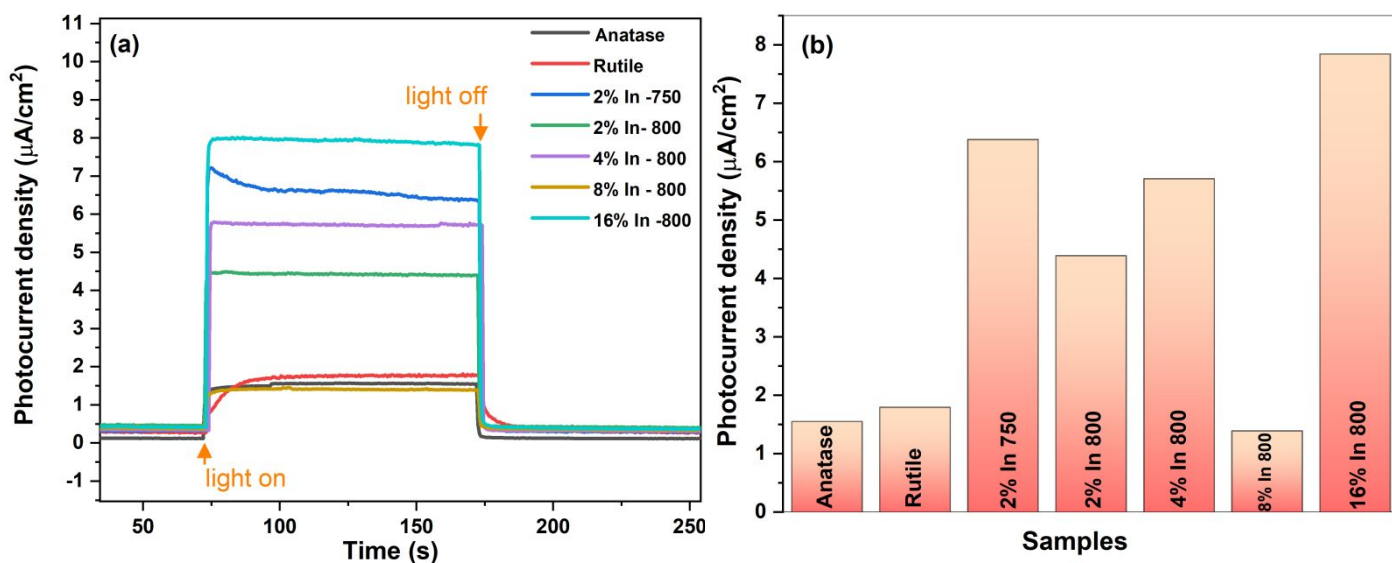


Fig. 12. (a) The photocurrent density of anatase, rutile and various In- TiO_2 samples at +1.0 V vs SCE, and (b) steady state photocurrent density of anatase, rutile and various In- TiO_2 samples at +1.0 V.

Photocatalytic H₂ production:

The samples were tested for photocatalytic H₂ production efficiency *via* water splitting under simulated solar light irradiation. H₂ production efficiency of 2 % In-TiO₂ @ 700 °C, 2 % In-TiO₂ @ 750 °C, 4 % In-TiO₂ @ 750 °C and 16 % In-TiO₂ @ 800 °C are shown in Fig. 13. H₂ production efficiency order of In-TiO₂ samples is 2 % In-TiO₂ @700 °C (105.2 μL of H₂/h) > 4 % In-TiO₂ @750 °C (31.5 μL of H₂/h) > 2 % In-TiO₂ @750 °C (28.2 μL of H₂/h) > 16 % In-TiO₂ @800 °C (25.6 μL of H₂/h) > 2 % In-TiO₂ @850 °C (19.20 μL of H₂/h). The efficiency of pure anatase and rutile were 145.6 μL of H₂/h and 65.4 μL of H₂/h, respectively. The photocatalytic activity of 2 % In-TiO₂ @700 °C is more comparable with that of pure anatase (0 % In-TiO₂ @500 °C). Nevertheless, the efficiency of In-TiO₂ is strongly influenced by the anatase percentage, calcination temperature and In concentration. The water splitting efficiency of TiO₂ is decreased with increasing of In content. This is ascribed to poor dispersion, agglomeration, and decrease of active surface area at high In content^{80, 81}. It is also noticed that the colour of nanoparticles was changed from white to black during 6 h of light irradiation. This is accredited to the photo-reduction of In(III) to In(I) or In(0), indicating the poisoning of catalyst surface under prolonged light irradiation. The excess of In dopant could act also as an electron-hole recombination centre near the CB of TiO₂⁸⁰. It could be rectified with the help of a suitable co-catalyst⁸². There are no detailed studies for the water splitting efficiency of In-TiO₂ samples. In a recent study, the similar kind of trend was observed by Zhong *et al.*⁸⁰ for In doped barium titanate (In-BaTiO₃). The efficiency of In-BaTiO₃ was further improved with the help of cadmium selenide co-catalyst. However, the efficiency was again dropped when the In concentration was more than 2 %.

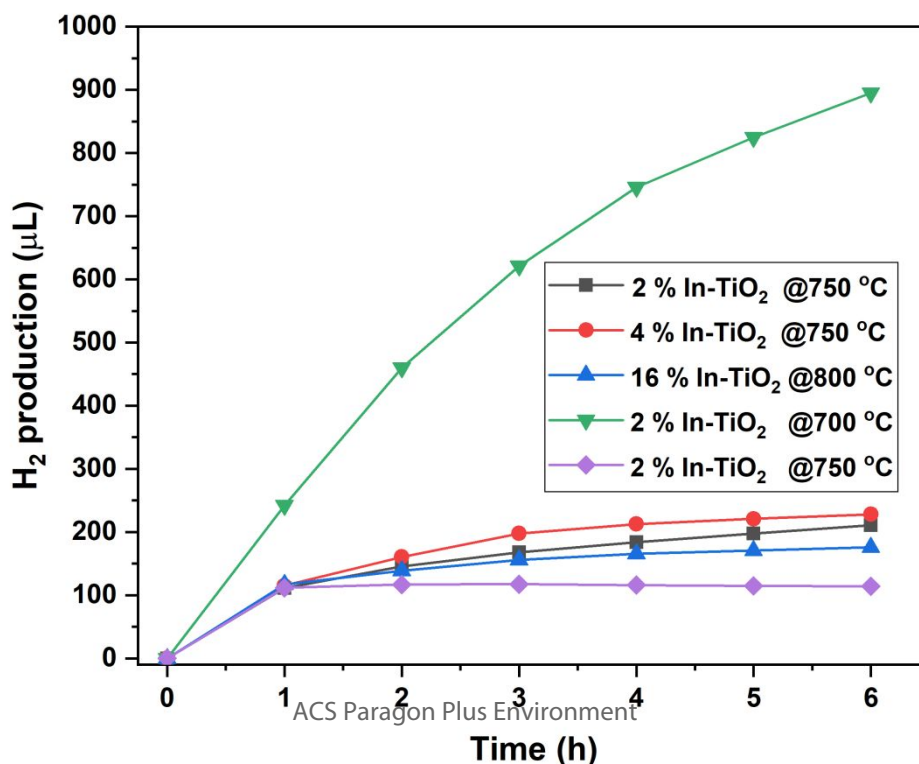


Fig. 13. H₂ production efficiency of 0.5 g/L of In-TiO₂ under simulated solar light irradiation

XRD, Raman, PL and photocurrent results verified DFT calculations for the generation of gap states (In- 5s states), variations in crystal lattice parameters and oxygen vacancies. DFT calculations also demonstrate the influence of In₂O₃ formation on anatase through the In₄O₆-a101 model. XRD results confirmed that the lattice parameters and cell volume of anatase are not significantly influenced by In doping. The variations in the anatase and rutile percentages for In-TiO₂ samples are endorsed by the differences in E_g and B_{2g} peaks in the Raman spectra. The increase in the lifetime of charge carriers after In doping is supported through PL and photocurrent analyses. The transition of electrons between oxygen vacancies and In energy levels is evidenced by the PL spectra. In dopant could improve the current density of TiO₂ and enhance the separation of charge carriers on the photocatalyst surface. During the photo-absorption phenomena, two electronic transitions are possible: (i) from the VB of TiO₂ to CB; (ii) from the VB of TiO₂ to In- 5s state⁴⁸. This kind of electron transfer could favourably separate the photo-generated electron-hole pairs and increase their life time on the catalyst surface⁷⁴. Besides, the Bronsted acidity of In-TiO₂ surface could further promote the adsorption of pollutant/microbes and H₃O⁺/OH⁻ species to enhance the production of hydroxyl radicals⁷¹. Hinojosa-Reyes *et al.*⁷⁰ suggested that In dopant could also act as discrete reactive sites to accelerate the adsorption of pollutant on the photocatalyst surface. They found that In-TiO₂ coated perlite-granules showed the highest efficiency for the photochemical decomposition of ethylbenzene in contrast to pure TiO₂. The decrease of average crystallite size from the XRD results reveals the stabilization of TiO₂ anatase phase by In dopant during calcination⁷⁴. It was evidenced that the small particle size of In-TiO₂ is beneficial to enhance the photocatalytic activity as compared to pure TiO₂⁴². DFT results describe that the substitutional doping of In in the TiO₂ anatase crystal restricts the bond breaking and reformation to avoid the ART at high temperature²³. Some studies suggested that In dopant on TiO₂ could also act as an electron trap to stimulate the electron transfer to surface adsorbed oxygen for the generation of reactive oxygen species^{42, 68}. Even though, a high concentration of In could preserve the anatase content (more than 700 °C calcination temperature) in this present work, the water splitting efficiency is influenced by the concentration of In⁸³. This is accredited to the poor bonding interactions between In-TiO₂, water and glycerol, which could reduce the dispersion of nanoparticles in water⁸¹. A high concentration of In leads to the formation of In₂O₃, which could reduce the interface area between the dopant and TiO₂. In addition to that, a thin layer of In₂O₃ could cover the

1
2
3 reactive sites of TiO₂ responsible for water splitting⁸⁴. The high grain size of In-TiO₂
4 (samples at high calcination temperature) affects the mass transport and accessibility of the
5 reactants at the photocatalyst surface⁸³. H₂ production efficiency of 2 % In-TiO₂ calcined at
6 700 °C is more comparable with respect to pure anatase (0 % In-TiO₂ calcined at 500 °C) and
7 it could be used as a thermally stable photocatalytic coating. Future studies should be focused
8 to improve the dispersion of In-TiO₂ calcined at high temperatures.
9
10
11
12
13
14

15 **4. Conclusions:**

16
17 The effect of indium doping on the anatase rutile transition of TiO₂ was systematically
18 studied in a temperature range of 500 °C – 900 °C. Theoretical and experimental
19 characterizations were performed for the as-synthesised In-TiO₂ nanoparticles. The results
20 shown that In is an effective dopant to preserve the anatase content of TiO₂, up to 64 % at a
21 temperature as high as 800 °C. The ART of TiO₂ is strongly influenced by the In dopant
22 concentration. XRD results revealed that In³⁺ retards the crystallization of TiO₂ through the
23 substitution of Ti⁴⁺ ions. Raman spectroscopy shows the generation of defects and oxygen
24 vacancies in TiO₂ by In doping. The lifetime of photo-generated charge carriers in TiO₂ could
25 also be extended by In doping.
26
27
28
29
30
31

32
33 DFT results indicate that charge compensating oxygen vacancies will form spontaneously
34 in In-doped TiO₂ and that formation of further, reducing oxygen vacancies have moderate
35 energy costs. Considerations of oxygen vacancy formation as the primary mechanism in the
36 ART is therefore insufficient in accounting for the inhibition of the transition reported in the
37 experimental findings. The computed DOS plots for In-doped bulk anatase TiO₂ reveal that,
38 upon formation of reducing oxygen vacancies, states emerge in the bandgap due to
39 localisation of charge in the vicinity of the In-dopants.
40
41
42
43
44

45 Our model for In₂O₃ formation at the anatase (101) surface indicates that the In₄O₆
46 nanocluster is bound at the surface with a moderate adsorption energy. We predict that for
47 higher calcination temperatures the In₂O₃ at the surface will desorb or migrate and aggregate
48 at the surface. The latter outcome would explain the enhanced In₂O₃ signals in the XRD
49 spectrum for those samples calcined at higher temperatures. Formation of a reducing oxygen
50 vacancy in the surface bound In₂O₃ has moderate formation energies with the resulting excess
51 charge localizing at In sites on the surface. The presence of In₂O₃ at the surface extends the
52 VBM of the titania support to higher energies and, in combination with In-derived states in
53 the bandgap for both stoichiometric and reduced In₂O₃, a red shift in the light absorption edge
54 is predicted.
55
56
57
58
59
60

1
2
3 The photocatalytic activity of 2 % In-TiO₂ @700 °C is more similar with that of pure
4 anatase. It could be further improved with the help of appropriate co-catalyst. The
5 photocatalytic activity is strongly affected by the calcination temperature and anatase
6 percentage. Overall, the results demonstrate that In is an effective dopant for the fabrication
7 of thermally stable TiO₂ with photocatalytic activity.
8
9
10
11
12
13
14

15 **Acknowledgements:**

16
17 The authors are grateful to the Renewable Engine project funded by European Union's
18 INTERREG VA Programme, managed by the Special EU Programmes Body (SEUPB), with
19 match funding provided by the Department for the Economy and Department of Jobs,
20 Enterprise and Innovation in Ireland. SR and MN acknowledge the support from Science
21 Foundation Ireland through the ERA. Net for Materials Research and Innovation (M-
22 ERA.Net 2), Horizon 2020 grant agreement number 685451, SFI Grant Number SFI/16/M-
23 ERA/3418 (RATOCAT). We acknowledge access to SFI funded computing resources at
24 Tyndall Institute and the SFI/HEA funded Irish Centre for High End Computing. We are
25 grateful for support from the COST Action CM1104 "Reducible Metal Oxides, Structure and
26 Function". AS would like to acknowledge the financial support via VCRS scholarship from
27 Ulster University. PKS and TB would like to acknowledge Invest Northern Ireland for
28 financial assistance (R&D project Novel Dielectrics RD071392).
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43

44 **References:**

- 45 1. Kogo, A.; Sanehira, Y.; Numata, Y.; Ikegami, M.; Miyasaka, T., Amorphous Metal
46 Oxide Blocking Layers for Highly Efficient Low-Temperature Brookite TiO₂-Based
47 Perovskite Solar Cells. *ACS Appl. Mater. Interfaces* **2018**, *10*, 2224-2229.
- 48 2. Huang, J.; Li, G.; Zhou, Z.; Jiang, Y.; Hu, Q.; Xue, C.; Guo, W., Efficient
49 Photocatalytic Hydrogen Production over Rh and Nb Codoped TiO₂ Nanorods. *Chem. Eng. J.*
50 **2018**, *337*, 282-289.
- 51 3. Low, J.; Qiu, S.; Xu, D.; Jiang, C.; Cheng, B., Direct Evidence and Enhancement of
52 Surface Plasmon Resonance Effect on Ag-Loaded TiO₂ Nanotube Arrays for Photocatalytic
53 CO₂ Reduction. *Appl. Surf. Sci.* **2018**, *434*, 423-432.
- 54 4. Ganguly, P.; Byrne, C.; Breen, A.; Pillai, S. C., Antimicrobial Activity of
55 Photocatalysts: Fundamentals, Mechanisms, Kinetics and Recent Advances. *Appl. Catal., B*
56 **2018**, *225*, 51-75.
57
58
59
60

5. Hazarika, D.; Saikia, D.; Gupta, K.; Mandal, M.; Karak, N., Photoluminescence, Self Cleaning and Photocatalytic Behavior of Waterborne Hyperbranched Polyester/Carbon Dot@TiO₂ Nanocomposite. *Chemistry Select* **2018**, *3*, 6126-6135.
6. Lyulyukin, M.; Kolinko, P.; Selishchev, D.; Kozlov, D., Hygienic Aspects of TiO₂-Mediated Photocatalytic Oxidation of Volatile Organic Compounds: Air Purification Analysis Using a Total Hazard Index. *Appl. Catal., B* **2018**, *220*, 386-396.
7. Pastrana-Martínez, L. M.; Morales-Torres, S.; Carabineiro, S. A.; Buijnsters, J. G.; Figueiredo, J. L.; Silva, A. M.; Faria, J. L., Photocatalytic Activity of Functionalized Nanodiamond-TiO₂ Composites Towards Water Pollutants Degradation under UV/Vis Irradiation. *Appl. Surf. Sci.* **2018**, *458*, 839-848..
8. Kumaravel, V.; Mathew, S.; Bartlett, J.; Pillai, S. C., Photocatalytic Hydrogen Production Using Metal Doped TiO₂: A Review of Recent Advances. *Appl. Catal., B* **2019**, *244*, 1021-1064.
9. Li, Y.; Lv, K.; Ho, W.; Dong, F.; Wu, X.; Xia, Y., Hybridization of Rutile TiO₂ (Rt-TiO₂) with g-C₃N₄ Quantum Dots (CN Qds): An Efficient Visible-Light-Driven Z-Scheme Hybridized Photocatalyst. *Appl. Catal., B* **2017**, *202*, 611-619.
10. Boningari, T.; Inturi, S. N. R.; Suidan, M.; Smirniotis, P. G., Novel one-step synthesis of sulfur doped-TiO₂ by flame spray pyrolysis for visible light photocatalytic degradation of acetaldehyde. *Chem. Eng. J.* **2018**, *339*, 249-258.
11. Vignesh, K.; Suganthi, A.; Rajarajan, M.; Sakthivadivel, R., Visible Light Assisted Photodecolorization of Eosin-Y in Aqueous Solution Using Hesperidin Modified TiO₂ Nanoparticles. *Appl. Surf. Sci.* **2012**, *258*, 4592-4600.
12. Moradi, V.; Jun, M. B.; Blackburn, A.; Herring, R. A., Significant Improvement in Visible Light Photocatalytic Activity of Fe Doped TiO₂ Using an Acid Treatment Process. *Appl. Surf. Sci.* **2018**, *427*, 791-799.
13. Vignesh, K.; Priyanka, R.; Hariharan, R.; Rajarajan, M.; Suganthi, A., Fabrication of CdS and CuWO₄ Modified TiO₂ Nanoparticles and Its Photocatalytic Activity under Visible Light Irradiation. *J. Ind. Eng. Chem.* **2014**, *20*, 435-443.
14. Li, J.; Zhang, M.; Li, Q.; Yang, J., Enhanced Visible Light Activity on Direct Contact Z-Scheme G-C₃N₄-TiO₂ Photocatalyst. *Appl. Surf. Sci.* **2017**, *391*, 184-193.
15. Liu, L.; Zhao, H.; Andino, J. M.; Li, Y., Photocatalytic CO₂ Reduction with H₂O on TiO₂ Nanocrystals: Comparison of Anatase, Rutile, and Brookite Polymorphs and Exploration of Surface Chemistry. *ACS Catal.* **2012**, *2*, 1817-1828.
16. Zhang, J.; Zhou, P.; Liu, J.; Yu, J., New Understanding of the Difference of Photocatalytic Activity among Anatase, Rutile and Brookite TiO₂. *Phys. Chem. Chem. Phys.* **2014**, *16*, 20382-20386.
17. Koltzakidou, A.; Antonopoulou, M.; Evgenidou, E.; Konstantinou, I.; Giannakas, A.; Papadaki, M.; Bikiaris, D.; Lambropoulou, D., Photocatalytical Removal of Fluorouracil Using TiO₂-P25 and N/S Doped TiO₂ Catalysts: A Kinetic and Mechanistic Study. *Sci. Total Environ.* **2017**, *578*, 257-267.
18. Shayegan, Z.; Haghghat, F.; Lee, C.-S.; Bahloul, A.; Huard, M., Effect of Surface Fluorination of P25-TiO₂ on Adsorption of Indoor Environment Volatile Organic Compounds. *Chem. Eng. J.* **2018**, *346*, 578-589.
19. Mohamed, M. A.; Salleh, W.; Jaafar, J.; Ismail, A.; Nor, N. A. M.; Physics, Photodegradation of Phenol by N-Doped TiO₂ Anatase/Rutile Nanorods Assembled Microsphere under Uv and Visible Light Irradiation. *Mater. Chem. Phys.* **2015**, *162*, 113-123.
20. Fagan, R.; Synnott, D. W.; McCormack, D. E.; Pillai, S. C., An Effective Method for the Preparation of High Temperature Stable Anatase TiO₂ Photocatalysts. *Appl. Surf. Sci.* **2016**, *371*, 447-452.

21. Bossa, N.; Chaurand, P.; Levard, C.; Borschneck, D.; Miche, H.; Vicente, J.; Geantet, C.; Aguerre-Chariol, O.; Michel, F. M.; Rose, J., Environmental Exposure to TiO₂ Nanomaterials Incorporated in Building Material. *Environ. Pollut.* **2017**, *220*, 1160-1170.
22. Lin, C.-C.; Chen, W.-Y., Effect of Paint Composition, Nano-Metal Types and Substrate on the Improvement of Biological Resistance on Paint Finished Building Material. *Build. Environ.* **2017**, *117*, 49-59.
23. Hanaor, D. A.; Sorrell, C. C., Review of the Anatase to Rutile Phase Transformation. *J. Mater. Sci.* **2011**, *46*, 855-874.
24. Ding, K.; Miao, Z.; Hu, B.; An, G.; Sun, Z.; Han, B.; Liu, Z., Study on the Anatase to Rutile Phase Transformation and Controlled Synthesis of Rutile Nanocrystals with the Assistance of Ionic Liquid. *Langmuir* **2010**, *26*, 10294-10302.
25. Byrne, C.; Fagan, R.; Hinder, S.; McCormack, D. E.; Pillai, S. C., New Approach of Modifying the Anatase to Rutile Transition Temperature in TiO₂ Photocatalysts. *RSC Adv.* **2016**, *6*, 95232-95238.
26. Wang, C.-L.; Hwang, W.-S.; Chu, H.-L.; Lin, H.-J.; Ko, H.-H.; Wang, M.-C., Kinetics of Anatase Transition to Rutile TiO₂ from Titanium Dioxide Precursor Powders Synthesized by a Sol-Gel Process. *Ceram. Int.* **2016**, *42*, 13136-13143.
27. Khatun, N.; Tiwari, S.; Lal, J.; Tseng, C.-M.; Liu, S. W.; Biring, S.; Sen, S., Stabilization of Anatase Phase by Uncompensated Ga-V Co-Doping in TiO₂: A Structural Phase Transition, Grain Growth and Optical Property Study. *Ceram. Int.* **2018**, *44*, 22445-22455.
28. Nguyen, C.-C.; Nguyen, D. T.; Do, T.-O., A Novel Route to Synthesize C/Pt/TiO₂ Phase Tunable Anatase-Rutile TiO₂ for Efficient Sunlight-Driven Photocatalytic Applications. *Appl. Catal., B* **2018**, *226*, 46-52.
29. Potlog, T.; Dobromir, M.; Luca, D.; Onufrijevs, P.; Medvids, A.; Shamardin, A., Rutile to Anatase Phase Transition in TiO₂: Nb Thin Films by Annealing in H₂ Atmosphere. *Curr. Appl. Phys.* **2016**, *16*, 826-829.
30. Mathew, S.; Ganguly, P.; Rhatigan, S.; Kumaravel, V.; Byrne, C.; Hinder, S.; Bartlett, J.; Nolan, M.; Pillai, S., Cu-Doped TiO₂: Visible Light Assisted Photocatalytic Antimicrobial Activity. *Appl. Sci.* **2018**, *8*, 2067.
31. Huang, F.; Motealleh, B.; Zheng, W.; Janish, M. T.; Carter, C. B.; Cornelius, C. J., Electrospinning Amorphous SiO₂-TiO₂ and TiO₂ Nanofibers Using Sol-Gel Chemistry and Its Thermal Conversion into Anatase and Rutile. *Ceram. Int.* **2018**, *44*, 4577-4585.
32. Tsai, C.-M.; Song, C.-G.; Hung, Y.-C.; Jeong, Y.-G.; Oh, S. H.; Jeong, J. H.; Kim, H.; Huh, H.; Yoon, J.-W.; Sigmund, W., Carbon Induced Phase Transformation in Electrospun TiO₂/Multiwall Carbon Nanotube Nanofibers. *Ceram. Int.* **2017**, *43*, 3761-3768.
33. Da Silva, A. L.; Dondi, M.; Hotza, D., Self-Cleaning Ceramic Tiles Coated with Nb₂O₅-Doped-TiO₂ Nanoparticles. *Ceram. Int.* **2017**, *43*, 11986-11991.
34. Khatun, N.; Tiwari, S.; Lal, J.; Tseng, C.-M.; Liu, S. W.; Biring, S.; Sen, S., Stabilization of Anatase Phase by Uncompensated Ga-V Co-Doping in TiO₂: A Structural Phase Transition, Grain Growth and Optical Property Study. *Ceram. Int.* **2018**, *44*, 22445-22455.
35. Li, J.; Xu, X.; Liu, X.; Qin, W.; Pan, L., Novel Cake-Like N-Doped Anatase/Rutile Mixed Phase TiO₂ Derived from Metal-Organic Frameworks for Visible Light Photocatalysis. *Ceram. Int.* **2017**, *43*, 835-840.
36. Giraldi, T. R.; Dias, J. A.; Baggio, C. M.; Maestrelli, S. C.; Oliveira, J. A., Anatase-to-Rutile Transition in Co-Doped TiO₂ Pigments. *J. Sol-Gel Sci. Technol.* **2017**, *83*, 115-123.
37. Yadav, A. K.; Khatun, N.; Kumar, S.; Tseng, C.-M.; Biring, S.; Sen, S., Size and Strain Dependent Anatase to Rutile Phase Transition in TiO₂ Due to Si Incorporation. *J. Mater. Sci.- Mater. Electron.* **2017**, *28*, 19017-19024.

- 1
2
3 38. Kondamareddy, K. K.; Neena, D.; Lu, D.; Peng, T.; Lopez, M. A. M.; Wang, C.; Yu,
4 Z.; Cheng, N.; Fu, D.; Zhao, X.-Z., Ultra-Trace (Parts Per Million-Ppm) W^{6+} Dopant Ions
5 Induced Anatase to Rutile Transition (ART) of Phase Pure Anatase TiO_2 Nanoparticles for
6 Highly Efficient Visible Light-Active Photocatalytic Degradation of Organic Pollutants.
7 *Appl. Surf. Sci.* **2018**, *456*, 676-693.
- 8 39. Khatun, N.; Rajput, P.; Bhattacharya, D.; Jha, S.; Biring, S.; Sen, S., Anatase to Rutile
9 Phase Transition Promoted by Vanadium Substitution in TiO_2 : A Structural, Vibrational and
10 Optoelectronic Study. *Ceram. Int.* **2017**, *43*, 14128-14134.
- 11 40. Makal, P.; Das, D., Self-Doped TiO_2 Nanowires in TiO_2 -B Single Phase, TiO_2 -
12 B/Anatase and TiO_2 -Anatase/Rutile Heterojunctions Demonstrating Individual Superiority in
13 Photocatalytic Activity under Visible and UV Light. *Appl. Surf. Sci.* **2018**, *455*, 1106-1115.
- 14 41. Reddy, B. M.; Sreekanth, P. M.; Reddy, E. P.; Yamada, Y.; Xu, Q.; Sakurai, H.;
15 Kobayashi, T., Surface Characterization of La_2O_3 - TiO_2 and V_2O_5/La_2O_3 - TiO_2 Catalysts. *J.*
16 *Phys. Chem. B* **2002**, *106*, 5695-5700.
- 17 42. Tahir, M.; Amin, N. S., Photocatalytic CO_2 Reduction and Kinetic Study over in/ TiO_2
18 Nanoparticles Supported Microchannel Monolith Photoreactor. *Appl. Catal., B* **2013**, *467*,
19 483-496.
- 20 43. Yu, Y.; Wang, E.; Yuan, J.; Cao, Y., Enhanced Photocatalytic Activity of Titania with
21 Unique Surface Indium and Boron Species. *Appl. Surf. Sci.* **2013**, *273*, 638-644.
- 22 44. Zhang, Y.; Xu, H.; Xu, Y.; Zhang, H.; Wang, Y., The Effect of Lanthanide on the
23 Degradation of Rb in Nanocrystalline Ln/ TiO_2 Aqueous Solution. *J. Photochem. Photobiol.,*
24 *A* **2005**, *170*, 279-285.
- 25 45. Byrne, C.; Moran, L.; Hermosilla, D.; Merayo, N.; Blanco, Á.; Rhatigan, S.; Hinder,
26 S.; Ganguly, P.; Nolan, M.; Pillai, S. C., Effect of Cu Doping on the Anatase-to-Rutile Phase
27 Transition in TiO_2 Photocatalysts: Theory and Experiments. *Appl. Catal., B* **2019**, *246*, 266-
28 276.
- 29 46. Tahir, M.; Amin, N. S., Indium-Doped TiO_2 Nanoparticles for Photocatalytic CO_2
30 Reduction with H_2O Vapors to CH_4 . *Appl. Catal., A* **2015**, *162*, 98-109.
- 31 47. Wang, E.; Yang, W.; Cao, Y., Unique Surface Chemical Species on Indium Doped
32 TiO_2 and Their Effect on the Visible Light Photocatalytic Activity. *J. Phys. Chem. C* **2009**,
33 *113*, 20912-20917.
- 34 48. Wang, E.; Zhang, P.; Chen, Y.; Liu, Z.; He, T.; Cao, Y., Improved Visible-Light
35 Photocatalytic Activity of Titania Activated by Nitrogen and Indium Modification. *J. Phys.*
36 *Chem. C* **2012**, *22*, 14443-14449.
- 37 49. Iwaszuk, A.; Nolan, M., Charge Compensation in Trivalent Cation Doped Bulk Rutile
38 TiO_2 . *J. Phys.: Condens. Matter* **2011**, *23*, 334207.
- 39 50. Khan, M.; Lan, Z.; Zeng, Y., Analysis of Indium Oxidation State on the Electronic
40 Structure and Optical Properties of TiO_2 . *Materials* **2018**, *11*, 952.
- 41 51. Kresse, G.; Furthmüller, J., Efficiency of Ab-Initio Total Energy Calculations for
42 Metals and Semiconductors Using a Plane-Wave Basis Set. *Comput. Mater. Sci.* **1996**, *6*, 15-
43 50.
- 44 52. Kresse, G.; Furthmüller, J., Efficient Iterative Schemes for Ab-Initio Total-Energy
45 Calculations Using a Plane-Wave Basis Set. *Phys. Rev. B* **1996**, *54*, 11169.
- 46 53. Kresse, G.; Joubert, D., From ultrasoft pseudopotentials to the projector augmented-
47 wave method. *Phys. Rev. B.* **1999**, *59*, 1758-1775.
- 48 54. Blöchl, P. E., Projector Augmented-Wave Method. *Phys. Rev. B.* **1994**, *50*, 17953-
49 17979.
- 50 55. Anisimov, V. I.; Zaanen, J.; Andersen, O. K., Band Theory and Mott Insulators:
51 Hubbard U Instead of Stoner I. *Phys. Rev. B.* **1991**, *44*, 943-954.
- 52
53
54
55
56
57
58
59
60

- 1
2
3 56. Dudarev, S. L.; Botton, G. A.; Savrasov, S. Y.; Humphreys, C. J.; Sutton, A. P.,
4 Electron-energy-loss spectra and the structural stability of nickel oxide: An LSDA+U study.
5 *Phys. Rev. B.* **1998**, *57*, 1505-1509.
6
7 57. Carey, J. J.; Nolan, M., Dissociative adsorption of methane on the Cu and Zn doped
8 (111) surface of CeO₂. *Appl. Catal., B* **2016**, *197*, 324-336.
9
10 58. Nolan, M.; Elliott, S. D., The p-type conduction mechanism in Cu₂O: a first principles
11 study. *Phys. Chem. Chem. Phys.* **2006**, *8*, 5350-5358.
12
13 59. Morgan, B. J.; Watson, G. W., A DFT + U description of oxygen vacancies at the
14 TiO₂ rutile (1 1 0) surface. *Surf. Sci.* **2007**, *601*, 5034-5041.
15
16 60. Nolan, M.; Elliott, S. D.; Mulley, J. S.; Bennett, R. A.; Basham, M.; Mulheran, P.,
17 Electronic structure of point defects in controlled self-doping of the TiO₂ (110) surface:
18 Combined photoemission spectroscopy and density functional theory study. *Phys. Rev. B.*
19 **2008**, *77*, 235424.
20
21 61. Kowalski, P. M.; Camellone, M. F.; Nair, N. N.; Meyer, B.; Marx, D., Charge
22 Localization Dynamics Induced by Oxygen Vacancies on the TiO₂ Surface. *Phys. Rev. Lett.*
23 **2010**, *105*, 146405.
24
25 62. Henkelman, G.; Arnaldsson, A.; Jónsson, H., A Fast and Robust Algorithm for Bader
26 Decomposition of Charge Density. *Comput. Mater. Sci.* **2006**, *36*, 354-360.
27
28 63. Ilie, A. G.; Scarisoreanu, M.; Dutu, E.; Dumitrache, F.; Banici, A.-M.; Fleaca, C. T.;
29 Vasile, E.; Mihailescu, I. J. A. S. S., Study of Phase Development and Thermal Stability in as
30 Synthesized TiO₂ Nanoparticles by Laser Pyrolysis: Ethylene Uptake and Oxygen
31 Enrichment. *Appl. Surf. Sci.* **2018**, *427*, 798-806.
32
33 64. Boningari, T.; Inturi, S. N. R.; Suidan, M.; Smirniotis, P. G., Novel One-Step
34 Synthesis of Nitrogen-Doped TiO₂ by Flame Aerosol Technique for Visible-Light
35 Photocatalysis: Effect of Synthesis Parameters and Secondary Nitrogen (N) Source. *Chem.*
36 *Eng. J.* **2018**, *350*, 324-334.
37
38 65. Sharma, P. K.; Cortes, M. A. L.; Hamilton, J. W.; Han, Y.; Byrne, J. A.; Nolan, M.,
39 Surface modification of TiO₂ with copper clusters for band gap narrowing. *Catal. Today*
40 **2019**, *321*, 9-17.
41
42 66. Pillai, S. C.; Periyat, P.; George, R.; McCormack, D. E.; Seery, M. K.; Hayden, H.;
43 Colreavy, J.; Corr, D.; Hinder, S. J., Synthesis of high-temperature stable anatase TiO₂
44 photocatalyst. *J. Phys. Chem. C* **2007**, *111*, 1605-1611.
45
46 67. Fagan, R.; McCormack, D. E.; Hinder, S.; Pillai, S. C., Improved high temperature
47 stability of anatase TiO₂ photocatalysts by N, F, P co-doping. *Mater. Des.* **2016**, *96*, 44-53.
48
49 68. Hamadani, M.; Reisi-Vanani, A.; Razi, P.; Hoseinifard, S.; Jabbari, V.,
50 Photodeposition-assisted synthesis of novel nanoparticulate In, S-codoped TiO₂ powders with
51 high visible light-driven photocatalytic activity. *Appl. Surf. Sci.* **2013**, *285*, 121-129.
52
53 69. Zhang, W.; Pei, X.; Chen, J.; He, H., Effects of Al doping on properties of xAl-3%
54 In-TiO₂ photocatalyst prepared by a sol-gel method. *Mater. Sci. Semicond. Process.* **2015**,
55 *38*, 24-30.
56
57 70. Hinojosa-Reyes, M.; Arriaga, S.; Diaz-Torres, L.; Rodríguez-González, V., Gas-
58 Phase Photocatalytic Decomposition of Ethylbenzene over Perlite Granules Coated with
59 Indium Doped TiO₂. *Chem. Eng. J.* **2013**, *224*, 106-113.
60
71. Myilsamy, M.; Mahalakshmi, M.; Murugesan, V.; Subha, N., Enhanced
Photocatalytic Activity of Nitrogen and Indium Co-Doped Mesoporous TiO₂
Nanocomposites for the Degradation of 2, 4-Dinitrophenol under Visible Light. *Appl. Surf. Sci.* **2015**, *342*, 1-10.

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
72. Tahir, B.; Tahir, M.; Amin, N. S., Gold–Indium Modified TiO₂ Nanocatalysts for Photocatalytic CO₂ Reduction with H₂ as Reductant in a Monolith Photoreactor. *Appl. Sur. Sci.* **2015**, *338*, 1-14.
73. Choudhury, B.; Choudhury, A., Oxygen Vacancy and Dopant Concentration Dependent Magnetic Properties of Mn Doped TiO₂ Nanoparticle. *Curr. Appl. Phys.* **2013**, *13*, 1025-1031.
74. Sasikala, R.; Shirole, A.; Sudarsan, V.; Sudakar, C.; Naik, R.; Rao, R.; Bharadwaj, S., Enhanced Photocatalytic Activity of Indium and Nitrogen Co-Doped TiO₂–Pd Nanocomposites for Hydrogen Generation. *Appl. Catal., A* **2010**, *377*, 47-54.
75. Al mashary, F. S.; de Castro, S., et al., Effect of Growth Techniques on the Structural, Optical and Electrical Properties of Indium Doped TiO₂ Thin Films. *J. Alloys Compd.* **2018**, *766*, 194-203.
76. Al Saqri, N. A., et al., Investigation of Defects in Indium Doped TiO₂ Thin Films Using Electrical and Optical Techniques. *J. Alloys Compd.* **2017**, *698*, 883-891.
77. Yang, X.; Wang, Y.; Xu, L.; Yu, X.; Guo, Y. J. T., Silver and Indium Oxide Codoped TiO₂ Nanocomposites with Enhanced Photocatalytic Activity. *J. Phys. Chem. C* **2008**, *112*, 11481-11489.
78. Sasikala, R.; Sudarsan, V.; Sudakar, C.; Naik, R.; Panicker, L.; Bharadwaj, S., Modification of the Photocatalytic Properties of Self Doped TiO₂ Nanoparticles for Hydrogen Generation Using Sunlight Type Radiation. *Int. J. Hydrogen Energy* **2009**, *34*, 6105-6113.
79. Beula, R. J.; Devadason, S.; Vidhya, B., Incorporation of Indium in TiO₂-Based Photoanodes for Enhancing the Photovoltaic Conversion Efficiency of Dye-Sensitized Solar Cells. *Appl. Nanosci.* **2018**, 1-9.
80. Zhong, D.; Liu, W.; Tan, P.; Zhu, A.; Qiao, L.; Bian, Y.; Pan, J., Efficient hydrogen generation of indium doped BaTiO₃ decorated with CdSe quantum dots: Novel understanding of the effect of doping strategy. *Int. J. Hydrogen Energy* **2019**, *44*, 1627-1639
81. Kumaravel, V.; Imam, M. D.; Badreldin, A.; Chava, R. K.; Do, J. Y.; Kang, M.; Abdel-Wahab, A., Photocatalytic Hydrogen Production: Role of Sacrificial Reagents on the Activity of Oxide, Carbon, and Sulfide Catalysts. *Catalysts* **2019**, *9*, 276.
82. Ganguly, P.; Harb, M.; Cao, Z.; Cavallo, L.; Breen, A.; Dervin, S.; Dionysiou, D. D.; Pillai, S. C., 2D Nanomaterials for Photocatalytic Hydrogen Production. *ACS Energy Lett.* **2019**, *4*, 1687-1709.
83. Xu, L.; Guan, J.; Shi, W.; Liu, L., Heterostructured mesoporous In₂O₃/Ta₂O₅ composite photocatalysts for hydrogen evolution: Impacts of In₂O₃ content and calcination temperature. *J. Colloid Interface Sci.* **2012**, *377*, 160-168.
84. Cao, S.-W.; Liu, X.-F.; Yuan, Y.-P.; Zhang, Z.-Y.; Liao, Y.-S.; Fang, J.; Loo, S. C. J.; Sum, T. C.; Xue, C., Solar-to-fuels conversion over In₂O₃/g-C₃N₄ hybrid photocatalysts. *Appl. Catal., B* **2014**, *147*, 940-946.

Table of Contents Graphic

