

**UCC Library and UCC researchers have made this item openly available.  
Please [let us know](#) how this has helped you. Thanks!**

<b>Title</b>	Efficient one-pot synthesis of highly monodisperse carbon quantum dots
<b>Author(s)</b>	Linehan, Keith; Doyle, Hugh
<b>Publication date</b>	2013-11-01
<b>Original citation</b>	LINEHAN, K. & DOYLE, H. 2014. Efficient one-pot synthesis of highly monodisperse carbon quantum dots. RSC Advances, 4, pp. 18-21. doi: 10.1039/C3RA45083J
<b>Type of publication</b>	Article (peer-reviewed)
<b>Link to publisher's version</b>	<a href="http://dx.doi.org/10.1039/C3RA45083J">http://dx.doi.org/10.1039/C3RA45083J</a> Access to the full text of the published version may require a subscription.
<b>Rights</b>	© 2013, the Authors.
<b>Item downloaded from</b>	<a href="http://hdl.handle.net/10468/2512">http://hdl.handle.net/10468/2512</a>

Downloaded on 2019-09-23T19:42:41Z

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

COMMUNICATION

## Efficient one-pot synthesis of highly monodisperse carbon quantum dots

Keith Linehan and Hugh Doyle\*

Received (in XXX, XXX) Xth XXXXXXXXXX 20XX, Accepted Xth XXXXXXXXXX 20XX

DOI: 10.1039/b000000x

5 **Highly luminescent carbon quantum dots (CQDs) with narrow size distributions were synthesised in reverse micelles using a simple room temperature, solution-phase synthesis. The CQDs are stabilised by covalently bound alkyl ligand to minimise surface oxidation and exhibit blue emission with a**  
 10 **marked dependency on excitation wavelength.**

The recent emergence of carbon quantum dots (CQDs) as a versatile fluorescence nanomaterial has garnered widespread interest due to their attractive photophysical properties, high quantum yields, low toxicity and biocompatibility.<sup>1-3</sup> Compared  
 15 to conventional organic dyes and semiconductor nanocrystals, CQDs possess several advantages in terms of chemical inertness, easy functionalisation, high resistance to photobleaching, an absence of fluorescence intermittency and the potential for low cost production. As a result, much attention has been paid to their  
 20 potential application in areas from biological labelling and imaging to fluorescence nanosensors and optoelectronic devices.<sup>2, 4, 5</sup> A number of different synthetic strategies have been developed and reported for the preparation of CQDs, which may be divided into physical and chemical methods. Physical methods  
 25 include arc discharge,<sup>6</sup> laser ablation/passivation<sup>7, 8</sup> and plasma treatment.<sup>9</sup> Chemical methods include electrochemical synthesis,<sup>10-12</sup> combustion and acidic oxidation,<sup>13, 14</sup> hydrothermal and pyrolysis routes,<sup>15</sup> supported synthesis<sup>16-18</sup> and microwave/ultrasonic synthesis.<sup>19, 20</sup> However, some drawbacks  
 30 associated these methods include extensive post-synthetic purification, lack of control of CQD surface chemistry and sample polydispersity. To date, it has been proven difficult to produce ultra-small monodisperse CQDs with narrow size distributions, with many methods still requiring the need for  
 35 impractical size separation processes to obtain monodisperse CQDs.<sup>1</sup>


The use of solution based synthetic methods have been the most promising due to their ability to control the size, shape and surface chemistry of the CQDs. Rhee and co-workers reported the  
 40 solution-phase synthesis of CQDs using reverse micelles as nanoscale reactors.<sup>21</sup> The CQDs were formed *via* condensation polymerisation and subsequent carbonization of glucose within AOT reverse micelles at 160 °C. Control of the water-surfactant

45 Tyndall National Institute, University College Cork, Lee Malting, Cork, Ireland. Email: hugh.doyle@tyndall.ie; Tel: +353-21-2346300

† Electronic Supplementary Information (ESI) available: Synthetic method, characterisation and additional figures. See DOI: 10.1039/b000000x/


ratio within the micelle allowed the CQD diameter to be tuned from 1.8 to 4.1 nm, but with increasing polydispersity at larger diameters. They later reported a similar hydrothermal synthesis of nearly monodisperse ( $1.4 \pm 0.15$  nm) CQDs using octanol as the surfactant.<sup>22</sup> In both cases, subsequent *in situ* surface passivation  
 55 resulted in formation of hexadecylamide-capped CQDs. More recently, Gao *et al.* reported on the hydrothermal synthesis of CQDs by oxidation of C<sub>60</sub> by hydrogen peroxide under alkaline conditions within CTAB reverse micelles at 150 °C.<sup>23</sup>

In this communication, we report a simple one-pot, solution  
 60 phase synthesis of highly monodisperse, alkyl-capped, brightly luminescent CQDs formed by chemical reduction of carbon precursors in reverse micelles. This single-phase, room temperature method is inspired by our previously reported syntheses of size monodisperse Group IV nanocrystals.<sup>24, 25</sup> The  
 65 overall synthetic procedure is illustrated in Scheme 1. Under inert atmospheric conditions, carbon tetrachloride is dissolved within the hydrophilic interior of a tetraoctyl ammonium bromide (TOAB) reverse micelle; the carbon source material is then readily reduced using lithium aluminium hydride to form  
 70 hydrogen-terminated CQDs confined within the micelle interior. The surface of the as-synthesised CQDs is then modified using a platinum-catalysed process to form C-C bonds, which chemically passivates the CQD surface to minimise oxidation.

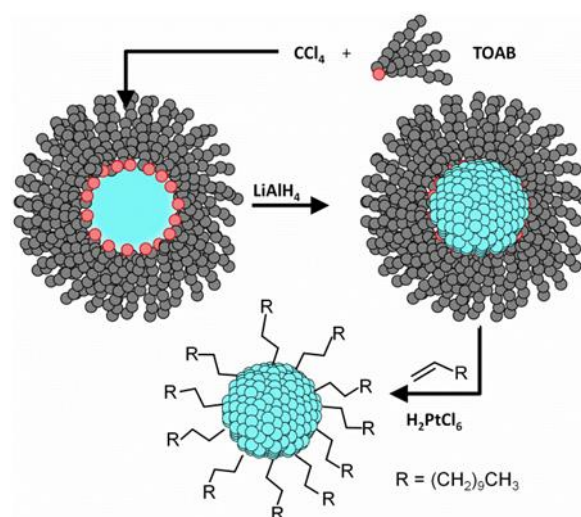

75 **Scheme 1** Schematic of the chemical synthesis and surface passivation of highly monodisperse dodecane-capped CQDs.


Fig. 1(a) shows a transmission electron microscope (TEM) image of the as-synthesized CQDs. The CQDs are highly size and shape monodisperse with no evidence of aggregation, see Fig 1 and S1 of ESI. Inset in Fig. 1(a) is a high resolution TEM image showing that the CQDs are highly crystalline with a lattice spacing of 2.1 Å, in excellent agreement with the (100) spacing reported for graphitic carbon. Fig. 1(b) shows a histogram of the CQD diameters, determined by analysis of TEM images of *ca.* 250 CQDs located at different locations on the grid. The mean diameter of the CQDs is  $1.5 \pm 0.3$  nm, based on fitting the histogram to a Gaussian model.

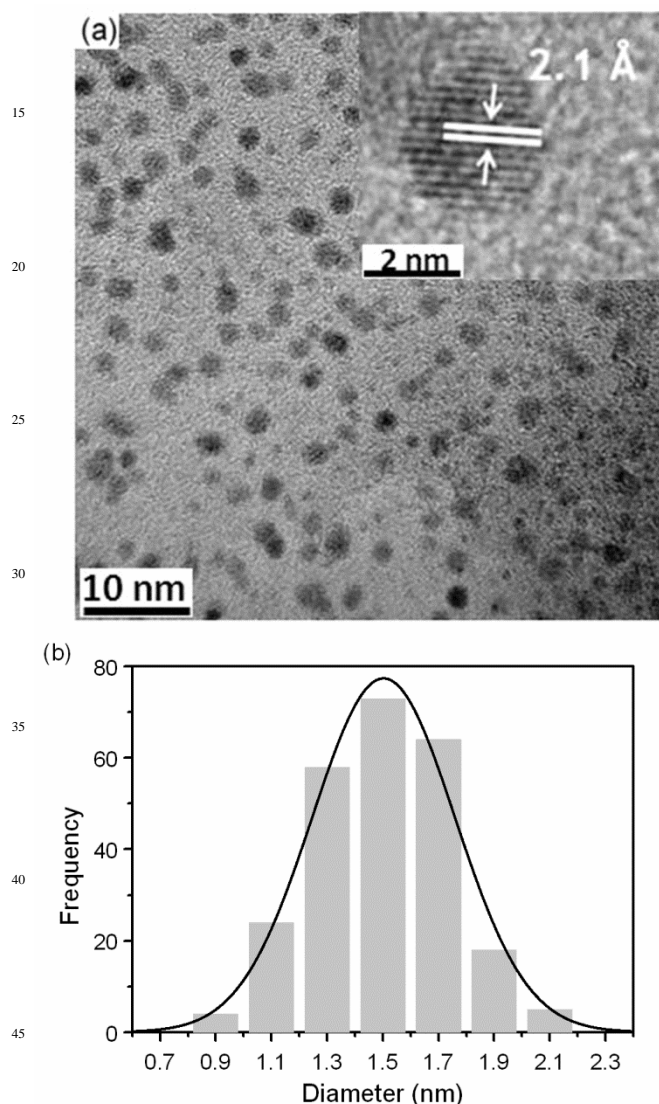

**Fig. 1** (a) Representative TEM image of the carbon quantum dots. Inset: high-resolution TEM image of an individual CQD. (b) Size histogram of the CQDs with curve fitted to the data using a Gaussian model.

The surface chemistry of the quantum dots was characterized by infrared spectroscopy; Fig. 2 shows the FTIR spectra of 1-dodecane and the as-synthesised CQDs. Both spectra exhibit strong C-H vibrational modes with symmetric  $\text{CH}_2$ , asymmetric  $\text{CH}_2$ , and the asymmetric C- $\text{CH}_3$  stretching vibrations at 2856, 2922, and 2960  $\text{cm}^{-1}$ , respectively. Further peaks at 1457 and

1378  $\text{cm}^{-1}$  are attributed to the C- $\text{CH}_2$  vibrational scissoring and C- $\text{CH}_3$  symmetric bending modes. The presence of the vinyl (R- $\text{CH}=\text{CH}_2$ ) group in the spectrum of 1-dodecane is confirmed by the peak at 1640  $\text{cm}^{-1}$ , corresponding to the C=C stretching mode. The peaks at 912 and 992  $\text{cm}^{-1}$  are due to the =CH out-of-plane deformation and  $\text{CH}_2$  out-of-plane wagging, while the small peak at 3081  $\text{cm}^{-1}$  is due to the =CH stretch. The presence of strong  $\text{CH}_x$  peaks in the spectrum of the CQDs, combined with the absence of peaks due to the vinyl group, is consistent with successful binding of the ligand to the quantum dot surface to form dodecane-capped CQDs. The presence of some small peaks between 1300-1000  $\text{cm}^{-1}$  is probably due to the presence of oxygenous functional groups such as C=O and C-O at the surface. However, the relatively low intensity of these peaks indicates that the CQDs are well passivated with minimal oxidation.

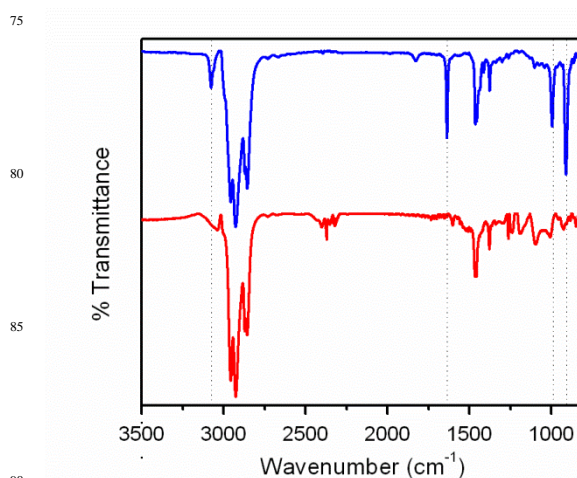


**Fig. 2** FTIR spectra of 1-dodecane (blue line) and the as-synthesised CQDs (red line). The dotted lines indicate the vinyl (R- $\text{CH}=\text{CH}_2$ ) stretching and bending vibrations.

The optical properties of the CQDs were investigated using UV-visible and photoluminescence spectroscopy. Fig. 3(a) shows the absorbance and photoluminescence spectra of the dodecane-capped CQDs in hexane. The absorption spectrum shows a peak centred at 264 nm with an onset of absorbance at 370 nm. This is in excellent agreement with reports of graphitic carbon CQDs strongly absorbing in the UV region. The photoluminescence spectra were obtained using excitation wavelengths ranging from 280 to 400 nm in 10 nm increments. The wavelength position of the PL maximum ranges from 325 nm for excitation at 280 nm to 450 nm for 400 nm excitation. This corresponds to an overall red shift in the PL peak position of 125 nm, as the excitation wavelength is increased by 120 nm; see Fig. 3(b). This clear dependency on excitation wavelength has also been widely observed for CQDs prepared using different methods of preparation and surface functionalities.<sup>1-3</sup>

To date, the origin of luminescence for CQDs remains controversial and complicated due to the wide variety of methods reported, together with the different ligand schemes, surface oxidation and broad particle size distributions which all contribute to the lack of consensus.<sup>1-3</sup> The wavelength dependency has been mainly attributed to optical selection of

differently sized nanocrystals (*i.e.* a quantum confinement effect), and/or emissive trap states on the surface but the exact mechanism still remains unresolved.<sup>1, 3</sup> Given the high degree of size monodispersity in the CQDs reported here, the most plausible explanation is that the blue luminescence originates from recombination of excitons at shallow surface trap states.<sup>7,24</sup> The high degree of surface passivation may also contribute to the narrow PL spectra (FWHM: 60 nm) observed. The CQDs also exhibit excellent long-term PL stability, decreasing by less than 4 % after continuous illumination for 12 hours; see Fig S2.

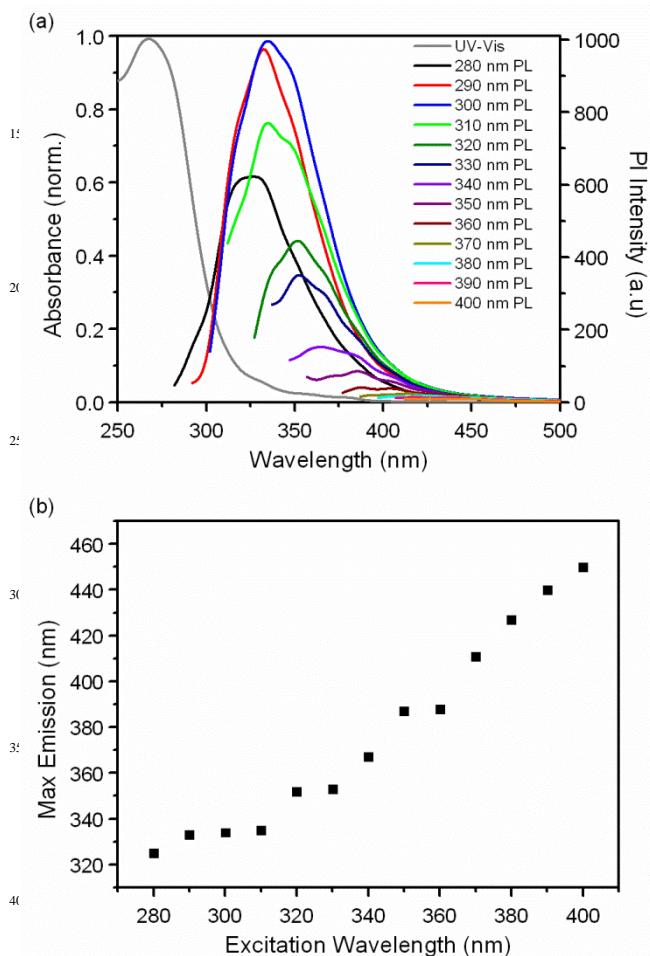

**Fig. 3** (a) UV-Vis absorbance and photoluminescence spectra of CQDs dispersed in hexane. (b) Wavelength position of the luminescence maximum as a function of excitation wavelength.

In conclusion, we have developed a simple room temperature route that readily provides alkyl-capped CQDs, with close control of internal structure and surface chemistry. The use of micelle templates thus allows for superior control over the CQD size, which is highlighted by the narrow size distributions achieved. The CQDs are readily dispersed in hexane, tetrahydrofuran, chloroform, toluene and other non-polar solvents, making them amenable to low cost, solution based device processing. The one-pot synthetic method reported here provides an attractive approach for efficient production of highly monodisperse CQDs with facile control of surface chemistry and passivation without

the need for any size separation steps.

This work was supported by the European Commission under the FP7 Projects SNAPSUN (grant agreement n° 246310) and CommonSense (grant agreement n° 2618309) and the Irish Higher Education Authority under the PRTL program (cycle 3 “Nanoscience” and Cycle 4 “INSPIRE”).

## Notes and references

- H. Li, Z. Kang, Y. Liu and S. T. Lee, *Journal of Materials Chemistry*, 2012, 22, 24230-24253.
- J. C. G. Esteves da Silva and H. M. R. Gonçalves, *TrAC, Trends in Analytical Chemistry*, 2011, 30, 1327-1336.
- S. N. Baker and G. A. Baker, *Angewandte Chemie, International Edition*, 2010, 49, 6726-6744.
- W. Kwon, S. Do, D. C. Won and S.-W. Rhee, *ACS Applied Materials & Interfaces*, 2013, 5, 822-827.
- F. Wang, Y.-H. Chen, C.-H. Liu and D.-H. Ma, *Chemical Communications*, 2011, 47, 3502-3504.
- X. Xu, R. Ray, Y. Gu, H. J. Ploehn, L. Gearheart, K. Raker and W. A. Scrivens, *Journal of the American Chemical Society*, 2004, 126, 12736-12737.
- Y. P. Sun, B. Zhou, Y. Lin, W. Wang, K. A. S. Fernando, P. Pathak, M. J. Meziani, B. A. Harruff, X. Wang, H. Wang, P. G. Luo, H. Yang, M. E. Kose, B. Chen, L. M. Veca and S. Y. Xie, *Journal of the American Chemical Society*, 2006, 128, 7756-7757.
- H. Goncalves and J. C. G. Esteves da Silva, *Journal of Fluorescence*, 2010, 20, 1023-1028.
- H. Jiang, F. Chen, M. G. Lagally and F. S. Denes, *Langmuir*, 2009, 26, 1991-1995.
- Q. L. Zhao, Z. L. Zhang, B. H. Huang, J. Peng, M. Zhang and D. W. Pang, *Chem. Commun.*, 2008, 5116-5118.
- L. Zheng, Y. Chi, Y. Dong, J. Lin and B. Wang, *Journal of the American Chemical Society*, 2009, 131, 4564-4565.
- J. Zhou, C. Booker, R. Li, X. Zhou, T. K. Sham, X. Sun and Z. Ding, *Journal of the American Chemical Society*, 2007, 129, 744-745.
- H. Liu, T. Ye and C. Mao, *Angewandte Chemie*, 2007, 119, 6593-6595.
- X. Wang, L. Cao, F. Lu, M. J. Meziani, H. Li, G. Qi, B. Zhou, B. A. Harruff, F. Kermarrec and Y. P. Sun, *Chem. Commun.*, 2009, 3774-3776.
- D. Pan, J. Zhang, Z. Li, C. Wu, X. Yan and M. Wu, *Chemical Communications*, 2010, 46, 3681-3683.
- R. Liu, D. Wu, S. Liu, K. Koynov, W. Knoll and Q. Li, *Angewandte Chemie*, 2009, 121, 4668-4671.
- J. Zong, Y. Zhu, X. Yang, J. Shen and C. Li, *Chem. Commun.*, 2011, 47, 764-766.
- A. B. Bourlinos, A. Stassinopoulos, D. Anglos, R. Zboril, V. Georgakilas and E. P. Giannelis, *Chemistry of Materials*, 2008, 20, 4539-4541.
- H. Zhu, X. Wang, Y. Li, Z. Wang, F. Yang and X. Yang, *Chem. Commun.*, 2009, 5118-5120.
- X. Wang, K. Qu, B. Xu, J. Ren and X. Qu, *Journal of Materials Chemistry*, 2011, 21, 2445-2450.
- W. Kwon and S. W. Rhee, *Chem. Commun.*, 2012, 48, 5256-5258.
- W. Kwon, S. Do and S.-W. Rhee, *RSC Advances*, 2012, 2, 11223-11226.
- M. X. Gao, C. F. Liu, Z. L. Wu, Q. L. Zeng, X. X. Yang, W. B. Wu, Y. F. Li and C. Z. Huang, *Chemical Communications*, 2013, 49, 8015-8017.
- K. Linehan and H. Doyle, *Small*, 2013, doi: 10.1002/smll.201301189.
- K. Linehan and H. Doyle, *MRS Online Proceedings Library*, 2013, 1546, mrrs13-1546-11506-1548.