

**UCC Library and UCC researchers have made this item openly available.  
Please [let us know](#) how this has helped you. Thanks!**

<b>Title</b>	Structural analysis, elemental profiling, and electrical characterization of HfO <sub>2</sub> thin films deposited on In <sub>0.53</sub> Ga <sub>0.47</sub> As surfaces by atomic layer deposition
<b>Author(s)</b>	Long, Rathnait D.; O'Connor, Éamon; Newcomb, Simon B.; Monaghan, Scott; Cherkaoui, Karim; Casey, P.; Hughes, Gregory; Thomas, Kevin K.; Chalvet, Francis N.; Povey, Ian M.; Pemble, Martyn E.; Hurley, Paul K.
<b>Publication date</b>	2009
<b>Original citation</b>	Long, R. D., O'Connor, É., Newcomb, S. B., Monaghan, S., Cherkaoui, K., Casey, P., Hughes, G., Thomas, K. K., Chalvet, F., Povey, I. M., Pemble, M. E. and Hurley, P. K. (2009) 'Structural analysis, elemental profiling, and electrical characterization of HfO <sub>2</sub> thin films deposited on In <sub>0.53</sub> Ga <sub>0.47</sub> As surfaces by atomic layer deposition', Journal of Applied Physics, 106(8), 084508 (7pp). doi: 10.1063/1.3243234
<b>Type of publication</b>	Article (peer-reviewed)
<b>Link to publisher's version</b>	<a href="http://aip.scitation.org/doi/10.1063/1.3243234">http://aip.scitation.org/doi/10.1063/1.3243234</a> <a href="http://dx.doi.org/10.1063/1.3243234">http://dx.doi.org/10.1063/1.3243234</a> Access to the full text of the published version may require a subscription.
<b>Rights</b>	© 2009, American Institute of Physics. This article may be downloaded for personal use only. Any other use requires prior permission of the author and AIP Publishing. The following article appeared in Long, R. D., O'Connor, É., Newcomb, S. B., Monaghan, S., Cherkaoui, K., Casey, P., Hughes, G., Thomas, K. K., Chalvet, F., Povey, I. M., Pemble, M. E. and Hurley, P. K. (2009) 'Structural analysis, elemental profiling, and electrical characterization of HfO <sub>2</sub> thin films deposited on In <sub>0.53</sub> Ga <sub>0.47</sub> As surfaces by atomic layer deposition', Journal of Applied Physics, 106(8), 084508 (7pp). doi: 10.1063/1.3243234 and may be found at <a href="http://aip.scitation.org/doi/10.1063/1.3243234">http://aip.scitation.org/doi/10.1063/1.3243234</a>
<b>Item downloaded from</b>	<a href="http://hdl.handle.net/10468/4750">http://hdl.handle.net/10468/4750</a>



Downloaded on 2024-09-24T11:41:07Z

**UCC**



## Structural analysis, elemental profiling, and electrical characterization of HfO<sub>2</sub> thin films deposited on In<sub>0.53</sub>Ga<sub>0.47</sub>As surfaces by atomic layer deposition

R. D. Long<sup>1</sup>, É. O'Connor, S. B. Newcomb, S. Monaghan, K. Cherkaoui, P. Casey, G. Hughes, K. K. Thomas, F. Chalvet, I. M. Povey, M. E. Pemble, and P. K. Hurley

Citation: *Journal of Applied Physics* **106**, 084508 (2009); doi: 10.1063/1.3243234

View online: <http://dx.doi.org/10.1063/1.3243234>

View Table of Contents: <http://aip.scitation.org/toc/jap/106/8>

Published by the *American Institute of Physics*

---

---

**AIP** | Journal of  
Applied Physics

Save your money for your research.  
It's now **FREE** to publish with us -  
no page, color or publication charges apply.

Publish your research in the  
*Journal of Applied Physics*  
to claim your place in applied  
physics history.

# Structural analysis, elemental profiling, and electrical characterization of HfO<sub>2</sub> thin films deposited on In<sub>0.53</sub>Ga<sub>0.47</sub>As surfaces by atomic layer deposition

R. D. Long,<sup>1,a)</sup> É. O'Connor,<sup>1</sup> S. B. Newcomb,<sup>2</sup> S. Monaghan,<sup>1</sup> K. Cherkaoui,<sup>1</sup> P. Casey,<sup>3</sup> G. Hughes,<sup>3</sup> K. K. Thomas,<sup>1</sup> F. Chalvet,<sup>1</sup> I. M. Povey,<sup>1</sup> M. E. Pemble,<sup>1</sup> and P. K. Hurley<sup>1</sup>

<sup>1</sup>Tyndall National Institute, University College Cork, Lee Maltings, Prospect Row, Cork, Ireland

<sup>2</sup>Glebe Scientific, Ltd., Newport, County Tipperary, Ireland

<sup>3</sup>School of Physics, Dublin City University, Glasnevin, Dublin 9, Ireland

(Received 13 August 2009; accepted 8 September 2009; published online 23 October 2009)

In this work results are presented on the structural analysis, chemical composition, and interface state densities of HfO<sub>2</sub> thin films deposited by atomic layer deposition (ALD) from Hf[N(CH<sub>3</sub>)<sub>2</sub>]<sub>4</sub> and H<sub>2</sub>O on In<sub>0.53</sub>Ga<sub>0.47</sub>As/InP substrates. The structural and chemical properties are investigated using high resolution cross-sectional transmission electron microscopy and electron energy loss spectroscopy. HfO<sub>2</sub> films (3–15 nm) deposited on In<sub>0.53</sub>Ga<sub>0.47</sub>As are studied following a range of surface treatments including *in situ* treatment of the In<sub>0.53</sub>Ga<sub>0.47</sub>As surface by H<sub>2</sub>S exposure at 50–350 °C immediately following the metal organic vapor phase epitaxy growth of the In<sub>0.53</sub>Ga<sub>0.47</sub>As layer, *ex situ* treatment with (NH<sub>4</sub>)<sub>2</sub>S, and deposition on the native oxides of In<sub>0.53</sub>Ga<sub>0.47</sub>As with no surface treatment. The structural analysis indicates that the In<sub>0.53</sub>Ga<sub>0.47</sub>As surface preparation prior to HfO<sub>2</sub> film deposition influences the thickness of the HfO<sub>2</sub> film and the interlayer oxide. The complete interfacial self-cleaning of the In<sub>0.53</sub>Ga<sub>0.47</sub>As native oxides is not observed using an ALD process based on the Hf[N(CH<sub>3</sub>)<sub>2</sub>]<sub>4</sub> precursor and H<sub>2</sub>O. Elemental profiling of the HfO<sub>2</sub>/In<sub>0.53</sub>Ga<sub>0.47</sub>As interface region by electron energy loss spectroscopy reveals an interface oxide layer of 1–2 nm in thickness, which consists primarily of Ga oxides. Using a conductance method approximation, peak interface state densities in the range from  $6 \times 10^{12}$  to  $2 \times 10^{13}$  cm<sup>-2</sup> eV<sup>-1</sup> are estimated depending on the surface preparation. © 2009 American Institute of Physics. [doi:10.1063/1.3243234]

## I. INTRODUCTION

To continue complementary metal oxide semiconductor (MOS) development beyond the 22 nm node, replacement channel materials in combination with high dielectric constant (*k*) gate layers are currently under investigation. High-mobility III-V materials such as In<sub>x</sub>Ga<sub>1-x</sub>As are realistic candidates for the channel replacement in *n*-type field effect transistors (MOSFETs),<sup>1–4</sup> and the growth of high In content metal semiconductor FETs on a silicon substrate has recently been demonstrated.<sup>5</sup> However, the implementation of these new channel materials faces many challenges, one of which is the lack of stable high quality gate insulators, which yield sufficiently low density of electrically active defects at the interface between the III-V channel and the high-*k* gate layer. Although significant effort has been dedicated to investigate HfO<sub>2</sub> thin films formed by atomic layer deposition on In<sub>x</sub>Ga<sub>1-x</sub>As (Refs. 6–8) and resultant In<sub>x</sub>Ga<sub>1-x</sub>As MOSFET structures,<sup>9</sup> an improvement in the In<sub>x</sub>Ga<sub>1-x</sub>As MOSFET performance is expected from an increased understanding of the structural and chemical properties of the interface region between the In<sub>x</sub>Ga<sub>1-x</sub>As substrate and the high-*k* gate layer and analysis of the resulting electrical performance of the devices.

In a recent publication,<sup>10</sup> an *in situ* treatment of *n*-type

In<sub>0.53</sub>Ga<sub>0.47</sub>As using H<sub>2</sub>S at the end of metal organic vapor phase epitaxy (MOVPE) growth was demonstrated to result in comparable electrical properties to those of *ex situ* aqueous sulfur treatments using (NH<sub>4</sub>)<sub>2</sub>S for Pd/HfO<sub>2</sub>/In<sub>0.53</sub>Ga<sub>0.47</sub>As/InP structures. The objective of this paper is to investigate the effect of the In<sub>0.53</sub>Ga<sub>0.47</sub>As surface preparation on the structural properties of the ALD deposited HfO<sub>2</sub> thin films and to investigate the composition of the oxide interface layer (IL) between the HfO<sub>2</sub> and the In<sub>0.53</sub>Ga<sub>0.47</sub>As using high angle angular dark field scanning microscopy and electron energy loss spectroscopy (EELS). The defect concentrations at the HfO<sub>2</sub>/In<sub>0.53</sub>Ga<sub>0.47</sub>As interface are also estimated using an approximation of the conductance method.

## II. EXPERIMENTAL DETAILS

The *n*-type lattice matched 2 μm In<sub>0.53</sub>Ga<sub>0.47</sub>As layers were grown on 350 μm InP(100) substrates by MOVPE at 670 °C. At the end of the MOVPE growth, the In<sub>0.53</sub>Ga<sub>0.47</sub>As surface was subjected to H<sub>2</sub>S exposure [flow rate of 0.1 SCCM (SCCM denotes standard cubic centimeter per minute at STP) in H<sub>2</sub>] for 90 minutes at temperatures of 50, 200, or 350 °C. The use of H<sub>2</sub>S is particularly suited to *in situ* passivation of In<sub>0.53</sub>Ga<sub>0.47</sub>As as it is used as the *n*-type dopant source in the MOVPE process. As a comparison, an *ex situ* aqueous sulfur treatment of the MOVPE In<sub>0.53</sub>Ga<sub>0.47</sub>As sur-

<sup>a)</sup>Electronic mail: rathnait.long@tyndall.ie.

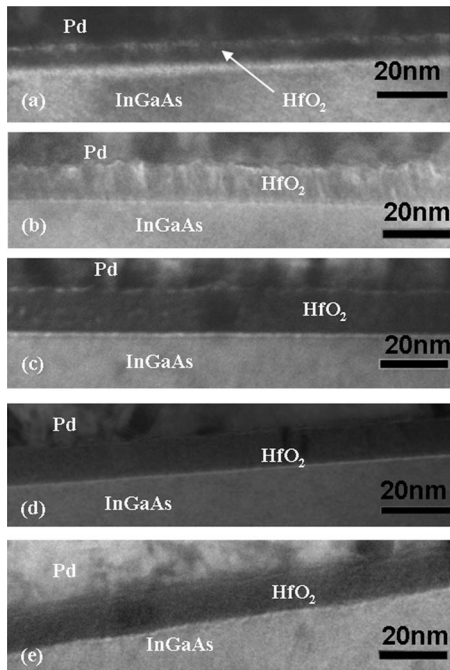


FIG. 1. High resolution cross-sectional TEM of the Pd/9 nm  $\text{HfO}_2/\text{In}_{0.53}\text{Ga}_{0.47}\text{As}/\text{InP}$  structures with various  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  starting surface conditions: (a) no treatment, (b)  $\text{H}_2\text{S}$  at 350 °C, (c)  $\text{H}_2\text{S}$  at 200 °C, (d)  $\text{H}_2\text{S}$  at 50 °C, and (e)  $(\text{NH}_4)_2\text{S}$ .

face was also carried out using 20%  $(\text{NH}_4)_2\text{S}$  in de-ionized (DI) water at  $\sim 60$  °C for 20 min. The  $\text{HfO}_2$  film was deposited by ALD using  $\text{Hf}[\text{N}(\text{CH}_3)_2]_4$  and  $\text{H}_2\text{O}$  at 250 °C on  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}/\text{InP}$  samples with typical size of  $20 \times 30 \text{ mm}^2$ . The  $\text{Hf}[\text{N}(\text{CH}_3)_2]_4$  is the first pulse in the ALD sequence. In the interim between surface passivation and the ALD process, the samples were exposed to air for  $\sim 2$  min. Metal gate formation (100 nm Pd) was achieved by electron beam evaporation and a lift-off process. The samples analyzed in this work did not receive either post oxide deposition annealing or post gate metallization annealing. No back contacts were formed. More details on the sample processing can be found in Ref. 10. Conventional transmission electron microscopy (TEM) samples were prepared using focused ion beam thinning procedures<sup>11</sup> in an FEI 200 Workstation and examined at 200 kV in a JEOL2000FX. Capacitance and conductance measurements were performed on-wafer at 25 °C in a humidity-controlled ambient using a Cascade Microtech probe station and an Agilent B1500A semiconductor device analyzer.

### III. RESULTS AND DISCUSSION

Figure 1 shows the high resolution cross-sectional TEM micrographs of the Pd/ $\text{HfO}_2/\text{In}_{0.53}\text{Ga}_{0.47}\text{As}/\text{InP}$  structures for the various treatment approaches examined: (a) no treatment (i.e. native oxide), (b)  $\text{H}_2\text{S}$  at 350 °C, (c)  $\text{H}_2\text{S}$  at 200 °C, (d)  $\text{H}_2\text{S}$  at 50 °C, and (e)  $(\text{NH}_4)_2\text{S}$ . The TEM micrographs for the untreated sample (a) and the  $\text{H}_2\text{S}$  at 50 °C treatment (d), already published by O'Connor *et al.*,<sup>10</sup> are included for completeness. There are a number of comparisons to be made from the TEM micrographs relating to the thickness of the  $\text{HfO}_2$  film, the interface oxide layer present

TABLE I.  $\text{HfO}_2$  and  $\text{HfO}_2/\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  IL thickness measurements of samples with varying  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  surface treatments, as obtained from high resolution cross-sectional TEM. The substrate surface conditions appear to influence the subsequent dielectric growth.

Condition	$\text{HfO}_2$ nominal (nm)	$\text{HfO}_2$ measured by HR-TEM (nm)	IL measured by HR-TEM (nm)
Untreated	9	5.2	1.90
$\text{H}_2\text{S}$ , 50 °C, 90 min	9	9.4	0.83
$\text{H}_2\text{S}$ , 200 °C, 90 min	9	13.5	0.90
$\text{H}_2\text{S}$ , 350 °C, 90 min	9	10.8	0.90
$(\text{NH}_4)_2\text{S}$	9	11.0	1.30

between the  $\text{HfO}_2$  film and the  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  substrate, and the surface roughness of the  $\text{HfO}_2/\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  interface.

All samples have an IL oxide present between the  $\text{HfO}_2$  film and the  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  substrate, which is expected since the ALD process involves the exposure of the  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  substrate surface to  $\text{H}_2\text{O}$  at 250 °C. However, there are differences in the IL thicknesses across the samples. These thicknesses, as measured by conventional TEM, are listed in Table I. The sample exposed to *in situ*  $\text{H}_2\text{S}$  treatment at 50 °C has the thinnest IL. The sample treated with the *ex situ* aqueous  $(\text{NH}_4)_2\text{S}$  solution has the thickest IL (1.3 nm) of all the  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  samples which experience a surface treatment prior to  $\text{HfO}_2$  ALD growth. The untreated  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  sample has an IL oxide thickness of 1.9 nm and is comparable to the native oxide thickness of 2 nm found on  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  by Kobayashi *et al.*<sup>12</sup> A number of recent publications have demonstrated that ALD deposition of  $\text{Al}_2\text{O}_3$  [using  $\text{Al}(\text{CH}_3)_3$ ] and  $\text{HfO}_2$  {using  $\text{Hf}[\text{N}(\text{CH}_3)\times(\text{C}_2\text{H}_5)]_4$ } on GaAs and  $\text{In}_x\text{Ga}_{1-x}\text{As}$  substrates can reduce the thickness of interfacial Ga and As oxides during the ALD growth process.<sup>6,7,12,13</sup> This is referred to as an interfacial “self-cleaning process” and is most likely precursor dependent. The thickness of the IL oxide for the untreated sample (1.9 nm) indicates that limited or no interfacial self-cleaning process is occurring using the  $\text{Hf}[\text{N}(\text{CH}_3)_2]_4$  and  $\text{H}_2\text{O}$  water process. This result is in agreement with the work of Shahrjerdi *et al.*<sup>14</sup> where no self-cleaning was observed using the same precursor [tetrakis(dimethyl-amino) hafnium] on GaAs.

The thicknesses of the ALD deposited  $\text{HfO}_2$  films as measured by TEM are also given in Table I. The untreated sample has a dielectric thickness of 5.2 nm, while all of the treated samples [*in situ*  $\text{H}_2\text{S}$  and  $(\text{NH}_4)_2\text{S}$ ] have film thicknesses closer to the nominal value of 9 nm. This suggests that the pre-ALD surface treatment has an impact on the nucleation of the  $\text{HfO}_2$  growth and therefore the thickness of the subsequent  $\text{HfO}_2$  film. A similar observation has been reported on GaAs.<sup>15</sup> The sample with the deposited thickness closest to the nominal 9 nm was the sample subjected to the *in situ*  $\text{H}_2\text{S}$  treatment at 50 °C. The TEM micrographs in Fig. 1 also present a variation in contrast within the  $\text{HfO}_2$  layer, indicating density variations through the  $\text{HfO}_2$  film as well as variability in the roughness of the  $\text{HfO}_2/\text{Pd}$  interface. These effects are most pronounced in the 350 °C *in situ*  $\text{H}_2\text{S}$  treated sample and the sample with no surface preparation



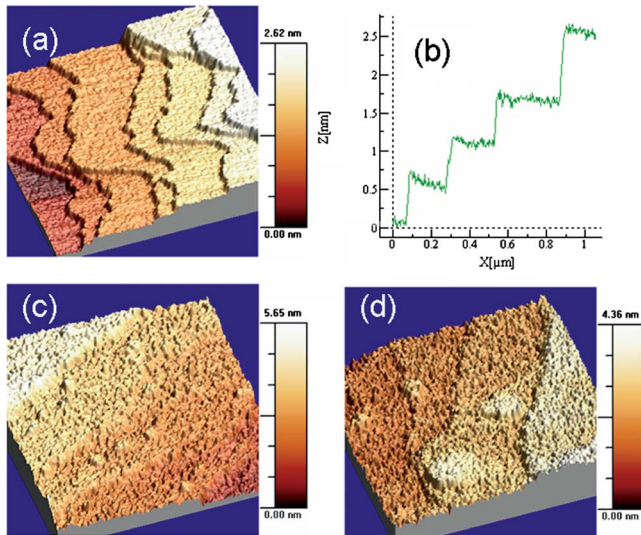


FIG. 2. (Color online) AFM images and atomic step height of  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  surfaces [(a) and (b)] before, (c) after  $(\text{NH}_4)_2\text{S}$  solution and (d) after  $(\text{NH}_4)_2\text{S}$  solution and annealing. The sample was in the  $(\text{NH}_4)_2\text{S}$  for 20 min at 60 °C. The  $(\text{NH}_4)_2\text{S}$  is 20% in DI water. The annealing was under vacuum at 200 °C for 5 min.

and are least pronounced for the sample treated with *in situ*  $\text{H}_2\text{S}$  at 50 °C.

From the TEM micrographs, it is evident that the  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  surface subjected to the aqueous  $(\text{NH}_4)_2\text{S}$  solution [Fig. 1(e)] has an increased semiconductor surface roughness when compared to the samples treated *in situ*. This roughening of the  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  has also been reported in a recent publication<sup>16</sup> and is consistent with an etching of the  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  by the  $(\text{NH}_4)_2\text{S}$  solution. This has the potential to increase surface scattering in MOSFET structures, reducing electron mobility in the inversion layer. This roughening effect was examined further using atomic force microscopy to examine the  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  surface morphology and root mean square (RMS) surface roughness before and after 20 min in 20%  $(\text{NH}_4)_2\text{S}$  at  $\sim 60$  °C followed by a de-ionized water rinse and  $\text{N}_2$  dry. Samples were also analyzed following the  $(\text{NH}_4)_2\text{S}$  treatment and a vacuum anneal at 200 °C for approximately 5 min. The AFM results for a  $1 \times 1 \mu\text{m}^2$  scan area are shown in Fig. 2, with the tabulated RMS surface roughness values, as measured from individual terraces, in Table II, obtained using a Veeco Dimension 3100. Table II also lists the average height of the surface roughness (taking the lowest point as the zero level and measuring the height of the other features with respect to it) and the maximum fea-

TABLE II. RMS roughness data measured from individual terraces for the  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  surface as measured by AFM, with no treatment (native oxide), following  $(\text{NH}_4)_2\text{S}$  solution and following  $(\text{NH}_4)_2\text{S}$  solution and annealing under vacuum (200 °C for 5 min). The  $(\text{NH}_4)_2\text{S}$  treatment significantly roughens the  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  surface.

Condition	Ave. height (nm)	Max. height (nm)	RMS roughness (nm)
InGaAs (native oxide)	0.3	0.5	0.1
$(\text{NH}_4)_2\text{S}$ treatment	0.8	1.7	0.2
$(\text{NH}_4)_2\text{S}$ and anneal	0.9	1.6	0.2

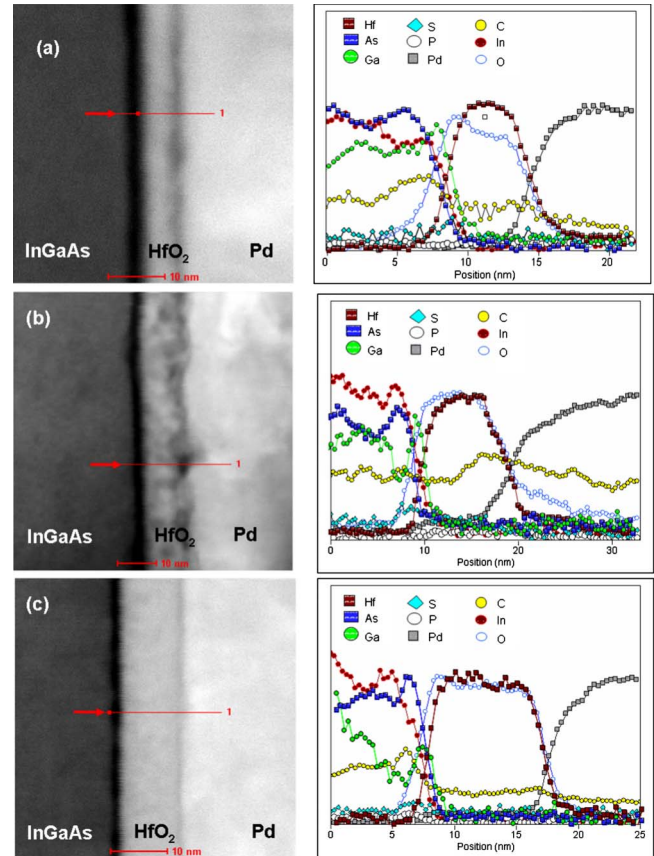


FIG. 3. (Color online) HAADF-STEM/EELS of Pd/ $\text{HfO}_2$ / $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  structures: (a) untreated, (b)  $\text{H}_2\text{S}$  at 350 °C, and (c)  $\text{H}_2\text{S}$  at 50 °C. EELS analysis reveals an interface oxide layer of 1–2 nm in thickness, which consists primarily of Ga oxide.

ture height observed. The  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  surface prior to the  $(\text{NH}_4)_2\text{S}$  exhibits atomic steps ( $\sim 0.6$  nm) and atomically smooth terraces (200–400 nm wide), with an RMS roughness of 0.1 nm. The 0.6 nm single atomic steps are consistent with the 0.5869 nm lattice constant of  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$ .<sup>17</sup> This type of surface morphology has been reported for AlGaAs/GaAs/AlGaAs quantum well structures grown by MOVPE.<sup>18</sup> Following the  $(\text{NH}_4)_2\text{S}$  treatment the terraces are still evident, but a clear roughening of the  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  surface has resulted, with a doubling of the RMS roughness to 0.2 nm.

High angle annular dark field scanning TEM (HAADF-STEM) and EELS results for the untreated sample and the samples subjected to the *in situ*  $\text{H}_2\text{S}$  at 350 and 50 °C are shown in Figs. 3(a)–3(c), respectively. In the HAADF-STEM micrographs, the IL oxide can be seen as a darker layer (lower average atomic number) between the  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  and the  $\text{HfO}_2$ . The variations in density of the  $\text{HfO}_2$  layer across the samples as observed by conventional TEM are also seen in the corresponding HAADF-STEM micrographs. The EELS data for each sample are representative of a single line scan. However, the results are repeatable, and the scans shown in Fig. 3 are representative of each sample as a whole. It should be noted that profile heights do not represent stoichiometric concentrations but instead only show relative change in each element's signal along the profiled line.

The HAADF-STEM micrographs of the untreated sample [Fig. 3(a)] and the sample treated with  $\text{H}_2\text{S}$  at

TABLE III. HfO<sub>2</sub>/In<sub>0.53</sub>Ga<sub>0.47</sub>As IL thicknesses measured by high resolution cross-sectional TEM and by HAADF-STEM. HfO<sub>2</sub> thickness measured by HAADF-STEM concurs with conventional TEM thickness measurements; however IL thickness measurements differ in magnitude between the two techniques.

Condition	HfO <sub>2</sub> Nominal (nm)	IL measured HR-TEM (nm)	IL measured HAADF-STEM (nm)	HfO <sub>2</sub> measured HR-TEM (nm)	HfO <sub>2</sub> measured HAADF-STEM (nm)
Untreated	9	1.90	2.2	5.2	6.0
H <sub>2</sub> S, 50 °C, 90 min	9	0.83	1.7	9.4	9.4
H <sub>2</sub> S, 350 °C, 90 min	9	0.90	2.1	10.8	10.5
H <sub>2</sub> S, 200 °C, 90 min	9	0.90	...	13.5	...
(NH <sub>4</sub> ) <sub>2</sub> S	9	1.30	2.0	11.0	10.7

350 °C [Fig. 3(b)] show an interlayer between the HfO<sub>2</sub> and the Pd. This could either be organic residue from the metal lift-off process or voids due to the roughness of the HfO<sub>2</sub> surface. This effect could also be enhanced as a result of Pd delamination during cross-sectional analysis. From the corresponding EELS line scan, there is no significant increase in the carbon signal at this interface, suggesting that it is more likely to be voids. The voids are not evident for the sample treated *in situ* with H<sub>2</sub>S at 50 °C [Fig. 3(c)], and this sample also exhibits the lowest leakage current density.<sup>10</sup>

From the EELS line scans in Figs. 3(a)–3(c), the region corresponding to the III–V/high-*k* interfacial oxide layer for all samples shows the oxygen signal increasing before the Hf signal and overlapping with the substrate elements' signals. This indicates the presence of an interface oxide in all cases. The composition of each interlayer appears similar, with some In and As oxides, but mostly comprising of a Ga oxide, seen by the peak of the Ga signal at each interface. The oxidation state of the Ga has not been determined. It has been reported for GaAs that oxygen will bond preferentially to Ga atoms that are below As dimers, with subsequent oxidation of nearby Ga dimers, and the formation of As clusters.<sup>19</sup> In each of the EELS profiles, we can see a slight increase in the As and In signals in the In<sub>0.53</sub>Ga<sub>0.47</sub>As substrate near the HfO<sub>2</sub>/In<sub>0.53</sub>Ga<sub>0.47</sub>As interface, with an increase in the Ga signal overlapping the oxygen at the interface. This is consistent with the proposed model for GaAs oxidation.

The Ga signal increases with the rising oxygen signal at the top of the substrate (the In and As signals do not) and then decreases as the Hf signal increases. At each interface there appears to be a peak of the As signal, which may not be real, as the Ga signal becomes less prominent, allowing easier detection of the As signal. With regard to the presence of sulfur, the EELS agrees with the x-ray photoelectron spectroscopy results previously published,<sup>10</sup> with no sulfur at the HfO<sub>2</sub>/In<sub>0.53</sub>Ga<sub>0.47</sub>As interface for the untreated sample, as expected, and an increase in the sulfur concentration at the interface for the sample exposed to H<sub>2</sub>S at 350 °C. However, for the sample treated *in situ* at 50 °C, the EELS cannot conclusively determine whether sulfur is present at the interface or not. A clear carbon signal was observed throughout the EELS line scan for all samples. This carbon is most likely from surface contamination during sample preparation, shipping, and handling.

In all cases, the HfO<sub>2</sub> thicknesses measured by HAADF-STEM concur with the conventional TEM thickness measurements, shown in Table III. However, the IL oxide thicknesses from conventional TEM and HAADF-STEM images are not in full agreement. Even though the trends in the thickness of the IL agree with both methods, the HAADF-STEM images yield consistently thicker IL oxides (Table III). One possible explanation for this discrepancy is that the HAADF-STEM image is based on atomic number contrast and the IL is the thickness of the region with average low atomic number. The conventional TEM, by comparison, provides structural information, and the IL oxide is the thickness of the amorphous region between the InGaAs substrate and the HfO<sub>2</sub> layer. Consequently, the two measurements are not directly comparable. Further research is required to fully understand this discrepancy.

To investigate the effect of HfO<sub>2</sub> film thickness on the IL properties, HfO<sub>2</sub> films with nominal thicknesses from 3 to 15 nm were examined by cross-sectional TEM. All samples were subject to H<sub>2</sub>S exposure at 50 °C prior to the HfO<sub>2</sub> ALD growth. The resulting TEM micrographs are shown in Fig. 4 for nominal thicknesses of 3, 9, and 15 nm in (a), (b), and (c), respectively. Thickness measurements obtained using conventional TEM are shown in Table IV. The variation

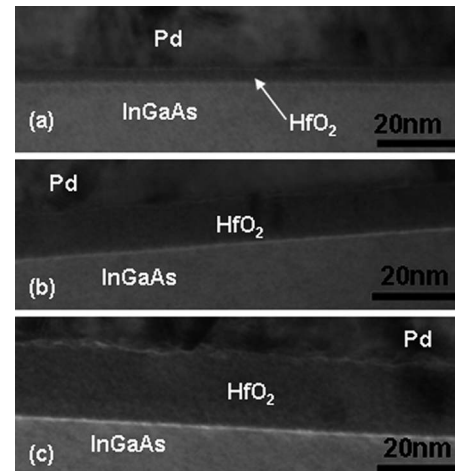


FIG. 4. High resolution cross-sectional TEM of samples treated *in situ* H<sub>2</sub>S at 50 °C with varying nominal HfO<sub>2</sub> thicknesses of (a) 3, (b) 9, and (c) 15 nm. The interfacial layer thickness and the In<sub>0.53</sub>Ga<sub>0.47</sub>As surface roughness do not change significantly with varying HfO<sub>2</sub> thicknesses.

TABLE IV. HfO<sub>2</sub> and HfO<sub>2</sub>/In<sub>0.53</sub>Ga<sub>0.47</sub>As IL thickness measurements of samples with varying dielectric nominal thicknesses obtained from conventional high resolution cross-sectional TEM. All samples had the same surface treatment: H<sub>2</sub>S at 50 °C for 90 min. The thickness of the IL is constant within experimental limitations at ~0.8 nm for the 3, 9, and 15 nm HfO<sub>2</sub> films, indicating that the IL oxide of ~0.8 nm is formed prior to or at the initial stages of the HfO<sub>2</sub> film growth.

Condition	Nominal (nm)	HfO <sub>2</sub> measured TEM (nm)	IL measured TEM (nm)
H <sub>2</sub> S, 50 °C, 90 min	3	3.0	0.80
H <sub>2</sub> S, 50 °C, 90 min	9	9.4	0.83
H <sub>2</sub> S, 50 °C, 90 min	15	16.8	0.85

in the deposited HfO<sub>2</sub> film thicknesses across the three samples as measured by TEM is within ~10% of the nominal ALD target thickness. The thickness of the IL is constant within experimental limitations for the 3, 9, and 15 nm HfO<sub>2</sub> films, indicating that this IL is formed at the initial stages of the HfO<sub>2</sub> film growth or air exposure prior to ALD, and is not being altered during the ALD process. Note the presence of crystalline regions in the 9 and 15 nm HfO<sub>2</sub>, which are present even though the maximum temperature experienced by the HfO<sub>2</sub> during the ALD growth process is 250 °C.

Figure 5 shows the capacitance-voltage (CV) characteristics of the 9 nm sample treated *in situ* with H<sub>2</sub>S at 50 °C from 1 kHz to 1 MHz. The CV characteristic for positive gate bias (1–2 V) is representative of accumulation of electrons at the HfO<sub>2</sub>/In<sub>0.53</sub>Ga<sub>0.47</sub>As interface based on the insensitivity of the accumulation capacitance to frequency (1 kHz–1 MHz) and temperature (–50 to 75 °C).<sup>20</sup> The region from 0 to –1.5 V, however, is not representative of inversion at the HfO<sub>2</sub>/In<sub>0.53</sub>Ga<sub>0.47</sub>As interface. The measured capacitance passes through a peak value and subsequently decreases with increasing negative bias (see the open symbol 10 kHz CV sweep in Fig. 5). This is characteristic of an interface defect response where the interface state distribution exhibits a peak at a specific energy in the band gap at the dielectric/semiconductor interface.<sup>21–23</sup> For the case of inversion at the HfO<sub>2</sub>/In<sub>0.53</sub>Ga<sub>0.47</sub>As interface with an associated minority carrier response, the capacitance should acquire a constant value in inversion, where the magnitude of the ca-

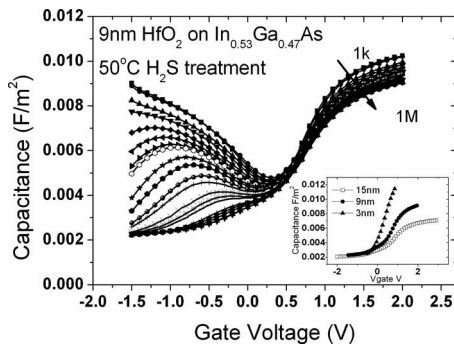


FIG. 5. CV curves from 1 kHz to 1 MHz of the sample with 9.4 nm of HfO<sub>2</sub> treated *in situ* with H<sub>2</sub>S at 50 °C. The curves correspond to the extracted equivalent parallel conductance measurements shown in Fig. 6. Inset: to illustrate the flatband voltage shift as a function of dielectric thickness, the 1 MHz CV curves are shown for the devices with 3.0, 9.4, and 16.8 nm of HfO<sub>2</sub> (all have similar substrate surface treatment).

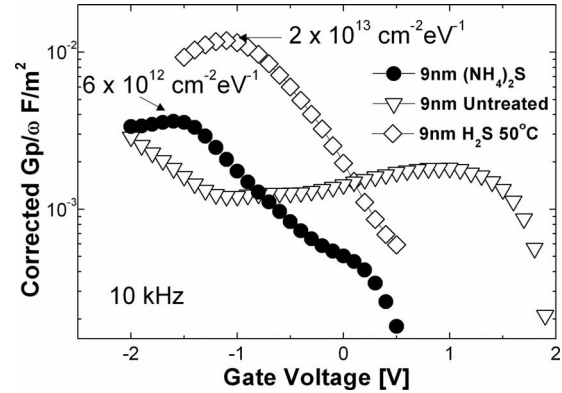


FIG. 6.  $G_p/\omega$  vs  $V$  curves at 10 kHz for the samples treated *in situ* with H<sub>2</sub>S at 50 °C (9.4 nm HfO<sub>2</sub>), the (NH<sub>4</sub>)<sub>2</sub>S treated sample (10.8 nm HfO<sub>2</sub>), and the sample with an untreated In<sub>0.53</sub>Ga<sub>0.47</sub>As surface (5.4 nm of HfO<sub>2</sub>). The approximate equivalent parallel conductance has been corrected for series resistance effects and also for the lossy dielectric effects. The peak value in the conductance is not observed within the measured voltage range for the sample with the untreated InGaAs surface and the samples treated with H<sub>2</sub>S at 200 °C and 350 °C.

pacitance increases with decreasing ac signal frequency. The inset of Fig. 5 shows the 1 MHz curve for each of the three thicknesses of HfO<sub>2</sub>, illustrating a positive  $V_{fb}$  shift with increasing dielectric thickness.

The corresponding conductance ( $G$ ) of the Pd/HfO<sub>2</sub>/In<sub>0.53</sub>Ga<sub>0.47</sub>As/InP MOS structure was measured simultaneously with the capacitance as a function of voltage at the selected ac frequencies. The equivalent parallel conductance ( $G_p/\omega$ ) was extracted from the measured data and then corrected for series resistance<sup>24</sup> and for a “lossy dielectric” as demonstrated by Kwa *et al.*<sup>25</sup> The resulting corrected equivalent parallel conductance is shown in Fig. 6 at 10 kHz for the samples with a nominal HfO<sub>2</sub> thickness of 9 nm. The capacitor with a 50 °C *in situ* H<sub>2</sub>S treated In<sub>0.53</sub>Ga<sub>0.47</sub>As surface exhibits a peak equivalent parallel conductance loss located between –1 and –1.5 V, corresponding to an approximate interface state densities of  $\sim 2 \times 10^{13} \text{ cm}^{-2} \text{ eV}^{-1}$  taking  $D_{it} = (2.5 |G_p/\omega|_{\text{peak}}/q)$ . The HfO<sub>2</sub> film on the In<sub>0.53</sub>Ga<sub>0.47</sub>As surface treated with (NH<sub>4</sub>)<sub>2</sub>S exhibits a similar  $G_p/\omega$  versus bias dependence profile to the *in situ* H<sub>2</sub>S at 50 °C treated sample. However, the equivalent parallel conductance loss is lower on the aqueously treated sample by a factor of ~0.32, yielding an approximate peak interface state density of  $\sim 6 \times 10^{12} \text{ cm}^{-2} \text{ eV}^{-1}$ . It should be noted here that due to the ability of the defects to communicate with both the conduction and the valence bands (the In<sub>0.53</sub>Ga<sub>0.47</sub>As energy gap is ~0.75 eV), the  $D_{it}$  values may be an overestimation of the actual  $D_{it}$  level, as discussed by Martens *et al.*<sup>26</sup> The profile for the untreated sample, shown in Fig. 6, and the samples treated with H<sub>2</sub>S at 200 and 350 °C (not shown) do not exhibit a peak equivalent parallel conductance loss within the bias range studied. However, these samples display a higher equivalent parallel conductance loss over the bias range 0–1 V, when compared to the *in situ* H<sub>2</sub>S and the (NH<sub>4</sub>)<sub>2</sub>S treated In<sub>0.53</sub>Ga<sub>0.47</sub>As surfaces, and this is reflected in a higher CV stretch-out for these samples in this bias range.<sup>10</sup> Table V compares the resulting interface state den-



TABLE V. Interface state density values at peak  $G_p/\omega$  at 10 kHz (where possible) and at flatband voltage. The  $(\text{NH}_4)_2\text{S}$  and the  $\text{H}_2\text{S}$  at 50 °C treatments are effective at reducing the interface state density in the upper gap (from  $E_i$  to  $E_c$ ). The corresponding energy positions in the  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  energy gap for the peak  $D_{it}$  and at flatband are estimated from *CV* measurements at 77 K and 1 MHz, where  $D_{it}$  effects are minimized (Ref. 28).

Condition	Peak $D_{it}(\text{cm}^{-2} \text{eV}^{-1}) \sim E_v + 0.4 \text{ eV}$	$D_{it}$ at $V_{fb}(\text{cm}^{-2} \text{eV}^{-1}) \sim E_v + 0.7 \text{ eV}$
Untreated	Peak $D_{it}$ outside bias range	$\sim 2.8 \times 10^{12}$
9 nm $\text{H}_2\text{S}$ at 350 °C	Peak $D_{it}$ outside bias range	$\sim 2.6 \times 10^{12}$
9 nm $\text{H}_2\text{S}$ at 200 °C	Peak $D_{it}$ outside bias range	$\sim 2.3 \times 10^{12}$
9 nm $\text{H}_2\text{S}$ at 50 °C	$\sim 2 \times 10^{13}$	$\sim 1.1 \times 10^{12}$
9 nm $(\text{NH}_4)_2\text{S}$	$\sim 6 \times 10^{12}$	$\sim 3.75 \times 10^{11}$

sities for the 10 kHz peak value of the conductance and also at the flatband voltage.

From these values it is evident that the *in situ*  $\text{H}_2\text{S}$  and the  $(\text{NH}_4)_2\text{S}$  surface preparations both reduce interface state densities in the upper region (from  $E_i$  to  $E_c$ ) of the  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  energy gap at the  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}/\text{HfO}_2$  interface. If we assume that sulfur is the main passivating element for the *in situ*  $\text{H}_2\text{S}$  and  $(\text{NH}_4)_2\text{S}$  processes, then the *in situ*  $\text{H}_2\text{S}$  process is considerably more effective when considering the differing amount of sulfur available between the  $(\text{NH}_4)_2\text{S}$  *ex situ* treatment and the *in situ* 50 °C  $\text{H}_2\text{S}$  treatment, which is 20%  $(\text{NH}_4)_2\text{S}$  in DI water versus a flow rate of 0.1 SCCM of  $\text{H}_2\text{S}$  in  $\text{H}_2$ .

Considering the results in Table III, it is evident that the interface state densities are not related to the thickness of the IL oxide, as the IL oxide is thicker for the  $(\text{NH}_4)_2\text{S}$  samples (1.3 nm) when compared to the *in situ*  $\text{H}_2\text{S}$  samples (0.83–0.9 nm), while the  $\text{Pd}/\text{HfO}_2/\text{InGaAs}/\text{InP}$  MOS structure with the  $(\text{NH}_4)_2\text{S}$  surface preparation exhibits a reduced interface state density. In addition, the frequency dependence of the *CV* response as shown in Fig. 5 has also been observed for different  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  surface preparations and different high- $k$  oxide layers.<sup>8,27</sup> These results indicate that the interface defects detected by the *CV* and *GV* analysis originate from the  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  surface.

This work has presented the results of a study examining the structural properties, chemical composition, and interface defect concentrations in  $\text{Pd}/\text{HfO}_2/\text{In}_{0.53}\text{Ga}_{0.47}\text{As}/\text{InP}$  MOS structures for varying  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  surface treatments prior to  $\text{HfO}_2$  deposition. All samples exhibit an IL oxide, suggesting that the “self-cleaning” phenomenon is either limited or not present for ALD  $\text{Hf}[\text{N}(\text{CH}_3)_2]_4 + \text{H}_2\text{O}$  on  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$ . The composition of the IL is primarily a gallium oxide as determined by EELS. Varying the substrate surface starting conditions affects the IL oxide thickness, with a reduced IL thickness for either *in situ*  $\text{H}_2\text{S}$  or  $(\text{NH}_4)_2\text{S}$  when compared to deposition on the  $\text{InGaAs}$  native oxides. The  $(\text{NH}_4)_2\text{S}$  process results in a marked increase in  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  surface roughness, which may have implications for electron mobility degradation in  $\text{InGaAs}$  MOSFETs. The  $(\text{NH}_4)_2\text{S}$  and  $\text{H}_2\text{S}$  at 50 °C treatments are the most effective at reducing the peak interface state density in the upper gap with approximate peak interface state densities at  $\sim E_v + 0.7 \text{ eV}$  of  $1 \times 10^{12} \text{ cm}^{-2} \text{eV}^{-1}$  and  $3.7 \times 10^{11} \text{ cm}^{-2} \text{eV}^{-1}$  for the *in situ*  $\text{H}_2\text{S}$  sample treated at 50 °C and the  $(\text{NH}_4)_2\text{S}$  treated samples respectively. The  $\text{HfO}_2$   $n$ - $\text{InGaAs}/\text{InP}$  structures also exhibit a peak in the interface defect density at  $\sim 0.4 \text{ eV}$

above the valence band edge with peak concentrations of  $2 \times 10^{13} \text{ cm}^{-2} \text{eV}^{-1}$  for the *in situ*  $\text{H}_2\text{S}$  sample treated at 50 °C and  $6 \times 10^{12} \text{ cm}^{-2} \text{eV}^{-1}$  for the  $(\text{NH}_4)_2\text{S}$  treated sample. The experimental results are consistent with the interface defects originating from the  $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$  surface.

## ACKNOWLEDGMENTS

The authors thank Niti Goel and Wilman Tsai of Intel Corporation for HAADF-STEM/EELS analysis and Dan O’Connell, Tyndall National Institute, for sample processing. The authors would like to acknowledge the following for financial support of this work: Science Foundation Ireland (Grant No. 05/IN/1751) and the Irish Research Council for Science, Engineering, and Technology.

- <sup>1</sup>Y. Xuan, Y. Q. Wu, and P. D. Ye, *IEEE Electron Device Lett.* **29**, 294 (2008).
- <sup>2</sup>S. Kovesnikov, N. Goel, P. Majhi, H. Wen, M. B. Santos, S. Oktyabrsky, V. Tokranov, R. Kambhampati, R. Moore, F. Zhu, J. Lee, and W. Tsai, *Appl. Phys. Lett.* **92**, 222904 (2008).
- <sup>3</sup>F. S. Aguirre-Tostado, M. Milojevic, C. L. Hinkle, E. M. Vogel, R. M. Wallace, S. McDonnell, and G. J. Hughes, *Appl. Phys. Lett.* **92**, 171906 (2008).
- <sup>4</sup>Y. Xuan, P. D. Ye, and T. Shen., *Appl. Phys. Lett.* **91**, 232107 (2007).
- <sup>5</sup>M. K. Hudait, G. Dewey, S. Datta, J. M. Fastenau, J. Kavalieros, W. K. Liu, D. Lubyshev, R. Pillarisetty, W. Rachmady, M. Radosavljevic, T. Rakshit, and R. Chau, *Tech. Dig. - Int. Electron Devices Meet.* **2007**, 625.
- <sup>6</sup>N. Goel, P. Majhi, C. O. Chui, W. Tsai, D. Choi, and J. S. Harris, *Appl. Phys. Lett.* **89**, 163517 (2006).
- <sup>7</sup>Y. C. Chang, M. L. Huang, K. Y. Lee, Y. J. Lee, T. D. Lin, M. Hong, J. Kwo, T. S. Lay, C. C. Liao, and K. Y. Cheng, *Appl. Phys. Lett.* **92**, 072901 (2008).
- <sup>8</sup>H.-S. Kim, I. Ok, M. Zhang, F. Zhu, S. Park, J. Yum, H. Zhao, J. C. Lee, P. Majhi, N. Goel, W. Tsai, C. K. Gaspe, and M. B. Santos, *Appl. Phys. Lett.* **93**, 062111 (2008).
- <sup>9</sup>A. M. Sonnet, C. L. Hinkle, M. N. Jivani, R. A. Chapman, G. P. Pollack, R. M. Wallace, and E. M. Vogel, *Appl. Phys. Lett.* **93**, 122109 (2008).
- <sup>10</sup>E. O’Connor, R. D. Long, K. Cherkaoui, K. K. Thomas, F. Chalvet, I. M. Povey, M. E. Pemble, B. Brennan, G. Hughes, S. B. Newcomb, and P. K. Hurley, *Appl. Phys. Lett.* **92**, 022902 (2008).
- <sup>11</sup>S. B. Newcomb, *Inst. Phys. Conf. Ser.* **179**, 357 (2003).
- <sup>12</sup>M. Kobayashi, P. T. Chen, Y. Sun, N. Goel, P. Majhi, M. Garner, W. Tsai, P. Pianetta, and Y. Nishi, *Appl. Phys. Lett.* **93**, 182103 (2008).
- <sup>13</sup>C. L. Hinkle, A. M. Sonnet, E. M. Vogel, S. McDonnell, G. J. Hughes, M. Milojevic, B. Lee, F. S. Aguirre-Tostado, K. J. Choi, H. C. Kim, J. Kim, and R. M. Wallace, *Appl. Phys. Lett.* **92**, 071901 (2008).
- <sup>14</sup>D. Shahrjerdi, D. I. Garcia-Gutierrez, T. Akyol, S. R. Bank, E. Tutuc, J. C. Lee, and S. K. Banerjee, *Appl. Phys. Lett.* **91**, 193503 (2007).
- <sup>15</sup>L. V. Goncharova, O. Celik, T. Gustafsson, E. Garfunkel, M. Warusawithana, D. G. Schlom, H. Wen, M. B. Santos, S. Sayan, W. Tsai, and N. Goel, *ECS Trans.* **11**, 117 (2007).
- <sup>16</sup>P. T. Chen, Y. Sun, E. Kim, P. C. McIntyre, W. Tsai, M. Garner, P. Pianetta, Y. Nishi, and C. O. Chui, *J. Appl. Phys.* **103**, 034106 (2008).
- <sup>17</sup>K. Heime, *InGaAs Field Effect Transistors* (Research Studies Press, Taun-

- ton, United Kingdom, 1989), p. 46.
- <sup>18</sup>E. Pelucchi, N. Moret, B. Dwir, D. Y. Oberli, A. Rudra, N. Gagneau, A. Kumar, E. Kapon, E. Levy, and A. Palevski, *J. Appl. Phys.* **99**, 093515 (2006).
- <sup>19</sup>P. Kruse, J. G. McLean, and A. C. Kummel, *J. Chem. Phys.* **113**, 20 (2000).
- <sup>20</sup>É. O'Connor, S. Monaghan, R. D. Long, A. O'Mahony, I. M. Povey, K. Cherkaoui, M. E. Pemble, G. Brammertz, M. Heyns, S. B. Newcomb, V. V. Afanas'ev, and P. K. Hurley, *Appl. Phys. Lett.* **94**, 102902 (2009).
- <sup>21</sup>E. Cartier and J. H. Stathis, *Appl. Phys. Lett.* **69**, 103 (1996).
- <sup>22</sup>B. J. O'Sullivan, P. K. Hurley, C. Leveugle, and J. H. Das, *J. Appl. Phys.* **89**, 3811 (2001).
- <sup>23</sup>P. K. Hurley, K. Cherkaoui, E. O'Connor, M. C. Lemme, H. D. B. Gottlob, M. Schmidt, S. Hall, Y. Lu, O. Bui, B. Raeissi, J. Piscator, O. Engstrom, and S. B. Newcomb, *J. Electrochem. Soc.* **155**, G13 (2008).
- <sup>24</sup>E. H. Nicollian and J. R. Brews, *MOS Physics and Technology* (Wiley, New York, 1982), Chap. 5.
- <sup>25</sup>K. S. K. Kwa, S. Chattopadhyay, N. D. Jankovic, S. H. Olsen, L. S. Driscoll, and A. G. O'Neill, *Semicond. Sci. Technol.* **18**, 82 (2003).
- <sup>26</sup>K. Martens, C. O. Chui, G. Brammertz, B. De Jaeger, D. Kuzum, M. Meuris, M. M. Heyns, T. Krishnamohan, K. Saraswat, H. E. Maes, and G. Groeseneken, *IEEE Trans. Electron Devices* **55**, 547 (2008).
- <sup>27</sup>N. Goel, P. Majhi, W. Tsai, M. Warusawithana, D. G. Schlom, M. B. Santos, J. S. Harris, and Y. Nishi, *Appl. Phys. Lett.* **91**, 093509 (2007).
- <sup>28</sup>P. K. Hurley, É. O'Connor, S. Monaghan, R. D. Long, A. O'Mahony, I. M. Povey, K. Cherkaoui, J. MacHale, A. J. Quinn, G. Brammertz, M. Heyns, S. B. Newcomb, V. V. Afanas'ev, A. M. Sonnet, R. V. Galatage, M. N. Jivani, E. M. Vogel, R. M. Wallace, and M. E. Pemble, "Structural and electrical properties of HfO<sub>2</sub>/n-InxGa1-xAs structures (x: 0, 0.15, 0.3 and 0.53)," *ECS Trans.* **25**(6), 113 (2009).