

**UCC Library and UCC researchers have made this item openly available.
Please [let us know](#) how this has helped you. Thanks!**

Title	Assessment of the dyeing properties of the pigments produced by <i>Talaromyces</i> spp.
Author(s)	Morales-Oyervides, Lourdes; Oliveira, Jorge C.; Sousa-Gallagher, Maria J.; Méndez-Zavala, Alejandro; Montañez, Julio Cesar
Publication date	2017
Original citation	Morales-Oyervides, L., Oliveira, J., Sousa-Gallagher, M., Méndez-Zavala, A. and Montañez, J. C. (2017) 'Assessment of the dyeing properties of the pigments produced by <i>Talaromyces</i> spp', <i>Journal of Fungi</i> , 3(3), 38 (9pp). doi: 10.3390/jof3030038
Type of publication	Article (peer-reviewed)
Link to publisher's version	http://www.mdpi.com/2309-608X/3/3/38 http://dx.doi.org/10.3390/jof3030038 Access to the full text of the published version may require a subscription.
Rights	© 2017, the Authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (http://creativecommons.org/licenses/by/4.0/) https://creativecommons.org/licenses/by/4.0/
Item downloaded from	http://hdl.handle.net/10468/4880

Downloaded on 2020-10-30T08:05:28Z

Article

Assessment of the Dyeing Properties of the Pigments Produced by *Talaromyces* spp.

Lourdes Morales-Oyervides ^{1,2} , Jorge Oliveira ¹, Maria Sousa-Gallagher ¹,
Alejandro Méndez-Zavala ²  and Julio Cesar Montañez ^{2,*}

¹ School of Engineering, University College Cork, Cork, Ireland; lourdesmorales@uadec.edu.mx (L.M.-O.); j.oliveira@ucc.ie (J.O.); M.deSousaGallagher@ucc.ie (M.S.-G.)

² Department of Chemical Engineering, Universidad Autónoma de Coahuila. Saltillo, Coahuila 25280, Mexico; alejandro.mendez@uadec.edu.mx

* Correspondence: julio.montanez@uadec.edu.mx; Tel.: +52-844-416-9213

Received: 1 June 2017; Accepted: 28 June 2017; Published: 5 July 2017

Abstract: The high production yields of pigments by *Talaromyces* spp. and their high thermal stability have implied that industrial application interests may emerge in the food and textile industries, as they both involve subjecting the colourants to high temperatures. The present study aimed to assess the potential application of the pigments produced by *Talaromyces* spp. in the textile area by studying their dyeing properties. Dyeing studies were performed on wool. The dyeing process consisted of three stages: scouring, mordanting, and dyeing. Two different mordants (alum, A; ferric chloride, F) were tested at different concentrations on fabric weight (A: 5, 10, 15%; F: 10, 20, 30%). The mordanting process had a significant effect on the final colour of the dyed fabrics obtained. The values of dyeing rate constant (k), half-time of dyeing ($t_{1/2}$), and sorption kinetics behaviour were evaluated and discussed. The obtained results showed that pigments produced by *Talaromyces* spp. could serve as a source for the natural dyeing of wool textiles.

Keywords: fungal pigments; dyeing properties; textiles; *Talaromyces*

1. Introduction

Market trends to use natural colourants as food additives [1], natural dyes [2], functional foods [3], and cosmetic products [4] represent an opportunity for the application of natural pigments in several sectors of industry.

The possibility to exploit biological sources such as microorganisms for the production of natural pigments has been recommended [5]. However, the successful application of microbial pigments relies on high production yields, reasonable production costs and capital investment, regulatory approval, pigment characterisation, and stability to environmental factors such as temperature and light. Among the microorganisms with potential to produce a vast variety of pigments (*Monascus* homologues) is *Talaromyces* spp. (formerly *Penicillium* spp.) [6,7].

There has been a considerable effort in performing studies regarding the optimisation of the production of *Talaromyces* pigments [8–11]; however, there are only a few studies on the application of pigments produced by this strain [12,13].

Talaromyces pigments are thermally stable [14], implying that industrial application interests can emerge in the food and textile industries, as both processes involve subjecting the colourants to high temperatures.

Colourants used by the textile industry are predominantly synthetic; however, synthetic dyes are not environment-friendly, and recently the textile industry has been challenged to ensure compliance with environmental issues [15]. Natural colourants are environmentally friendly and biodegrade more quickly than synthetic dyes [16].

Additionally, natural pigments present properties of great interest in the textile industry, such as antibacterial properties. Fabrics can act as carriers of bacteria responsible for undesirable odours. It has been shown that *Talaromyces* pigment extracts possess antimicrobial properties [17]. These properties, along with the absence of toxicity [18,19], make them a valuable alternative as natural colourants in the textile industry.

However, natural colourants still face a huge disadvantage against synthetic colourants. Dyeing textile with natural colourants usually involves issues of limited shade range and lower fastness properties of the dyed fabrics. These problems have been overcome applying a pretreatment to the textile with mordants in order to create affinity between the fibre and the dye. Selection of mordant and concentration is important in natural dyeing processes, as mordants can increase the depth of shade or drastically alter the final colour of the dyed fabric [2].

The present study aimed to assess the potential application of the pigments produced by *Talaromyces* spp. in the textile area by studying their dyeing capacity.

2. Materials and Methods

2.1. Microorganism and Inoculum Preparation

Talaromyces spp. was used for the production of red pigments (Department of Food Science and Technology, Autonomous University of Coahuila, Saltillo, Coahuila). The purified strain had been previously isolated and characterised as *Penicillium purpurogenum* GH2 [20,21]. *Penicillium purpurogenum* has, however, been transferred to *Talaromyces* spp. [22]. The strain was maintained on PDA (Potato dextrose agar) slants at 4 °C and sub-cultured periodically. Inoculum was prepared in Erlenmeyer flasks (125 mL in capacity) containing 25 mL of Potato Dextrose Broth medium (PDB medium, ATCC medium:336), which were sterilised and inoculated with a spore suspension (1×10^5 spores/mL) of *Talaromyces* spp. previously incubated for 5 days. The flasks were then incubated at 30 °C for 84 h in an orbital shaker (Innova 94, New Brunswick Scientific, Edison, NJ, USA) at 200 rpm [9,23].

2.2. Culture Media

The PDA medium was prepared with a concentration of 39.0 g/L (Bioxon, Mexico). The medium PDB medium was prepared by finely boiling 0.3 kg of diced potatoes in 500 mL of water until thoroughly cooked; then the potatoes were filtered through cheesecloth and water was added to the filtrate to complete a volume of 1.0 L. Finally, 20.0 g of glucose was added before sterilisation. The Czapek-dox modified medium [24] consisted of (g/L): D-xylose 15.0, NaNO₃ 3.0, MgSO₄·7H₂O 0.5, FeSO₄·7H₂O 0.1, K₂HPO₄ 1.0, KCl 1.0 and ethanol 20.0.

2.3. Cultivation Conditions for Pigment Production

The initial pH of the Czapek-dox modified medium was adjusted to 5.0 before sterilising by using 0.22 µm sterile membranes (Millipore, Billerica, MA, USA). A mycelial suspension of *Talaromyces* spp. was inoculated at 10% (v/v) in 125 mL Erlenmeyer flasks containing 25 mL of medium. The inoculated flasks were incubated at 30 ± 2 °C in an orbital shaker (Innova 94, New Brunswick Scientific, Edison, NJ, USA) at 200 rpm for 6 days.

2.4. Pigment Extraction

The pigment extraction was performed according to the methodology reported by Méndez-Zavala et al. (2011) [25]. The pigment extract was centrifuged at 8000 rpm and at 4 °C for 20 min (Sorvall, Primo R Biofuge Centrifugation Thermo, Waltham, MA, USA) and then filtered through a 0.45 µm cellulose membranes (Millipore, Billerica, MA, USA) for the subsequent analysis of pigments. In this study, only extracellular pigments were considered. The analysis of red pigment production was conducted by measuring the absorbance of the filtered extract at 500 nm using a

spectrophotometer (Cary 50, UV-Visible Varian, Palo Alto, CA, USA). This wavelength was selected by scanning the maximum sensitivity for the presence of the pigment (that is, the pigment absorbs maximum light at this wavelength). Red pigment extracts were stored in the dark at 4 °C before being used for the subsequent test.

2.5. Wool Dyeing Process

Wool fabric was bought at a local textile company. The dyeing process consisted of three stages: scouring [26], mordanting, and dyeing [12].

2.5.1. Fabric Scouring

The fabric was first scoured to remove any impurities so that they would not interfere with the dyeing process [26]. Wool was rinsed with 100 mL of hot distilled water (60 °C) per gram of wool; then, 18 mL of neutral soap per litre of water was added, along with 25% *w/v* of sodium carbonate, taking into consideration the wool weight. The mixture was heated to 60 °C and the wool was constantly moved from top to bottom. Then, the fabric was washed with water at ambient temperature (six times).

2.5.2. Fabric Mordanting

The fabric mordanting process was carried out using the pre-mordanting technique [12]. To assess the most appropriate mordant for *Talaromyces* spp. pigments, two different mordants were tested at different concentrations on the weight of fabric (Table 1). Concentrations were selected from literature according to recommended concentrations for these two mordants [27]. Wool was heated in mordant solutions at 70 °C for 1 h. Subsequently, the fabric was squeezed to remove excess liquid and then air dried at room temperature overnight.

Table 1. Mordants studied for the pre-mordanting process and selected concentrations. Codes were assigned.

Mordant	Concentration, % <i>w/w</i>	Code
Ferric chloride	10	F1
	20	F2
	30	F3
Alum	5	A1
	10	A2
	15	A3

2.6. Dyeing

The pre-mordanted wool was dyed with 40 mL of pigment extract (40:1, pigment extract per gramme of fabric) in a conical flask at 80 °C for 90 min. pH was not controlled. The colour of fabrics after dyeing was determinate by CIELAB colour coordinates using ColorEye XTS colorimeter (GretagMacbeth, Grand Rapids, MI, USA).

Pigment uptake was determined by measuring the optical density of the dye solution samples at a wavelength of 500 nm [27]. Percentage of pigment uptake (*q*, %) was calculated using the following equation:

$$q = \frac{OD_o - OD_i}{OD_o} * 100 \quad (1)$$

where OD_o is the initial optical density (500 nm) of the dye bath, and OD_i is the optical density after dyeing at different sampling times (*i* min).

The first-order rate equation of Lagergren, which is one of the most widely used equations for the sorption of solute from a liquid solution, was employed to describe the pigment sorption kinetics.

Rearrangement of the Lagergren model [28] was used for the variation of the adsorbed pigment as a function of time:

$$\frac{q_t}{q_r} = 1 - \frac{\exp[-kt_r](t/t_r)}{1 - \exp(-kt_r)} \quad (2)$$

where q_t and q_r are the amount of adsorbed pigment at time t (min) and at equilibrium (%), respectively, k is the first-order rate constant (min^{-1}), and t_r is the longest time of the sorption process (min).

2.7. Data Analysis

The model parameters were estimated by non-linear regression analysis [29]. Results were analysed statistically by factorial ANOVA to test statistical differences ($p < 0.05$), followed by Tukey's test at 5% probability for comparisons. Statistical and regression analyses were made with STATISTICA 7.1. (StatSoft, Inc., Tulsa, OK, USA, 2005).

3. Results and Discussion

Dying Properties of Pigments

The effect of the mordant used on L^* , a^* , and b^* parameters are given in Table 2; L^* represents a lightness value (a higher lightness value represents a lower colour yield). a^* and b^* represent the tone of the colour; positive values of a^* and b^* represent redder and yellowish tones, respectively.

Total colour difference ΔE^* between the dyed fabrics and the undyed wool was calculated as:

$$\Delta E^* = \sqrt{(L_U^* - L_D^*)^2 + (a_U^* - a_D^*)^2 + (b_U^* - b_D^*)^2} \quad (3)$$

where sub-index U and D represent undyed and dyed wool, respectively, for L^* , a^* , and b^* values.

Fabrics were qualitatively perceived as different; the dyeing process using mordant F presented a red colour while the dyeing process using mordant A showed a red tending to brown colour. Colorimetric studies indicated that the tested mordants significantly affected the colour exhibited by the fabric. The dyed wool using mordant F presented a higher total colour difference from the undyed wool than the dyed wool using mordant A (Table 2). Higher values of a^* were obtained with mordant F in comparison with mordant A, indicating that more reddish tones can be obtained using mordant F. Meanwhile, b^* values indicated that more yellowish tones can be obtained with mordant A. These results were more evident with the hue values obtained; hue values near to 0 indicated the degree of redness while values near to 90 represented the level of yellowness. Moreover, the wool dyed using mordant F presented a higher saturation of colour (Chroma) and a higher yield (L^*) than that dyed with mordant A.

Dyed fabrics obtained here presented a stronger shade (red colour) than the optimum conditions reported for the dyeing of cotton using pigments produced by different fungal strains (*Monascus purpureus*, *Isaria farinose*, *Emericella nidulans*, *Fusarium verticillioides* and *Penicillium purpurogenum*) [12].

Similarly, a^* and b^* values were higher than those reported for the dyeing of leather and silk with *Talaromyces* pigments [11,30]; however, those results were attained without the addition of mordants.

Mordant concentration also affected the colour exhibited by the dyed fabric. When mordant F was used, the colour yield obtained increased with concentration. However, there was not a statistical difference between F2 and F3. It is noted that a more reddish colour (a^*) was obtained by increasing the mordant concentration while there was not a statistical difference achieving a yellow tone (b^*) between F2 and F3 or between F1 and F2. In terms of colour saturation, hue, and total colour difference, there was not statistical difference between F2 and F3 indicating that if an F concentration between 20 and 30% w/w is used during the mordanting process, the same colour can be obtained.

Different results were obtained using mordant A; colour yield increased by increasing mordant concentration. A more reddish colour (a^*) was obtained using the highest concentration while the yellowish tone (b^*) was not affected by concentration. Furthermore, the concentration did not affect colour saturation (Chroma). A higher degree of redness (Hue) and higher total colour difference (ΔE^*) was attained using the highest concentration of mordant A.

These results are consistent with those reported by Arroyo-Figueroa et al. (2011) [26], who stated that a colour variation in terms of CIELAB scale is obtained as function of mordant concentration during the dyeing process using natural colourants.

In technical dyeing using synthetic dyes, a total colour difference of 1 is accepted as a tolerable colour difference between dyeings. However, with the introduction of natural dyes into the textile dyeing process, a wider total colour difference can be accepted ($\Delta E^* = 2$) [31]. Results demonstrated that, independent of the mordant and concentration tested, an acceptable colour difference between dyeings was obtained ($\Delta E^* = 0.71\text{--}1.70$).

The effect of the dyeing process time on pigment uptake using different mordants at different concentrations is shown in Figure 1. It can be seen that dyeings with mordant F presented higher values of pigment uptake (42.54–82.44%) than mordant A (33.98–41.98%). In Table 3 are listed the kinetic parameters obtained with the regression analysis of Equation (2). When mordant F was used, pigment uptake at equilibrium (q_r) increased as mordant concentration increased. Mordant A did not show a significant difference between concentrations A1 and A2, reaching the maximum pigment uptake with concentration A3. The higher pigment uptake here obtained ($81.33 \pm 0.43\%$) is similar to the maximum (80%) reported by Velmurugan et al. (2010) [12], which was achieved dyeing cotton with red pigments produced by *Monascus purpureus*.

Table 2. L^* , a^* , b^* values of dyed wool.

Experiment	Colour Coordinates					
	L^*	a^*	b^*	Chroma	Hue	ΔE^*
Wool	93.89 ± 1.16	0.44 ± 0.22	5.15 ± 1.47	5.17 ± 1.47	84.94 ± 2.63	0.00
F1	31.39 ± 1.11 ^b	24.35 ± 0.44 ^c	21.01 ± 0.20 ^c	32.16 ± 0.23 ^b	40.79 ± 0.76 ^b	68.78 ± 0.96 ^b
F2	28.20 ± 0.64 ^a	27.62 ± 0.68 ^b	20.61 ± 0.41 ^{bc}	34.47 ± 0.64 ^a	36.73 ± 0.78 ^a	72.76 ± 1.70 ^a
F3	27.53 ± 0.65 ^a	28.91 ± 0.35 ^a	21.87 ± 0.81 ^b	36.25 ± 0.25 ^a	37.10 ± 1.34 ^a	74.14 ± 0.90 ^a
A1	44.47 ± 0.68 ^e	14.84 ± 0.15 ^e	27.34 ± 0.32 ^a	31.11 ± 0.34 ^d	61.50 ± 0.21 ^d	56.07 ± 0.71 ^d
A2	42.48 ± 0.43 ^d	15.07 ± 0.24 ^e	27.83 ± 0.25 ^a	31.65 ± 0.13 ^d	61.56 ± 0.57 ^d	58.09 ± 1.65 ^d
A3	37.08 ± 0.56 ^c	17.14 ± 0.35 ^d	27.76 ± 0.14 ^a	32.63 ± 0.18 ^d	58.32 ± 0.57 ^c	63.40 ± 1.52 ^c

Different letters in each column indicate significant differences (Tukey’s post-hoc comparison, $p < 0.05$).

Results showed that there was no statistical difference in terms of exponential rate (k) using mordant F at all concentrations and mordant A at concentrations A2 and A3. Only mordant A showed the lowest exponential rate at the lowest concentration studied.

Table 3. Kinetic parameters and goodness of fit of the data.

Experiment	q_r , %	k , min ⁻¹	R^2
F1	50.56 ± 0.57 ^c	0.0504 ± 0.0028 ^a	0.98
F2	76.99 ± 0.55 ^b	0.0542 ± 0.0021 ^a	0.99
F3	81.33 ± 0.43 ^a	0.0537 ± 0.0015 ^a	0.99
A1	36.91 ± 0.82 ^e	0.0218 ± 0.0011 ^b	0.98
A2	35.40 ± 0.33 ^e	0.0497 ± 0.0023 ^a	0.99
A3	41.02 ± 0.39 ^d	0.0569 ± 0.0030 ^a	0.99

Different letters in each column indicate significant differences (Tukey’s post-hoc comparison, $p < 0.05$).

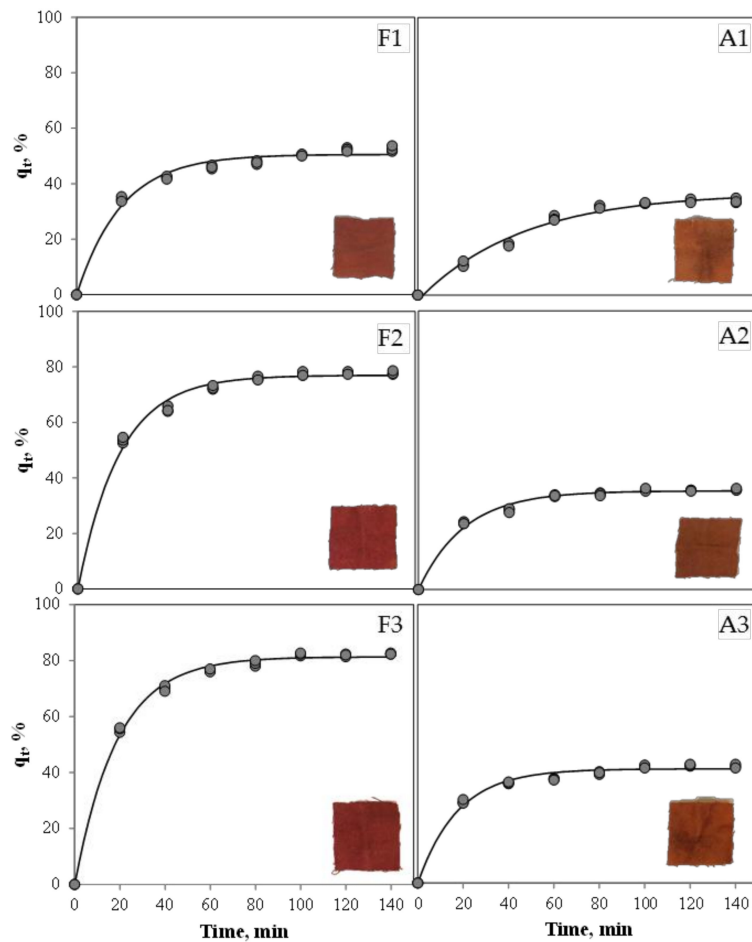


Figure 1. Effect of mordant type and concentration on pigment sorption on wool. Circles represent experimental data points and continuous lines represent the Lagergren model.

In literature, sorption curves are classified into four zones (0 to 4) according to the kt_r value; the kinetic behavior goes from no adsorption to drastic (Please see sorption kinetic behavior reported by Tseng et al. [28]).

The time of half dyeing $t_{1/2}$ is also used to express the time required for a fabric to adsorb half of the amount of the dye adsorbed at equilibrium ($q_t/q_r = 0.5$), calculated as:

$$t_{1/2} = \frac{\ln(2)}{k} \tag{4}$$

Table 4 lists the dimensionless rate constants (kt_r), the half dyeing time values ($t_{1/2}$), and the zone of kinetic sorption behavior presented for the mordants studied at three concentration levels.

Table 4. Sorption kinetic parameter (kt_r), $t_{1/2}$ and zone of the sorption behavior.

Experiment	kt_r	$t_{1/2}$, min	Zone
F1	7.06	13.74	III
F2	7.58	12.79	III
F3	7.51	12.92	III
A1	3.04	31.84	II
A2	6.95	13.95	III
A3	7.97	12.17	III

Results showed that most of sorption kinetic curves fell into zone III (Kinetic curve type, rapidly rise; kinetic behavior, quick), while only the dyeing process using A1 fell into zone II (Kinetic curve type, continuously rising; kinetic behavior, good).

The $t_{1/2}$ values obtained were in range with those reported for the optimised conditions for dyeing wool ($t_{1/2} = 13.1$ min) with natural anthraquinones dyes produced by the fungus *Fusarium oxysporum* [32]. The $t_{1/2}$ values are relatively short in comparison with the longest time of the sorption process (t_r), which could result in undesired colour yields. Thus, the above kinetics are useful to establish a target value ($q_t/q_r > 0.5$) to assist the engineering design and optimisation of the dyeing process of wool by *Talaromyces* pigments.

4. Conclusions

The above results showed the feasible potential applications of the pigments produced by *Talaromyces* spp.

These pigments could serve as a useful alternative source for the natural dyeing of wool textiles. High values of pigment uptake on the fabric were obtained. The values of dyeing rate constant (k), half-time of dyeing ($t_{1/2}$) and sorption kinetics behaviour compare well with other natural dyes used for dyeing textile. However, the process still needs to be optimised in terms of dyeing process conditions (pigment concentration, pH, temperature).

It is concluded that the mordant used plays an important role in the dyeing process. Colorimetric studies showed that it is possible to attain a strong red shade; therefore, these pigments can compete with other synthetic or natural red dyes.

From this point onward, full characterisation of the molecules, toxicity studies, and more in-depth analyses such as molecular interactions between the dye and the fabric are worth further investigation.

Acknowledgments: Author Lourdes Morales-Oyervides acknowledges CONACyT-México for the financial support provided for conducting her PhD studies (215490-2011).

Author Contributions: Julio Cesar Montañez and Jorge Oliveira conceived and designed the experiments; Lourdes Morales-Oyervides performed the experiments; Jorge Oliveira and Maria Sousa-Gallagher analysed the data; Alejandro Méndez-Zavala and Julio Cesar Montañez contributed reagents/materials/analysis tools; Lourdes Morales-Oyervides wrote the paper.

Conflicts of Interest: The authors declare no conflict of interest.

References

- Carocho, M.; Morales, P.; Ferreira, I.C.F.R. Natural food additives: Quo vadis? *Trends Food Sci. Technol.* **2015**, *45*, 284–295. [[CrossRef](#)]
- Shahid, M.; Mohammad, F. Recent advancements in natural dye applications: A review. *J. Clean. Prod.* **2013**, *53*, 310–331. [[CrossRef](#)]
- Fernández-García, E.; Carvajal-Lérida, I.; Jarén-Galán, M.; Garrido-Fernández, J.; Pérez-Gálvez, A.; Hornero-Méndez, D. Carotenoids bioavailability from foods: From plant pigments to efficient biological activities. *Food Res. Int.* **2012**, *46*, 438–450. [[CrossRef](#)]
- Kostick, R.; Wang, S.; Wang, J. Color Cosmetics—Coloring/Staining the Skin from Fruit and Plant Color Pigments. Patent US20060280762, 2006.
- Venil, C.K.; Zakaria, Z.A.; Ahmad, W.A. Bacterial pigments and their applications. *Process Biochem.* **2013**, *48*, 1065–1079. [[CrossRef](#)]
- Arai, T.; Kojima, R.; Motegi, Y.; Kato, J.; Kasumi, T.; Ogihara, J. PP-O and PP-V, *Monascus* pigment homologs, production and phylogenetic analysis in *Penicillium purpurogenum*. *Fungal Biol.* **2015**, *119*, 1226–1236. [[CrossRef](#)] [[PubMed](#)]
- Mapari, S.A.S.; Hansen, M.E.; Meyer, A.S.; Thrane, U. Computerized screening for novel producers of *Monascus*-like food pigments in *Penicillium* species. *J. Agric. Food Chem.* **2008**, *56*, 9981–9989. [[CrossRef](#)] [[PubMed](#)]

8. Santos-Ebinuma, V.C.; Roberto, I.C.; Teixeira, M.F.S.; Pessoa, A., Jr. Improvement of submerged culture conditions to produce colorants by *Penicillium purpurogenum*. *Braz. J. Microbiol.* **2014**, *45*, 731–742. [[CrossRef](#)] [[PubMed](#)]
9. Morales-Oyervides, L.; Oliveira, J.C.; Sousa-Gallagher, M.J.; Méndez-Zavala, A.; Montañez, J.C. Selection of best conditions of inoculum preparation for optimum performance of the pigment production process by *Talaromyces* spp. using the Taguchi method. *Biotechnol. Prog.* **2017**. [[CrossRef](#)] [[PubMed](#)]
10. Padmapriya, C.; Murugesan, R. Optimization of physical parameters on polyketide red pigment production from *Penicillium purpurogenum*. *Trends Biosci.* **2014**, *7*, 1664–1667.
11. Sudha; Gupta, C.; Aggarwal, S. Optimization and extraction of extra and intracellular color from *Penicillium minioluteum* for application on protein fibers. *Fibers Polym.* **2017**, *18*, 741–748. [[CrossRef](#)]
12. Velmurugan, P.; Kim, M.J.; Park, J.S.; Karthikeyan, K.; Lakshmanaperumalsamy, P.; Lee, K.J.; Park, Y.J.; Oh, B.T. Dyeing of cotton yarn with five water soluble fungal pigments obtained from five fungi. *Fibers Polym.* **2010**, *11*, 598–605. [[CrossRef](#)]
13. Dhale, M.A.; Vijay-Raj, A.S. Pigment and amylase production in *Penicillium* sp. NIOM-02 and its radical scavenging activity. *Int. J. Food Sci. Technol.* **2009**, *44*, 2424–2430. [[CrossRef](#)]
14. Morales-Oyervides, L.; Oliveira, J.C.; Sousa-Gallagher, M.J.; Méndez-Zavala, A.; Montañez, J.C. Effect of heat exposure on the colour intensity of red pigments produced by *Penicillium purpurogenum* GH2. *J. Food Eng.* **2015**, *164*, 21–29. [[CrossRef](#)]
15. Arora, S. Textile Dyes: It's impact on environment and its treatment. *J. Bioremediation Biodegrad.* **2014**, *5*, 1. [[CrossRef](#)]
16. Borges, M.E.; Tejera, R.L.; Díaz, L.; Esparza, P.; Ibáñez, E. Natural dyes extraction from cochineal (*Dactylopius coccus*). New extraction methods. *Food Chem.* **2012**, *132*, 1855–1860. [[CrossRef](#)]
17. Patil, S.; Sivanandhan, G.; Thakare, D. Effect of physical and chemical parameters on the production of Red exopigment from *Penicillium purpurogenum* isolated from spoilt onion and study of its antimicrobial activity. *Int. J. Curr. Microbiol. Appl. Sci.* **2015**, *4*, 599–609.
18. Chadni, Z.; Rahaman, M.H.; Jerin, I.; Hoque, K.M.; Reza, M.A. Extraction and optimisation of red pigment production as secondary metabolites from *Talaromyces verruculosus* and its potential use in textile industries. *Mycology* **2017**, *8*, 48–57. [[CrossRef](#)]
19. Sopandi, T.; Wardah, W. Sub-Acute toxicity of pigment derived from *Penicillium resticulosum* in mice. *Microbiol. Indones.* **2012**, *6*, 35–41. [[CrossRef](#)]
20. Cruz-Hernández, M.; Rodríguez, R. Aislamiento y caracterización morfológica de cepas microbianas degradadoras de taninos. In Proceedings of the XXII Annual Meeting of the Mexican Academy of Chemical Engineering (AMIDIQ), Mazatlan, Mexico, 9 September 2001.
21. Espinoza-Hernández, T. Caracterización Morfológica, Fisiológica y Molecular de tres Cepas Fúngicas Productoras de Pigmentos. Bachelor's Thesis, Universidad Autónoma de Coahuila, Saltillo, México, 2004.
22. Frisvad, J.C.; Yilmaz, N.; Thrane, U.; Rasmussen, K.B.; Houbraken, J.; Samson, R.A. *Talaromyces atroseus*, a new species efficiently producing industrially relevant red pigments. *PLoS ONE* **2013**, *8*, e84102. [[CrossRef](#)] [[PubMed](#)]
23. Morales-Oyervides, L.; Oliveira, J.C.; Sousa-Gallagher, M.J.; Méndez-Zavala, A.; Montañez, J.C. Quantitative assessment of the impact of the type of inoculum on the kinetics of cell growth, substrate consumption and pigment productivity by *Penicillium purpurogenum* GH2 in liquid culture with an integrated stochastic approach. *Food Bioprod. Process.* **2015**, *96*, 221–231. [[CrossRef](#)]
24. Méndez-Zavala, A. Identificación de Factores que Afectan la Producción de Pigmentos por *Penicillium purpurogenum* GH2 y Obtención de Perfiles Cromatográficos. Master's Thesis, Universidad Autónoma de Coahuila, Saltillo, México, 2011.
25. Méndez-Zavala, A.; Pérez, C.; Montañez, J.C.; Martínez, G.; Aguilar, C.N. Red pigment production by *Penicillium purpurogenum* GH2 is influenced by pH and temperature. *J. Zhejiang Univ. Sci. B* **2011**, *12*, 961–968. [[CrossRef](#)] [[PubMed](#)]
26. Arroyo-Figueroa, G.; Ruiz-Aguilar, G.M.L.; Cuevas-Rodríguez, G.; Sanchez, G.G. Cotton fabric dyeing with cochineal extract: Influence of mordant concentration. *Color. Technol.* **2011**, *127*, 39–46. [[CrossRef](#)]
27. Velmurugan, P. Studies on the Production and Dyeing Properties of Water Soluble Pigments from Filamentous Fungi. Ph.D. Thesis, Bharathiar University, Coimbatore, India, 2008.

28. Tseng, R.-L.; Wu, F.-C.; Juang, R.-S. Characteristics and applications of the Lagergren's first-order equation for adsorption kinetics. *J. Taiwan Inst. Chem. Eng.* **2010**, *41*, 661–669. [[CrossRef](#)]
29. Hill, C.G.J.; Grieger-Block, R.A. Kinetic data: Generation, interpretation, and use. *Food Technol.* **1980**, *34*, 55–66.
30. Gupta, C.S.; Aggarwal, S. Dyeing wet blue goat nappa skin with a microbial colorant obtained from *Penicillium minioluteum*. *J. Clean. Prod.* **2016**, *127*, 585–590.
31. Bechtold, T.; Mahmudali, A.; Mussak, R. Natural dyes for textile dyeing: A comparison of methods to assess the quality of Canadian golden rod plant material. *Dyes Pigments* **2007**, *75*, 287–293. [[CrossRef](#)]
32. Nagia, F.A.; El-Mohamedy, R.S.R. Dyeing of wool with natural anthraquinone dyes from *Fusarium oxysporum*. *Dyes Pigment.* **2007**, *75*, 550–555. [[CrossRef](#)]



© 2017 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<http://creativecommons.org/licenses/by/4.0/>).