

Title	Architected porous metals in electrochemical energy storage
Authors	Egorov, Vladimir;O'Dwyer, Colm
Publication date	2020-02-21
Original Citation	Egorov, V., and O'Dwyer, C. (2020) 'Architected porous metals in electrochemical energy storage'. Current Opinion in Electrochemistry, 21, pp. 201-208. doi: 10.1016/j.coelec.2020.02.011
Type of publication	Article (peer-reviewed)
Link to publisher's version	<a href="https://www.sciencedirect.com/science/article/pii/S2451910320300363">https://www.sciencedirect.com/science/article/pii/S2451910320300363</a> - 10.1016/j.coelec.2020.02.011
Rights	© 2020 Elsevier B.V. This is an open access article under the CC BY-NC-ND license ( <a href="https://creativecommons.org/licenses/by-nc-nd/4.0/">https://creativecommons.org/licenses/by-nc-nd/4.0/</a> ). - <a href="https://creativecommons.org/licenses/by-nc-nd/4.0/">https://creativecommons.org/licenses/by-nc-nd/4.0/</a>
Download date	2024-04-25 11:53:15
Item downloaded from	<a href="https://hdl.handle.net/10468/9789">https://hdl.handle.net/10468/9789</a>



## Review Article

## Architected porous metals in electrochemical energy storage

Vladimir Egorov<sup>1</sup> and Colm O'Dwyer<sup>1,2,3,4</sup>**Abstract**

Porous metallic structures are regularly used in electrochemical energy storage (EES) devices as supports, current collectors, or active electrode materials. Bulk metal porosity, dealloying, welding, or chemical synthesis routes involving crystal growth or self-assembly, for example, can sometimes provide limited control of porous length scale, ordering, periodicity, reproducibility, porosity, and surface area. Additive manufacturing has shown the potential to revolutionize the fabrication of architected metals, allowing complex geometries not usually possible by traditional methods, by enabling complete design freedom of a porous metal based on the required physical or chemical property to be exploited. We discuss properties of porous metal structures in EES devices and provide some opinions on how architected metals may alleviate issues with electrochemically active porous metal current collectors, and provide opportunities for optimum design based on electrochemical characteristics required by batteries, supercapacitors or other electrochemical devices.

**Addresses**

<sup>1</sup> School of Chemistry, University College Cork, Cork, T12 YN60, Ireland

<sup>2</sup> Micro-Nano Systems Centre, Tyndall National Institute, Lee Maltings, Cork, T12 R5CP, Ireland

<sup>3</sup> AMBER@CRANN, Trinity College Dublin, Dublin 2, Ireland

<sup>4</sup> Environmental Research Institute, University College Cork, Lee Road, Cork T23 XE10, Ireland

Corresponding author: O'Dwyer, Colm ([c.odwyer@ucc.ie](mailto:c.odwyer@ucc.ie))

**Current Opinion in Electrochemistry** 2020, **21**:201–208

This review comes from a themed issue on **Energy Storage**

Edited by **Mike Lyons** and **Kenneth I. Ozoemena**

For a complete overview see the [Issue](#) and the [Editorial](#)

Available online 21 February 2020

<https://doi.org/10.1016/j.coelec.2020.02.011>

2451-9103/© 2020 Elsevier B.V. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

**Keywords**

Porous metals, Current collector, Additive manufacturing (AM), Metal foams, Electrochemical energy storage (EES), Batteries, Supercapacitors, Metallic lattice, 3D printing.

**Introduction**

Porous metals, in ordered or random form, have been a mainstay in electrochemical science and technology [1–4]. Porous metals and metallic foam have been used as high surface area electrodes, current collectors, substrates, counter electrodes, or even faraday cages. We now have a wide range of methods to fabricate porous metal with different porosity length scales, and with different degrees of ordering or periodicity [5–8\*\*]. While certain metals, their alloys, and their physical properties fundamentally limit the range of latticed or porous structures that can be formed, the choice of metal for electrochemical energy storage applications [9–12] is usually based on surface activity, passivity, electrical conductivity, and weight. The length scale of porosity [13], and the types of porous ordering are not always obtainable “a la carte” for the electrochemical application when open-worked from the bulk metal. We examine the nature of the porous metal formation, address some limitation for transition metals and noble metals in foam, lattice or porous form [14] for electrochemical energy storage devices and discuss how the choice of metal and the method of fabrication influence the nature of the porosity and their relative benefit in energy storage devices.

While directed self-assembly from chemical routes, sacrificial templates [15], dealloying approaches, or macropore formation methods can create a wide variety of porous structures, including metals, replication and minimization (or elimination) of structural defects is a persistent problem when they are used as electrodes [16,17]. Additive manufacturing methods, including 3D printing, have evolved to allow large and small structures to be engineered to provide long range periodic or aperiodic metallic porous structures [18–21] that are, by comparison, almost defect free in their lattice structure. Accurate replication of any porous structure will allow for better quantitative comparison between supercapacitor, battery and other electrodes (e.g., water splitting and many more electrochemical processes [22]), provide a defined surface area for determining intrinsic geometrical surface area [23–25] effects in electrochemical processes, and allow us to choose metals and porous structures to take advantage of specific

physical properties useful to the application, e.g., toughness, thermal conductivity, flexibility, surface activity, etc.

Here, we provide a summary perspective on porous metal structures using in electrochemical energy storage, particularly supercapacitors and batteries, and the primary methods used to date to make these porous metals. We discuss periodic porous metals and porous metal foams, the main methods used to make these structures, and provide our opinion on the advent of additive manufacturing for metallic lattice or porous metal formation for EES devices. We also discuss the merits of some additive manufacturing approaches that can create metals in more complex and useful structures that cannot be achieved, for example, from the porosity of bulk metals, dealloying, and chemical assembly routes. These methods for porous metals widen the choice of active materials for electrochemical applications, or passive, conductive current collectors that do not contribute to unwanted parasitic activity.


### Porous metal fabrication methods

Metallic porous materials can exist in a variety of forms, such as foams, sponges, micro/nanolattices, micro/nanoarrays, etc.[19–21,23\*,24] Structurally, porous

materials can be categorized as stochastic (random) and ordered (mostly periodic, but aperiodic 3D-tiling is also possible), depending on the randomness of pore size and arrangement (Figure 1a) [5,20]. Examples of stochastic structures include metal foams and sponges, whereas micro or nanolattices belong to the ordered category. In order to achieve high accessible specific surface area and create continuous diffusion pathways, which is important for EES applications, the porous structures should ideally be open cell [5\*], i.e., internal pores should be well-interconnected minimizing the number of isolated cavities. Complete interconnectivity is more easily achieved in the engineered lattices and arrays, particularly when the structure is imposed by design. For other types of structures, such as bottom-up or self-assembled, for example, interconnectivity is a function of the method and conditions of fabrication. Stochastic materials are usually isotropic at scales larger than a cell size; however, periodic structures can be highly anisotropic when the spatial arrangement or dimensions of unit blocks have a prevalent direction [20\*].

*Metallic foams and sponges* (open-cell foams) are traditionally produced using two main approaches: by creating pores in the bulk material or by fusing many separate cells into a single structure [26]. The former

Figure 1

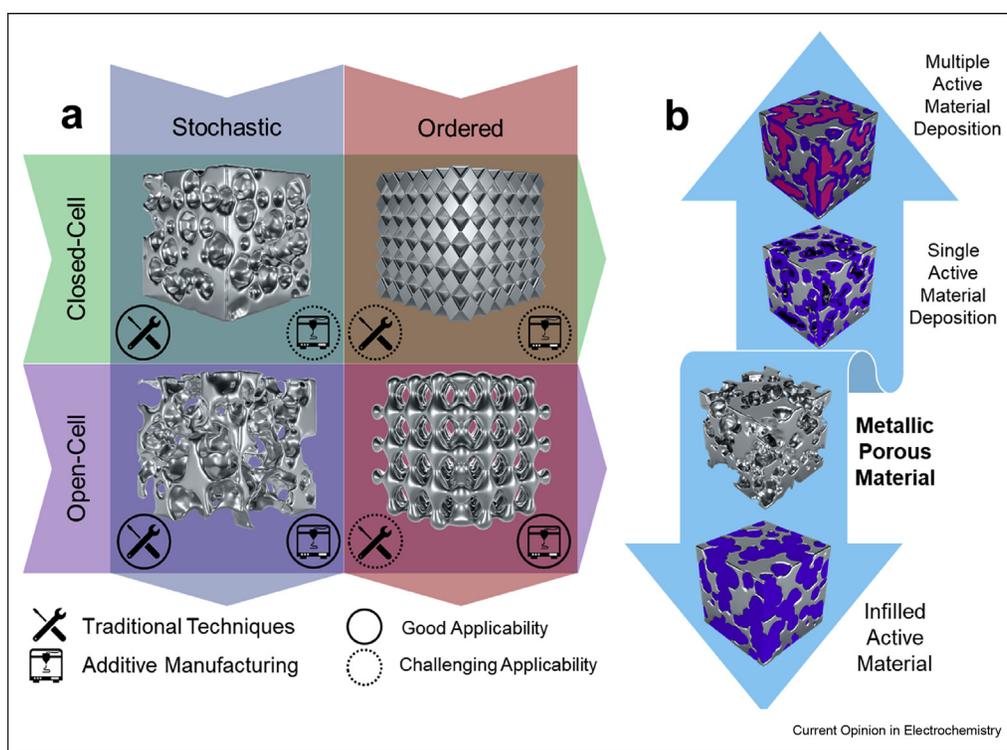

(a) Types of metallic porous structures and applicability of traditional and AM techniques to the fabrication of each material type. (b) Main approaches for filling of metallic porous structures with active materials in EES devices, such as battery electrodes.

approach, in turn, can be implemented using many different techniques. *Gas injection* employs the pumping of pressurized gas into metal melt forming gas bubbles, which then stay after cooling and form pores. *The addition of foaming agents*, such as metal hydrides, carbonates, oxides, which release gases upon heating, is another technique for metal foam fabrication. *Space holder and template-directed* methods utilize various fillers (e.g., polymer beads, salt grains, hollow spheres, woven wire meshes) or templates (e.g., polymer foams, ceramic templates, etc.), which are subsequently removed, for example, by pyrolysis or solvent leaching. *Sponge replication method* can be viewed as a variation of the previous methods in which metallic powder slurry is impregnated into polymeric foam followed by pyrolysis of polymer and post-sintering [6]. *Dealloying*, a corrosion process in which one or several components of an alloy are dissolved, is a powerful method of fabrication of metal foams and sponges capable of producing micro-, nano- and hierarchical (micro-nano) pores [13,27,28].

*Periodic metallic structures*, such as lattices or arrays, can also be fabricated by several different methods. *Investment casting* is one of the traditional industrial techniques used in metallurgy capable of producing complex high-precision patterns [19,29]. This method is based on the creation of a sacrificial master pattern (e.g., by rapid prototyping methods) from wax or polymer, which is then used to fabricate a mold by coating. Wax or polymer are subsequently removed by melting, pyrolysis or evaporation to leave a hollow mold, in which molten metal is later injected. *Deformation forming* can involve metal sheet perforation, deformation by pressing, shearing, expanding, and layer stacking. The unit cell size achievable by this technique can be as low as a millimeter scale, which is quite large for micro- or nanolattice fabrication. Using *metal textiles (woven or non-woven)* is another conventional approach to manufacturing periodic lattice materials, where metal wires are intertwined at various orientations, bent, sheared, or otherwise deformed, and optionally, soldered [21]. These approaches are relatively fast and inexpensive, but in some cases are limited by the specifications and precision of the equipment and forming methods.

The traditional techniques for metallic lattice fabrication have a number of disadvantages, such as a relatively high cost and complexity, slow fabrication rate, low number of cells per unit length (hence, large feature size), waste of sacrificial materials, limited choice of suitable low-viscosity metals or alloys (in the case of investment casting). Due to the nature of the fabrication process, some methods have limited capability for producing complex geometrical structures.

*Additive manufacturing (AM)*, or *3D printing*, which is a common name for a family of manufacturing methods

utilizing layer-by-layer fabrication of three-dimensional models created with computer-aided design (CAD) [3], has been gaining popularity in the fabrication of complex shapes and objects, in particular periodic metallic structures. Contrary to conventional techniques we have just discussed, AM is highly versatile and enables fabrication of both stochastic and ordered open-cell structures with mono- or hierarchical scaling of pore sizes, and these will prove useful for new form factor batteries and supercapacitors[30]. Given the ongoing improvements in 3D printing hardware, AM is able to produce high-resolution, geometrically accurate objects having small cell unit size at low cost and relatively fast production rate. This makes AM a superior and very promising technique compared to the conventional methods (see Figure 1a).

It is particularly important that 3D printing facilitates the fabrication of arbitrary ordered open-cell lattices with high resolution, which is difficult to achieve using traditional techniques. This type of structure has a number of advantages over other geometries, including high porosity (or, alternatively, low relative density), good mechanical strength, extensive pore interconnection and absence of closed cavities, and uniform or well-controlled (e.g., graded) pore distribution. The latter facilitates the controlled distribution of physical properties and pore sizes across the volume, and hence, allows to achieve the optimal material and space utilization, as well as uniform or gradient material filling/coating. 3D printing porous metals gives an opportunity to assess the intrinsic influence of pore structure, periodicity, volumetric space filling, and other factors, in the battery, water splitting, supercapacitor, or other electrodes. Porous current collectors or porous active materials, more so, are usually described as providing shorter ion diffusion distance in material and electrolyte, offer distributed electrical wiring throughout the composite, or improve electrolyte soakage, among other attributes. If these are universally true to some degree, they can, in principle, be optimized with CAD designed structures, and the relationship between specific porosity in active or substrate materials and electrochemical behaviour can be properly studied. With the advance of supercapacitors, Li-ion capacitors, and other EES system utilizing capacity and capacitance as energy storage processes, the nature of high surface area materials (all materials of the electrode) is important to be able to quantify.

Several 3D printing methods have been used to fabricate porous metallic materials, which differ by the physical processes involved in the printed layer formation. Most widely used techniques are variations of powder bed fusion (PBF), such as selective laser melting (SLM) and electron beam melting (EBM), material extrusion (ME), for example, fused deposition modelling (FDM), vat photopolymerization (VAT-P),

e.g., stereolithography (SLA) and digital light processing (DLP) [8,14,21,22,31–36\*]. PBF methods are capable of direct fabrication of fully metallic objects. ME and VAT-P techniques usually yield either polymer templates, which are further metalized, or metal–polymer composites that can be conductive and used as prepared (in this case, material brittleness issues are quite common). Alternatively, the polymer binder can be removed by post-treatment, as in the case of space holder/template-directed techniques discussed earlier in this section.

Various techniques based on *metalization of templates* (e.g., polymeric foams and lattices) have been reported. These metalization methods include *chemical vapor deposition* (CVD), *physical vapor deposition* (PVD), *electroless plating*, *electrodeposition*, and *dip-coating* [12,22,23,33,37–40]. The template can subsequently be either removed by sintering/dissolution or retained, in which case it can improve mechanical strength and maintain the integrity of the structure at the cost of the added weight and volume of usually inactive material. Among the metalization methods, electroless plating is one of the most frequently used due to its simplicity, low cost, and relatively uniform resulting metal coating. Also, no specialized, expensive equipment is required to perform this technique. Electroless plating involves sensitization and activation of the substrate surface by pre-treatment solutions followed by immersion of substrate into the plating solution containing the desired metal ion [22]. There are several published reviews, which consider the fabrication methods of metallic porous structures in more detail [5,21,41].

### Some properties of porous metallic structures in EES


Structured lattice or porous metals are a class of materials that show a wide variety of interesting properties, and these have been reviewed extensively [2,3,26,31,34,42–44]. Aside from modification to ductility, strength, flexibility, and effective optical and thermal conductivities caused by interconnected networking of a porous metal, some properties are inherently more interesting to electrochemical energy storage processes. Notably, surface activity, surface chemistry, oxidation (or oxidation resistance), corrosion (resistance), microstructure, and geometry play important active or passive roles in EES devices [14,34].

As current collectors with high nominal surface area, metal foams, such as steel, copper, and nickel foams, and other nanostructured metal oxide structures [45], as common examples, are readily used to support active materials in supercapacitor and battery electrodes. Templated metallic periodic porous surface also provides substrate for thin films for batteries, mimicking a porous metal current collector [46]. In practical

electrode preparation, metal current collector surfaces are often subject to solvent, water or acid/base exposure, and often involve a thermal treatment in cases where the material is being grown or crystallized on a surface. Often, electrode mass loading is defined by mass, without convincingly uniform coverage of a porous metal surface. This often leaves areas of porous metal that are subject to oxidation, and these oxides can, in some cases, contribute significantly to the overall electrochemical response [47]. A case in point is work by Geaney et al. who showed [48\*] how NiO formation on a nickel foam can eventually dominate the response of a Li-ion electrode when the areal mass coverage is low enough to expose oxidized Ni at the porous metal current collector surface.

Figure 2 summarises some of the salient properties of architected or 3D printed metal lattices useful for EES, and by comparison to metal foams (Figure 2b) and solid-state synthesis routes, rational design of the structure, order, and reproducibility is improved. New synthetic approaches have merged with SLA-type 3D printing to produce metal lattices on the nanoscale (Figure 2c). As metal foams tend to be used quite often in supercapacitor and pseudocapacitor research, we recommend that the activity of high surface area (non-noble) oxidizable metal foams be carefully assessed in terms of electrochemical activity in the EES device [50]. The chemistry of Ni, Cu, and other transition metals in acids and bases is now long established [51–54], but when the surface is not entirely covered, it will be active in many electrolytes under certain voltage ranges. While this effect is very sensitive in water splitting experiments for a range of metals, it is non-negligible in EES devices where very small mass loadings are used. Adding complexity and surface area to 3D porous metals could exacerbate this issue unless more chemically stable metals are used, or coating methods [55] are improved for lattice metal current collectors or electrodes. Porous metals by their nature, provide spatially inhomogeneous electric fields and locally high current densities if the lattice features dimension within the porous network are dissimilar. This may pose a problem for EES device electrode coatings that are susceptible to localized corrosion, dissolution, or for electrolyte decomposition in cases of incomplete metal coverage. Additionally, fluctuations in current collector mass can occur when oxidized, or by unexpected (electro)deposition events at exposed regions of a porous or latticed current collector. The often lauded geometrically enhanced activity of porous nanostructured materials [17,45] for various applications also occurs in other EES devices [17,56–62], and not always wanted in the case of current collector substrates. On the other hand, modification of engineered porous lattice structures may be beneficial for capacitor-based EES systems, where the actual surface area can be more precisely defined, to provide opportunities to more carefully assess the influence of

Figure 2

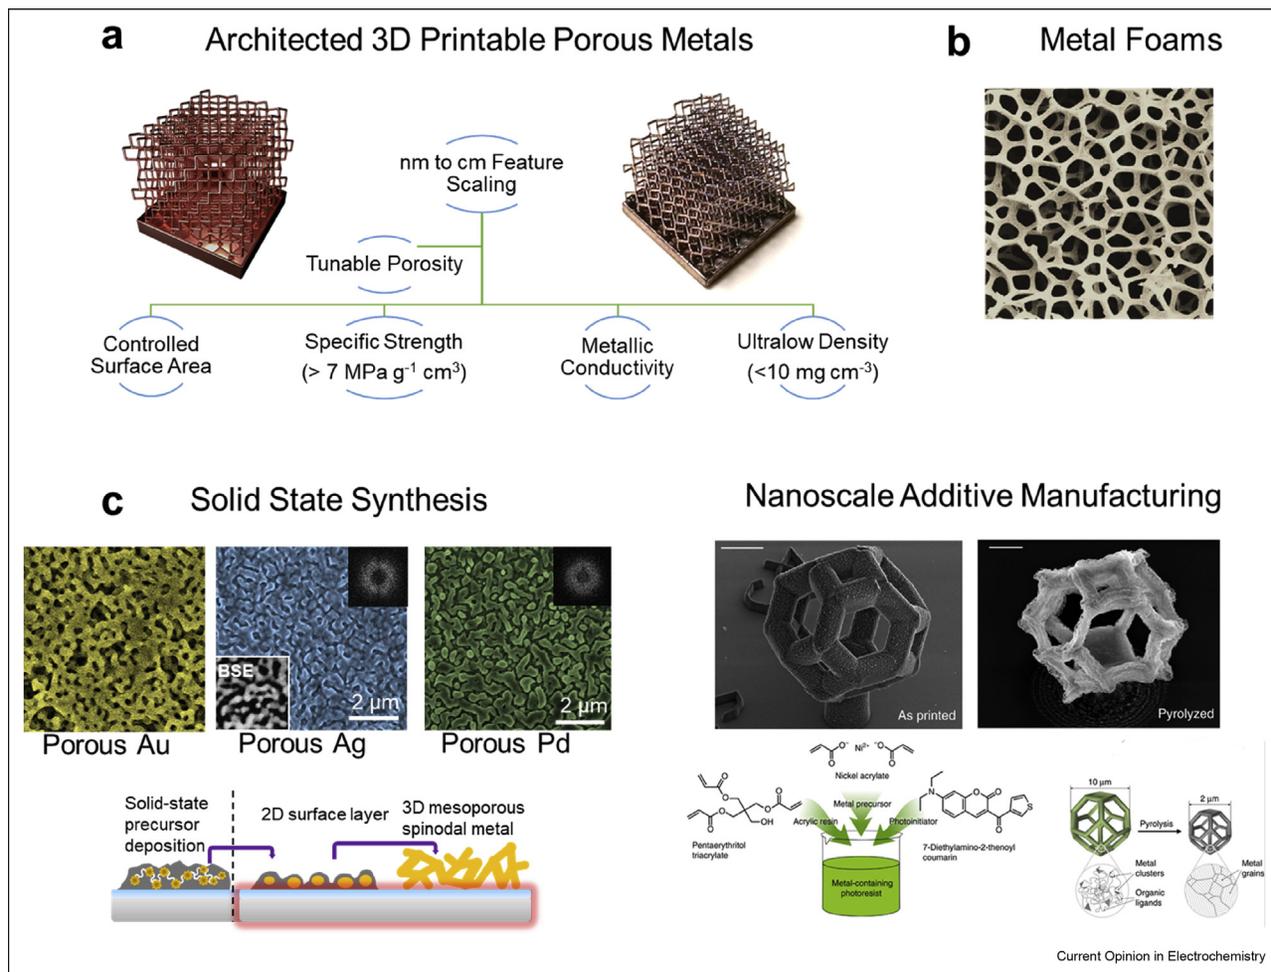

(a) Short summary of useful features of additively manufactured, architected porous metals important for EES devices. Other parameters not mentioned are assumed to be controllable by metal type, such as oxidation resistance, oxidation capability, surface reactivity, wettability, and flexibility, etc. The representative structure was designed and printed by FormLabs 2 stereolithographic 3D printer using the high temperature photoresist. (b) SEM of a typical nickel metal foam structure. (c) Summary of a solid-state precursor synthetic route to porous noble metals, such as gold, silver, and palladium, formed as a porous surface film without dealloying. Reproduced from Ref. [49] with permission from the authors. The insets are radially average FFTs of the porous metals confirming constant feature–feature separation in all directions. Nanoscale additive manufacturing using chemical precursors and photo-initiators is capable of producing printed architected metals with nanoscale features. Reproduced from Ref. [8] with permission from the authors.

other parameters (material, voltage range, scan rate, electrolyte, etc.) on the capacitance and to decouple intrinsic from geometrical enhancement in such devices [63\*]. AM grown or 3D printed reproducible porous metal lattices may prove very useful and can be constructed with flat top surfaces to ensure consistent interfacial pressure with the separator and anode, compared to spongy, nonplanar metal foams.

Finally, 3D printing not only allows CAD designed latticed porous metals optimized for a particular electrochemical cell but can also help reduce the overall mass of current collectors or electrodes. Thin-film metalization of 3D printed resin or plastic components requires much less metal than an electrode made

entirely from the metal of choice, benefitting costs, and overall cell weight. For example, ultralight lattices can be fashioned from 3D printed structures by metal deposition (physical, chemical, or vapor deposition) with subsequent removal of the underlying polymer or resin template.

Designing lattice structure and interconnectivity also ensure well defined electrical conductivity out of plane and in-plane for the electrode, and this becomes important for active battery electrode materials that are somewhat less conductive, or for electrodes that are thicker, as a case in point, in the infilling of lattice metal current collectors to minimize intrinsic resistivity of some materials for thicker electrodes[64]. Overall,

adding functional porosity has some usefulness in EES devices, and 3D printing methods can help evolve porous metallic electrode design beyond the limited range and length scales, periodicity, and order of their porosity.

## Conclusions and outlook

This opinion review looked at some primary methods for forming metallic porous structures, foams, and lattices in the context of their use in electrochemical energy storage devices. It is becoming clear that 3D printing and AM approaches in general will become very useful in the future to offset some limitations both in properties and scaled reproducibility, for porous metals in systems that are inherently very (electro)chemically active. While the extension to nonmetallic, nonpolymeric materials is already possible, rational design of periodicity and porosity in metals with structures and geometries not possible by bulk porosification or physicochemical assembly in the broadest sense might enable metallic electrode fabrication specifically designed for an EES application that was not possible before. For example, porosity, tortuosity, pore size, directionality, and surface area can be programmed, unlike the dealloying process for bimetallic systems. Electrical and mechanical characteristics can be dialed-in at the design stage for an electrode prior to fabrication based on the application need, which may be superior compared to randomly structured metal foams where pore sizes, periodicity, etc., are definitively difficult to exactly replicate and require other analytical methods to determine these properties. This applies to the electrode used in everything from batteries to water splitting, and from bioelectrochemical scaffolds to electrochemical labs-on-chip, printed based on device requirement or sensitivity to a physical structure or property. Second, some of these properties cannot be varied for certain metal foams, even when they are characterized, making 3D printing a powerful laboratory tool for electrode fabrication. We also hope that the ability to essentially create any lattice or porous metallic structure will allow the community to distinguish intrinsic (surface activity, chemical potential, oxidation state) and geometric (surface area, material fill factor, metallic truss density, etc.) parameters as contributors to charge storage in structurally and compositionally very complex electrode formulations.

## Conflict of interest statement

Nothing declared.

## Acknowledgements

This work is supported by Enterprise Ireland Commercialisation Fund as part of the European Regional Development Fund under contract no. CF-2018-0839-P. We also acknowledge funding support from the European Union's Horizon 2020 research and innovation program under grant agreement No 825114, Science Foundation Ireland (SFI) under Award no. 14/IA/2581, and from the Irish Research Council Advanced Laureate Award under grant no. IRCLA/2019/118.

## References

Papers of particular interest, published within the period of review, have been highlighted as:

- \* of special interest
- \*\* of outstanding interest

1. Sun H, Zhu J, Baumann D, Peng L, Xu Y, Shakir I, Huang Y, \* Duan X: **Hierarchical 3D electrodes for electrochemical energy storage**. *Nature Reviews Materials* 2019, **4**:45–60. Useful review article that puts hierarchical electrodes, by several techniques, including printing-based methods, into context and compares their usefulness in electrochemical energy storage systems. It provides a viewpoint on structured materials of many different compositions, and in particular, the importance of developing continuous conductive networks within active electrode materials that are very thick.
2. Pikul JH, Long JW: **Architected materials for advanced electrochemical systems**. *MRS Bull* 2019, **44**:789–795.
3. Pang Y, Cao Y, Chu Y, Liu M, Snyder K, MacKenzie D, Cao C: **Additive manufacturing of batteries**. *Adv Funct Mater* 2019: 1906244. n/a.
4. Braun PV, Cook JB: **Deterministic design of chemistry and mesostructure in Li-ion battery electrodes**. *ACS Nano* 2018, **12**:3060–3064.
5. Yeo SJ, Oh MJ, Yoo PJ: **Structurally controlled cellular architectures for high-performance ultra-lightweight materials**. \* *Adv Mater* 2019, **31**:1803670. This work shows the impact of controlling cellular architecture on the physical properties of lightweight materials and is useful reading for electrochemists wishing to add material engineering methods, and the knowledge behind it, to EES-based systems.
6. Sutygina A, Betke U, Scheffler M: **Open-cell aluminum foams by the sponge replication technique**. *Materials* 2019, **12**:3840.
7. Mines R: *Theory, simulation, analysis and synthesis for metallic microlattice structures, metallic microlattice structures: manufacture, materials and application*. Cham: Springer International Publishing; 2019:49–65.
8. Vyatskikh A, Delalande S, Kudo A, Zhang X, Portela CM, \*\* Greer JR: **Additive manufacturing of 3D nano-architected metals**. *Nat Commun* 2018, **9**:593. Very useful paper, in our opinion, showcasing additive manufacturing of metals with defined architecture with ~100 nm resolution in feature size. It shows a viable option for printable nanoscale architected metals.
9. Tian X, Jin J, Yuan S, Chua CK, Tor SB, Zhou K: **Emerging 3D-printed electrochemical energy storage devices: a critical review**. *Adv. Energy Mater.* 2017, **7**:1700127.
10. Wang C, Wang H, Matios E, Hu X, Li W: **A chemically engineered porous copper matrix with cylindrical core-shell skeleton as a stable host for metallic sodium anodes**. *Adv Funct Mater* 2018, **28**:1802282.
11. Zekoll S, Marriner-Edwards C, Ola Hekselman AK, Kasemchainan J, Kuss C, Armstrong DEJ, Cai D, Wallace RJ, Richter FH, Thijssen JHJ, Bruce PG: **Hybrid electrolytes with 3D bicontinuous ordered ceramic and polymer micro-channels for all-solid-state batteries**. *Energy Environ Sci* 2018, **11**:185–201.
12. Zhu H-W, Ge J, Peng Y-C, Zhao H-Y, Shi L-A, Yu S-H: **Dip-coating processed sponge-based electrodes for stretchable Zn-MnO<sub>2</sub> batteries**. *Nano Research* 2018, **11**: 1554–1562.
13. Song T, Yan M, Qian M: **The enabling role of dealloying in the creation of specific hierarchical porous metal structures—a review**. *Corrosion Sci* 2018, **134**:78–98.
14. Saleh MS, Li J, Park J, Panat R: **3D printed hierarchically-porous microlattice electrode materials for exceptionally high specific capacity and areal capacity lithium ion batteries**. *Additive Manufacturing* 2018, **23**:70–78.
15. Osiak M, Geaney H, Armstrong E, O'Dwyer C: **Structuring materials for lithium-ion batteries: advancements in**

- nanomaterial structure, composition, and defined assembly on cell performance.** *J Mater Chem A* 2014, **2**:9433–9460.
16. Vu A, Qian Y, Stein A: **Porous electrode materials for lithium-ion batteries – how to prepare them and what makes them special.** *Advanced Energy Materials* 2012, **2**:1056–1085.
  17. Long JW, Dunn B, Rolison DR, White HS: **Three-dimensional battery architectures.** *Chem Rev* 2004, **104**:4463–4492.
  18. Al-Ketan O, Rowshan R, Abu Al-Rub RK: **Topology-mechanical property relationship of 3D printed strut, skeletal, and sheet based periodic metallic cellular materials.** *Additive Manufacturing* 2018, **19**:167–183.
  19. Rashed MG, Ashraf M, Hazell PJ: **Manufacturing issues and the resulting complexity in modeling of additively manufactured metallic microlattices.** *Appl Mech Mater* 2017, **853**:394–398.
  20. Schaedler TA, Carter WB: **Architected cellular materials.** *Annu Rev Mater Res* 2016, **46**:187–210.
- We think this is an important review for electrochemistry and battery researchers using 3D printing or additive manufacturing, so that structural aspects of latticed or porous metal (or other) structures can be appreciated from an engineering standpoint, and why the architecture of microlattices and truss-based structures is important and useful.
21. Rashed MG, Ashraf M, Mines RAW, Hazell PJ: **Metallic microlattice materials: a current state of the art on manufacturing, mechanical properties and applications.** *Mater Des* 2016, **95**:518–533.
  22. Su X, Li X, Ong CYA, Heng TS, Wang Y, Peng E, Ding J: **Metalization of 3D printed polymers and their application as a fully functional water-splitting system.** *Advanced Science* 2019, **6**:1801670.
  23. Schaedler TA, Jacobsen AJ, Torrents A, Sorensen AE, Lian J, Greer JR, Valdevit L, Carter WB: **Ultralight metallic microlattices.** *Science* 2011, **334**:962.
- This paper showed how photolithographically printable resins could be electrolessly coated in metal (Nickel in this case) to form ultralight metallic microlattices once the template material was removed. While this work showed their improved mechanical attributes, it demonstrated a way to create electrodes for many electrochemistry-based studies.
24. Ashby MF: **The properties of foams and lattices.** *Phil Trans Math Phys Eng Sci* 2006, **364**:15–30.
  25. Wettergreen MA, Bucklen BS, Starly B, Yuksel E, Sun W, Liebschner MAK: **Creation of a unit block library of architectures for use in assembled scaffold engineering.** *Comput Aided Des* 2005, **37**:1141–1149.
  26. Singh S, Bhatnagar N: **A survey of fabrication and application of metallic foams (1925–2017).** *J Porous Mater* 2018, **25**:537–554.
- This review article provides a comprehensive summary of several decades of metallic foam fabrication, providing useful background history to both production of porous metals and their applications over the years.
27. Lu Z, Li C, Han J, Zhang F, Liu P, Wang H, Wang Z, Cheng C, Chen L, Hirata A, Fujita T, Erlebacher J, Chen M: **Three-dimensional bicontinuous nanoporous materials by vapor phase dealloying.** *Nat Commun* 2018, **9**:276.
  28. Erlebacher J, Aziz MJ, Karma A, Dimitrov N, Sieradzki K: **Evolution of nanoporosity in dealloying.** *Nature* 2001, **410**:450–453.
  29. Xue Y, Wang X, Wang W, Zhong X, Han F: **Compressive property of Al-based auxetic lattice structures fabricated by 3-D printing combined with investment casting.** *Mater Sci Eng, A* 2018, **722**:255–262.
  30. Gulzar U, Glynn C, O'Dwyer C: **Additive manufacturing for energy storage: methods, designs and materials selection for customizable 3D printed batteries and supercapacitors.** *arXiv*; 2020. 1912.04755.
  31. Mahmoud D, Elbestawi MA, Yu B: **Process–structure–property relationships in selective laser melting of porosity graded gyroids.** *J Manuf Syst* 2019, **13**.
  32. Park S-I, Rosen DW, Choi S-k, Duty CE: **Effective mechanical properties of lattice material fabricated by material extrusion additive manufacturing.** *Additive Manufacturing* 2014, **1**–4:12–23.
  33. Xue J, Gao L, Hu X, Cao K, Zhou W, Wang W, Lu Y: **Stereolithographic 3D printing-based hierarchically cellular lattices for high-performance quasi-solid supercapacitor.** *Nano-Micro Lett* 2019, **11**:46.
  34. Park SH, Kaur M, Yun D, Kim WS: **Hierarchically designed electron paths in 3D printed energy storage devices.** *Langmuir* 2018, **34**:10897–10904.
  35. Liu F, Zhang DZ, Zhang P, Zhao M, Jafar S: **Mechanical properties of optimized diamond lattice structure for bone scaffolds fabricated via selective laser melting.** *Materials* 2018, **11**:374.
  36. Egorov V, Gulzar U, Zhang Y, Breen S, O'Dwyer C: **Evolution of 3D printing methods and materials for electrochemical energy storage.** *arXiv* 2020, 04400. 1912.
- This work provides a detailed perspective on the relationship between 3D printing feed materials, their properties, and advances made in structured printed materials for Li-ion batteries and supercapacitors, which can be extended to metallic printable structures.
37. Juarez T, Schroer A, Schwaiger R, Hodge AM: **Evaluating sputter deposited metal coatings on 3D printed polymer micro-truss structures.** *Mater Des* 2018, **140**:442–450.
  38. Song J, Chen Y, Cao K, Lu Y, Xin JH, Tao X: **Fully controllable design and fabrication of three-dimensional lattice supercapacitors.** *ACS Appl Mater Interfaces* 2018, **10**:39839–39850.
  39. Cohen E, Menkin S, Lifshits M, Kamir Y, Gladkikh A, Kosa G, Golodnitsky D: **Novel rechargeable 3D-Microbatteries on 3D-printed-polymer substrates: feasibility study.** *Electrochim Acta* 2018, **265**:690–701.
  40. Xu C, Gallant BM, Wunderlich PU, Lohmann T, Greer JR: **Three-dimensional Au microlattices as positive electrodes for Li–O<sub>2</sub> batteries.** *ACS Nano* 2015, **9**:5876–5883.
  41. Zhao B, Gain AK, Ding W, Zhang L, Li X, Fu Y: **A review on metallic porous materials: pore formation, mechanical properties, and their applications.** *Int J Adv Manuf Technol* 2018, **95**:2641–2659.
  42. Ren X, Das R, Tran P, Ngo TD, Xie YM: **Auxetic metamaterials and structures: a review.** *Smart Mater Struct* 2018, **27**:023001.
  43. Yu X, Zhou J, Liang H, Jiang Z, Wu L: **Mechanical metamaterials associated with stiffness, rigidity and compressibility: a brief review.** *Prog Mater Sci* 2018, **94**:114–173.
  44. Gu H, Li S, Pavier M, Attallah MM, Paraskevoulakos C, Shterenlikht A: **Fracture of three-dimensional lattices manufactured by selective laser melting.** *Int J Solid Struct* 2019, **180**–181:147–159.
  45. Taberna PL, Mitra S, Poizot P, Simon P, Tarascon JM: **High rate capabilities Fe<sub>3</sub>O<sub>4</sub>-based Cu nano-architected electrodes for lithium-ion battery applications.** *Nat Mater* 2006, **5**:567–573.
  46. Zhang H, Braun PV: **Three-dimensional metal scaffold supported bicontinuous silicon battery anodes.** *Nano Lett* 2012, **12**:2778–2783.
  47. Needham SA, Wang GX, Liu HK: **Synthesis of NiO nanotubes for use as negative electrodes in lithium ion batteries.** *J Power Sources* 2006, **159**:254–257.
  48. Geaney H, McNulty D, O'Connell J, Holmes JD, O'Dwyer C: **Assessing charge contribution from thermally treated Ni foam as current collectors for Li-ion batteries.** *J Electrochem Soc* 2016, **163**:A1805–A1811.
- This paper provided evidence of NiO contribution to specific capacity in Li-ion batteries when Ni foams were used as high surface area current collectors, onto which hydrothermally grown active materials were formed. Oxidized metal foams are certainly electrochemically active and significantly contribute to overall capacity when low mass loadings are used.
49. Valenzuela CD, Carriedo GA, Valenzuela ML, Zúñiga L, O'Dwyer C: **Solid state pathways to complex shape evolution**

- and tunable porosity during metallic crystal growth. *Sci Rep* 2013, **3**:2642.
50. Park JC, Kim J, Kwon H, Song H: **Gram-scale synthesis of Cu<sub>2</sub>O nanocubes and subsequent oxidation to CuO hollow nanostructures for lithium-ion battery anode materials.** *Adv Mater* 2009, **21**:803–807.
  51. Peterson NL: **Impurity diffusion in transition-metal oxides.** *Solid State Ionics* 1984, **12**:201–215.
  52. Tuomi D: **The forming process in nickel positive electrodes.** *J Electrochem Soc* 1965, **112**:1–12.
  53. Armstrong RD, Wang H: **Behaviour of nickel hydroxide electrodes after prolonged potential float.** *Electrochim Acta* 1991, **36**:759–762.
  54. Kalu EE, Nwoga TT, Srinivasan V, Weidner JW: **Cyclic voltammetric studies of the effects of time and temperature on the capacitance of electrochemically deposited nickel hydroxide.** *J Power Sources* 2001, **92**:163–167.
  55. Sudagar J, Lian J, Sha W: **Electroless nickel, alloy, composite and nano coatings – a critical review.** *J Alloys Compd* 2013, **571**:183–204.
  56. McNulty D, Lonergan A, O'Hanlon S, O'Dwyer C: **3D open-worked inverse opal TiO<sub>2</sub> and GeO<sub>2</sub> materials for long life, high capacity Li-ion battery anodes.** *Solid State Ionics* 2018, **314**:195–203.
  57. McNulty D, Carroll E, O'Dwyer C: **Rutile TiO<sub>2</sub> inverse opal anodes for Li-ion batteries with long cycle life, high-rate capability and high structural stability.** *Adv. Energy Mater.* 2017, **7**:1602291.
  58. Collins G, Armstrong E, McNulty D, O'Hanlon S, Geaney H, O'Dwyer C: **2D and 3D photonic crystal materials for photocatalysis and electrochemical energy storage and conversion.** *Sci Technol Adv Mater* 2016, **17**:563–582.
  59. Armstrong E, O'Dwyer C: **Artificial opal photonic crystals and inverse opal structures - fundamentals and applications from optics to energy storage.** *J Mater Chem C* 2015, **3**:6109–6143.
  60. Armstrong E, McNulty D, Geaney H, O'Dwyer C: **Electro-deposited structurally stable V<sub>2</sub>O<sub>5</sub> inverse opal networks as high performance thin film lithium batteries.** *ACS Appl Mater Interfaces* 2015, **7**:27006–27015.
  61. Lytle JC: **Inverse opal nanoarchitectures as lithium-ion battery materials.** In *Nanotechnology for lithium-ion batteries*. Edited by Abu-Lebdeh Y, Davidson I, Springer Science+Business Media LLC; 2013.
  62. Ergang NS, Lytle JC, Lee KT, Oh SM, Smyrl WH, Stein A: **Photonic crystal structures as a basis for a three-dimensionally interpenetrating electrochemical-cell system.** *Adv Mater* 2006, **18**:1750–1753.
  63. Gogotsi Y, Simon P: **True performance metrics in electrochemical energy storage.** *Science* 2011, **334**:917.  
 This perspective tackles an important issue of performance in electrochemical capacitors (and by extension, Li-ion batteries), where contributory activity often linked with performance can stem from the surface area of active electrode components, and importantly the effect of porosity and other parameters in the calculation of performance metrics for EES devices.
  64. Kuang Y, Chen C, Kirsch D, Hu L: **Thick electrode batteries: principles, opportunities, and challenges.** *Ad Energy Mater* 2019, **9**:1901457.