CORA Cork Open Research Archive
Cartlann Taighde Oscailte Chorcaí

Title	Enhanced photoelectrochemical water splitting with doped transition metal dichalcogenide nanofilms
Authors	Ilhan, Cansu;Nedrygailov, Ievgen;Smith, Ross;Lin, Jun;Kent, Christopher;Povey, Ian M.;O'Dwyer, Colm;Lombardo, Salvatore;Nicotra, Giuseppe;Hurley, Paul K.;Morris, Mick;Fitzpatrick, Dara;Holmes, Justin D.;Monaghan, Scott
Publication date	2023-11-01
Original Citation	Ilhan, C., Nedrygailov, I., Smith, R., Lin, J., Kent, C., Povey, I. M., O'Dwyer, C., Lombardo, S., Nicotra, G., Hurley, P. K., Morris, M., Fitzpatrick, D., Holmes, J. D. and Monaghan, S. (2023) 'Enhanced photoelectrochemical water splitting with doped transition metal dichalcogenide nanofilms', 2023 Materials Research Society Fall Meeting & Exhibit, 26 November - 1 December, Boston, Massachusetts, EN06.07.03. doi: https://doi.org/10.5281/zenodo.10683980
Type of publication	Conference item
Link to publisher's version	https://www.mrs.org/meetings-events/fall-meetings-exhibits/2023-mrs-fall-meeting/symposium-sessions/presentations/detail/2023_mrs_fall_meeting/2023_mrs_fall_meeting-3955601 - 10.5281/zenodo.10683980
Rights	© 2023, the Authors.
Download date	2026-11-07 04:16:16
Item downloaded from	https://hdl.handle.net/10468/15426

UCC
University College Cork, Ireland
Coláiste na hOllscoile Corcaigh

Free Hydro Cells

Funded by the European Union

Title **Enhanced photoelectrochemical water splitting with doped transition metal dichalcogenide nanofilms**

Names Cansu Ilhan[4], Ievgen Nedrygailov[2,3,4], Ross Smith[4], Jun Lin[1], Christopher Kent[2,5], Ian M. Povey[1,2], Colm O'Dwyer[2,4], Salvatore Lombardo[6], Giuseppe Nicotra[6], Paul K. Hurley[1,2,4], Mick Morris[4], Dara Fitzpatrick[5], Justin D. Holmes[2,3,4] and Scott Monaghan[1,2,3,4]

Affiliations University College Cork (Tyndall National Institute[1], School of Chemistry[2], Environmental Research Institute[3], incorporating the AMBER Research Centre Ireland[4], UCC/CRANN/TCD), SME BARDS[5], CNR-IMM[6]

Event/Date MRS Meeting, Boston, USA, 26 November - 1 December 2023

AMBER Advancing Materials for Impact · UCC University College Cork, Ireland Coláiste na hOllscoile Corcaigh · RWTH AACHEN UNIVERSITY · Consiglio Nazionale delle Ricerche · cea · AMO · BARDS A Sound Approach to Chemical Analysis · UCC ACADEMY

Funded by the European Union

Talk Outline


- Introduction
- Materials' growth and formation
- Structural and physical characterisation
- Hall-effect analysis
- Photoelectric and Photoelectrochemical characterisation
- Conclusions, Future Work and Acknowledgements

Talk Outline

- Introduction
- Materials' growth and formation
- Structural and physical characterisation
- Hall-effect analysis
- Photoelectric and Photoelectrochemical characterisation
- Conclusions, Future Work and Acknowledgements

Photoelectrochemical Water Splitting

Single Layer Photoelectrochemical devices

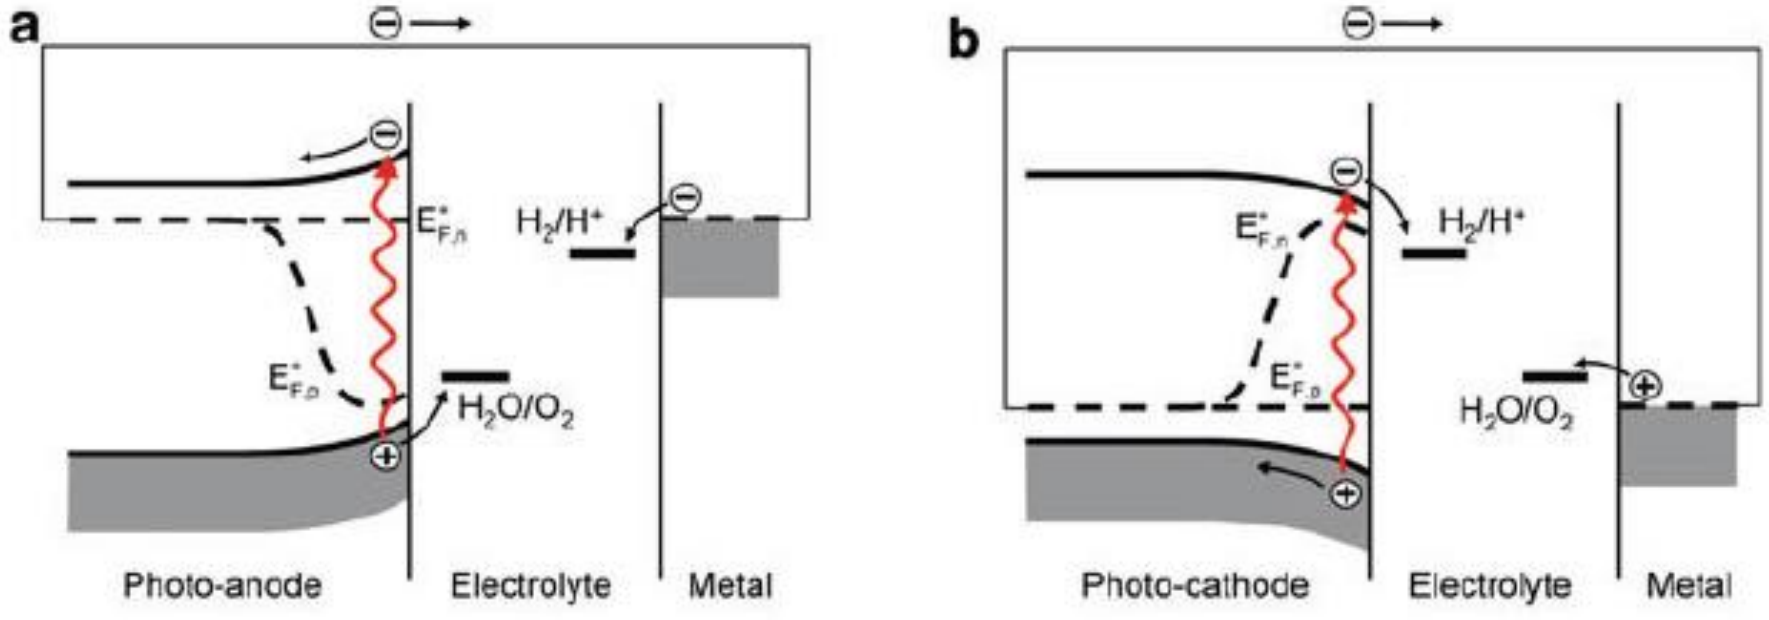


Standard single semiconductor devices based on a (a) Photo-anode or (b) Photo-cathode.

R. van de Krol , Photoelectrochemical Hydrogen Production (2012)

- Our work focuses on creation and characterising of novel and earth abundant electrodes for photo-anode [n-type] and photo-cathode [p-type] semiconductors to produce hydrogen.


Introduction to TMDs

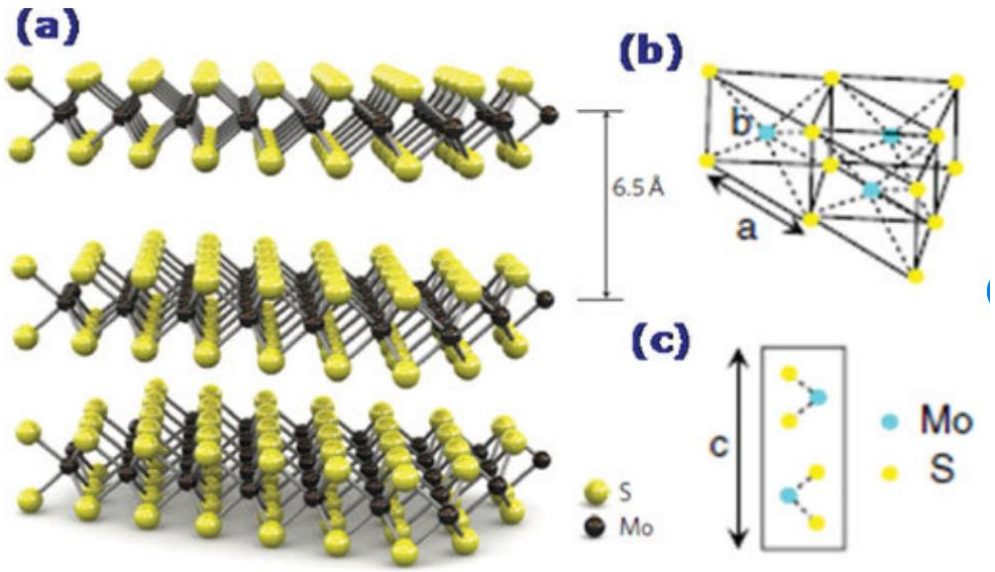

MX_2 (M=Mo, W X=S, Se)

- Earth abundant composition
- 1.1-1.6 eV bulk E_g
- High absorption coefficient
- Structure stability under illumination

Chhowalla *et al,*. Nature Chemistry vol.5, p.263 (2013)

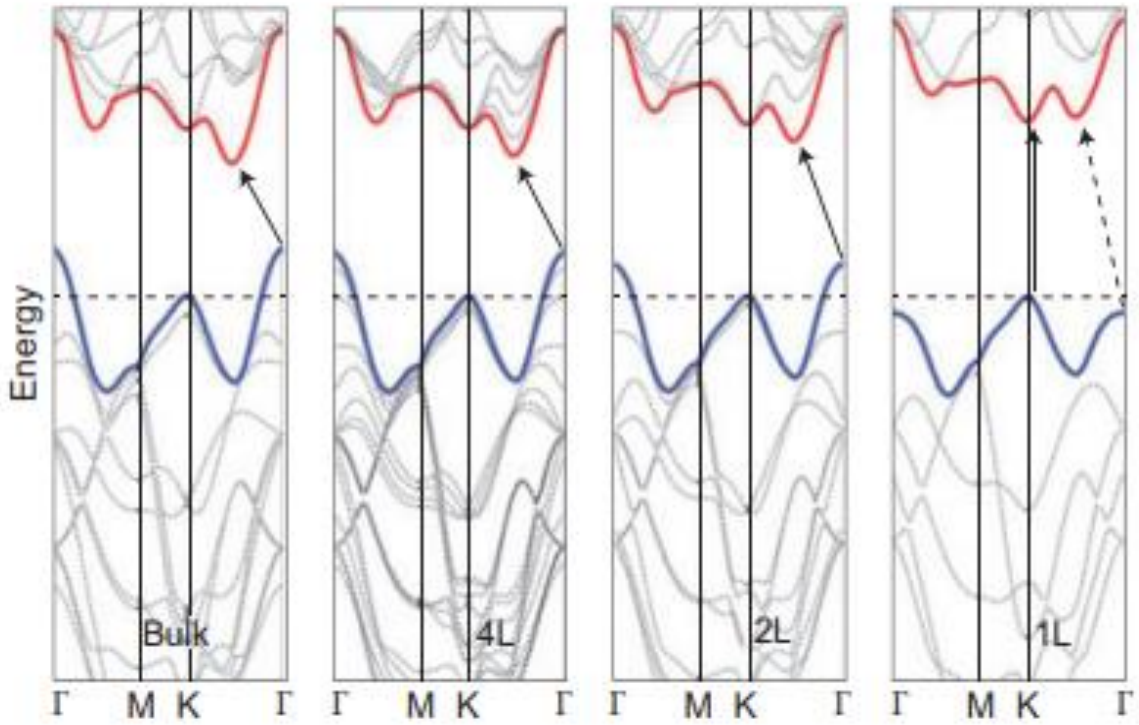

Energy dispersion in bulk MoS_2

Splendiani *et al,*. Nano Lett vol.10, p.1271 (2010)

Talk Outline

- Introduction
- Materials' growth and formation
- Structural and physical characterisation
- Hall-effect analysis
- Photoelectric and Photoelectrochemical characterisation
- Conclusions, Future Work and Acknowledgements

Transition Metal Dichalcogenide Film Growth

FreeHydroCells


Magnetron Sputtering [Co-sputtering]



Powers *et al,.* Journal of Materials Research vol 35, p.1531 (2020)

1

Thermally Assisted Conversion (TAC)

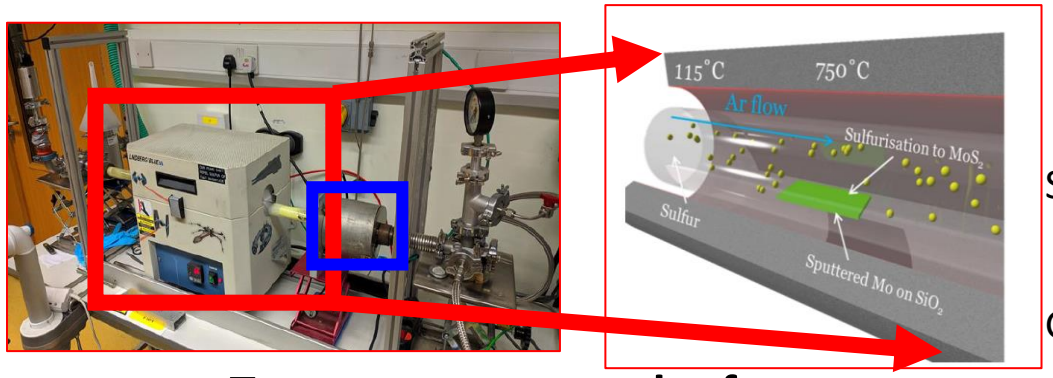

Sulphur Furnace

Growth Furnace


Two zone quartz tube furnace

Gatensby *et al,.* Applied Surface Science vol.297, p.139 (2014)

2



3

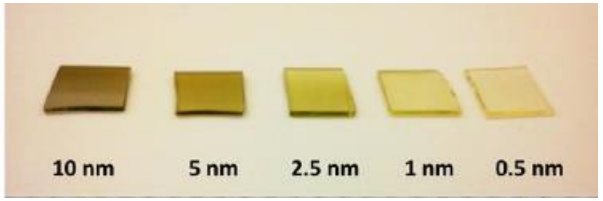

PVD system for TiO_2 capping layer deposition

Wang *et al,.* Chemical Engineering Journal vol.381, 122605 (2020)

Different thicknesses of films on quartz

Hallam *et al,.* Appl. Phys. Lett. 111, 203101 (2017)

This work includes doping of TMD

42 Mo Molybdenum 95.95 + 75 Re Rhenium 186.21

74 W Tungsten 183.84 + 41 Nb Niobium 92.906

AMBER Advancing Materials for Impact · UCC University College Cork, Ireland Coláiste na hOllscoile Corcaigh · RWTH AACHEN UNIVERSITY · Consiglio Nazionale delle Ricerche · cea · AMO · BARDS A Sound Approach to Chemical Analysis · UCC ACADEMY


Talk Outline

- Introduction and methods
- Materials' growth and formation
- Structural and physical characterisation
- Hall-effect analysis
- Photoelectric and Photoelectrochemical characterisation
- Conclusions, Future Work and Acknowledgements

Structural and Physical Characterisation I

- The methods used to assess TMDs in the presentation

1 X-Ray Reflectivity (Before and after Conversion)

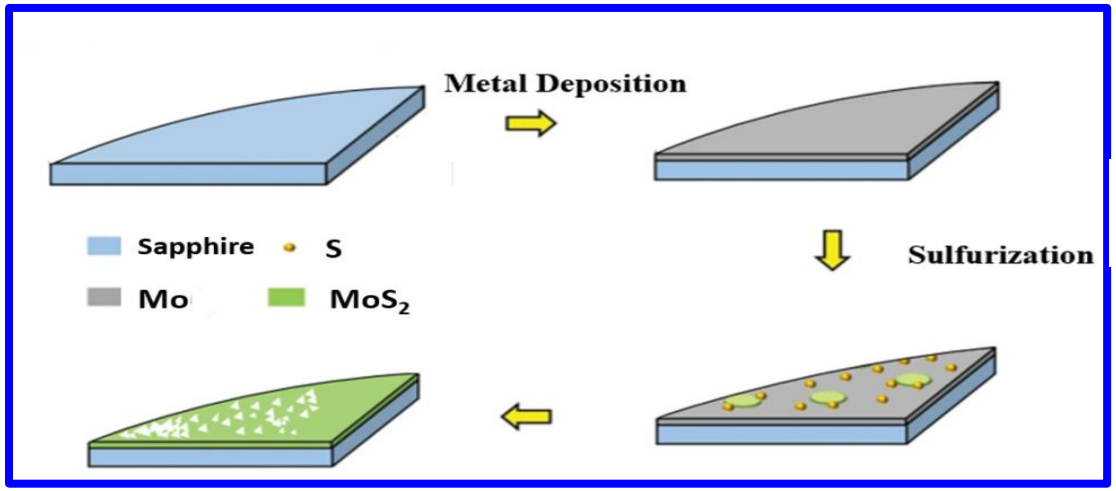

Furnace Process [Conversion]

2 Raman Spectroscopy

3 X-Ray Diffraction

Structural and Physical Characterisation I

XRR : Thickness Analysis

The basic principle is that when X-rays strike a surface, they are partially reflected, and the amount of reflection depends on the angle of incidence and the properties of the material.

WS_2 Samples (p –type targeted)


Samples	Before conversion	After conversion	TiO_2 Capping layer
0% Nb doped WS_2	**9-13 nm**	**21-25.5 nm**	**7 – 11 nm**
2% Nb doped WS_2	**9-13 nm**	**21-25.5 nm**	**7 – 11 nm**
4% Nb doped WS_2	**9-13 nm**	**21-25.5 nm**	**7 – 11 nm**

MoS_2 Samples (n-type targeted)


Samples	Before conversion	After conversion	TiO_2 Capping layer
0% Re doped MoS_2	**15-20 nm**	**44-48 nm**	**7 – 11 nm**
5% Re doped MoS_2	**15-20 nm**	**40-48 nm**	**7 – 11 nm**
9% Re doped MoS_2	15-20 nm	30-40 nm	**7 – 11 nm**
18% Re doped MoS_2	**13-17 nm**	**26-35 nm**	**7 – 11 nm**

Structural and Physical Characterisation II

Raman Spectroscopy

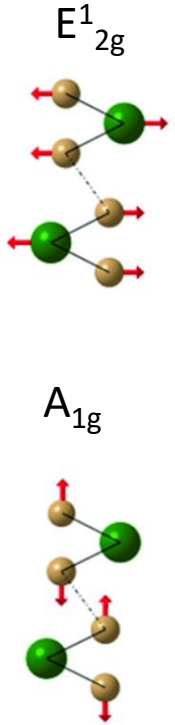


WS_2 Samples

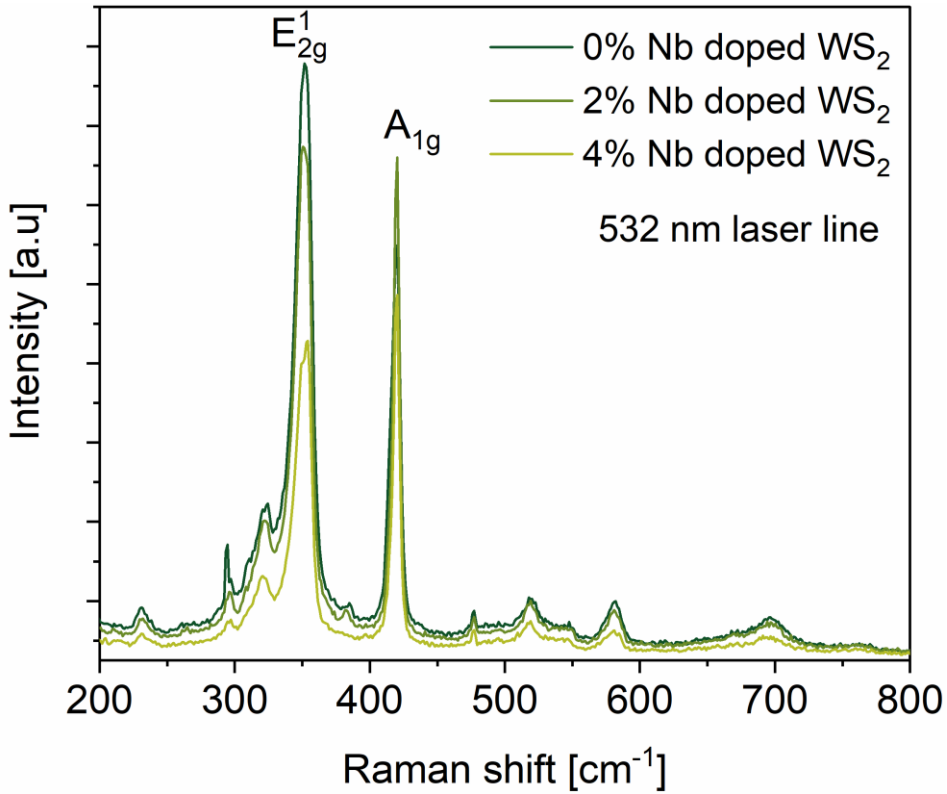

Igbal *et al*,. Microelectronic Engineering. 219, 111152 (2020)

Yang *et al*,. Research. 9862483, 111152 (2021)

MoS_2 Samples

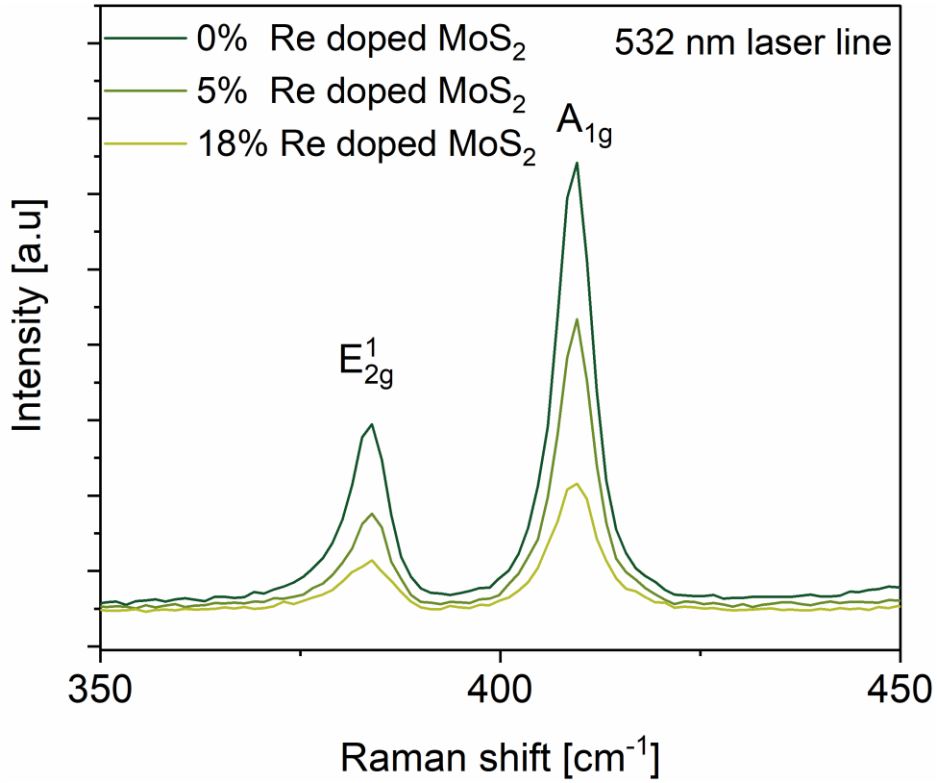


Hallam *et al*,. Appl. Phys. Lett. 111, 203101 (2017)

Structural and Physical Characterisation III


X-Ray Diffraction

WS_2 Samples

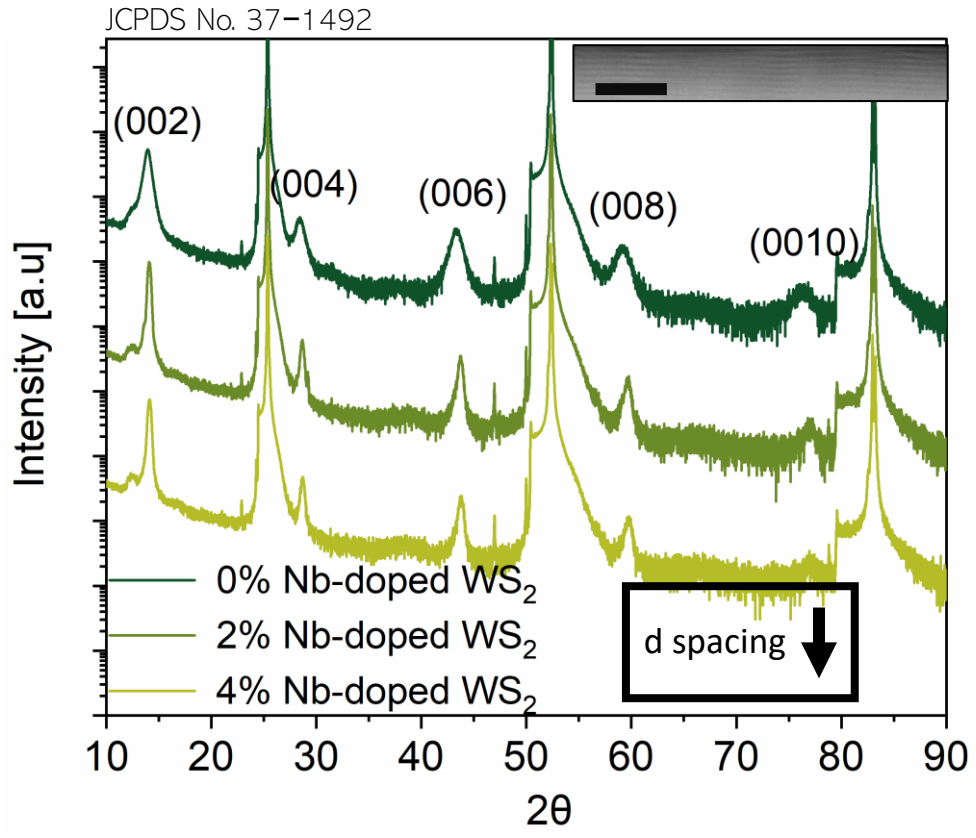

Pu *et al*,. Flat Chem. 29, 100278 (2021)

MoS_2 Samples

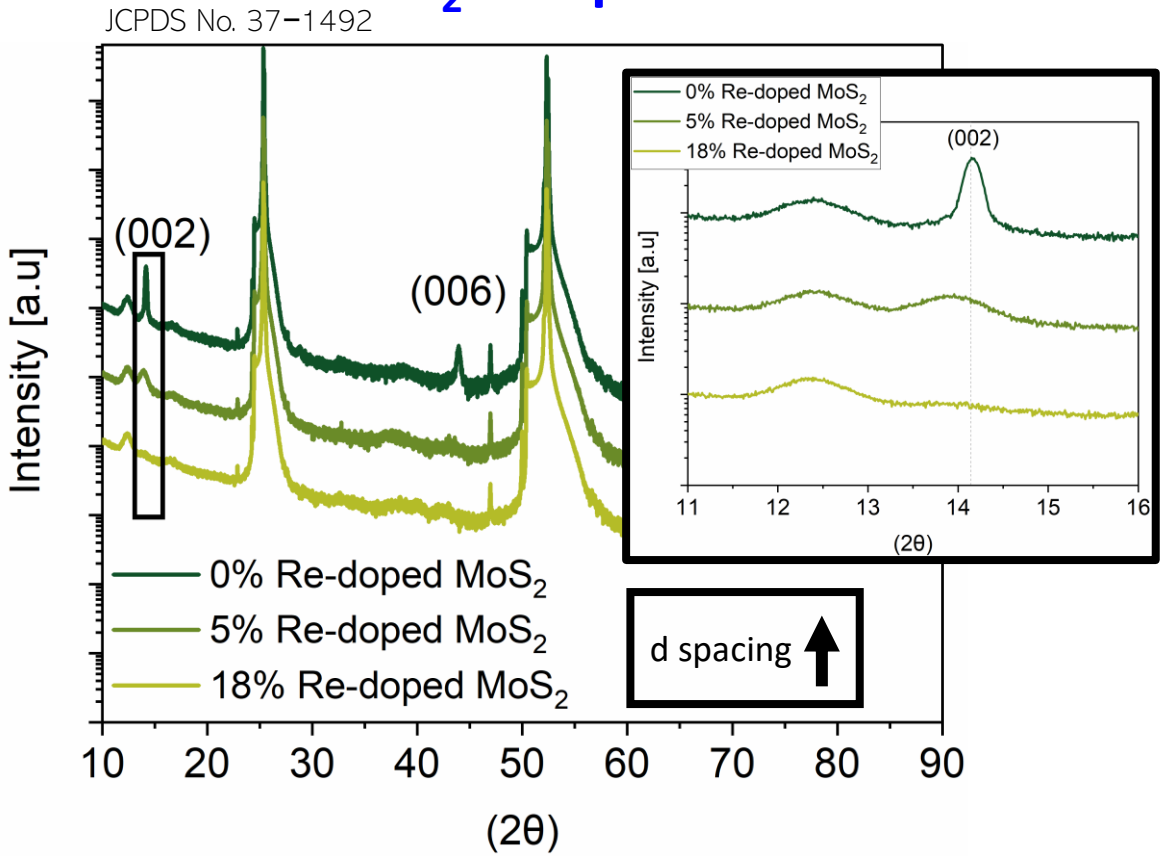


Qin *et al*,. Scientific Reports. 4, 7582 (2014)


Talk Outline

- Introduction
- Materials' growth and formation
- Structural and physical characterisation
- Hall-effect analysis
- Photoelectric and Photoelectrochemical analysis
- Conclusions, Future Work and Acknowledgements

Hall Effect Analysis

Doping Study

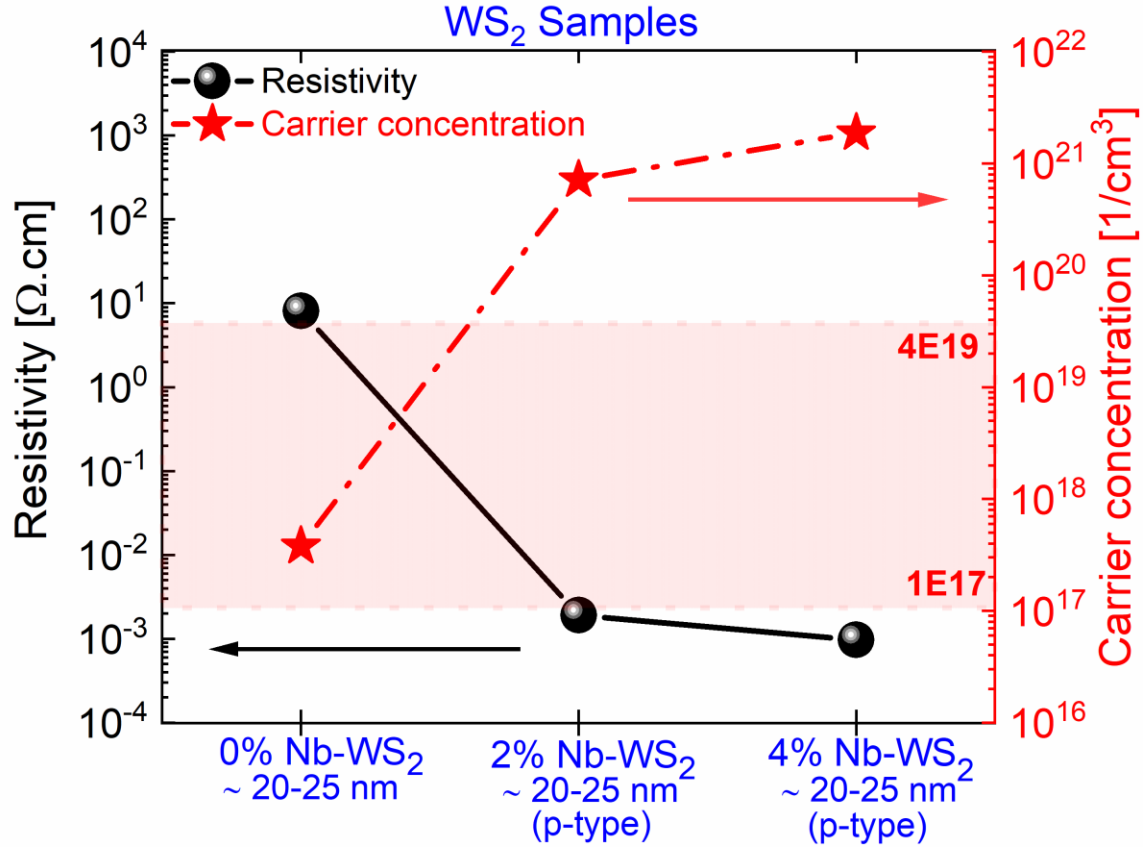


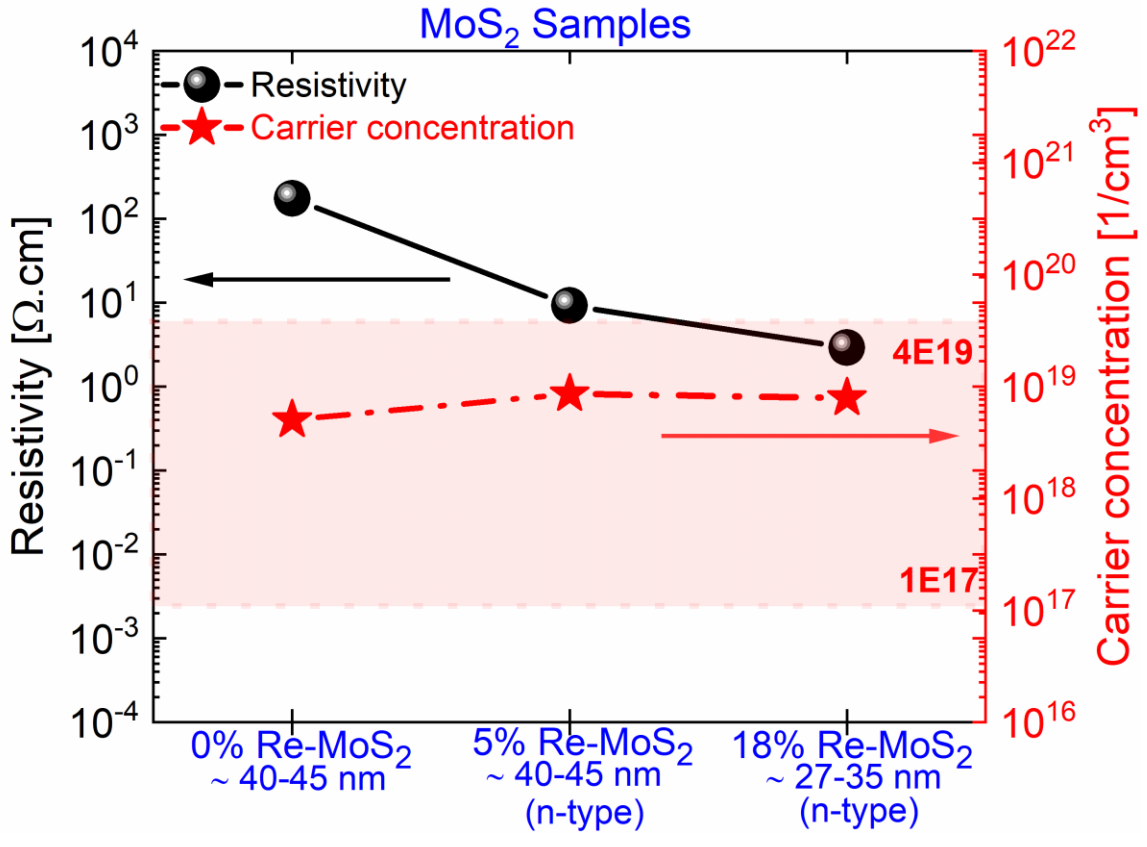

Talk Outline

- Introduction
- Materials' growth and formation
- Structural and physical characterisation
- Hall-effect analysis
- Photoelectric and photoelectrochemical analysis
- Conclusions, Future Work and Acknowledgements

Photoelectric and photoelectrochemical analysis

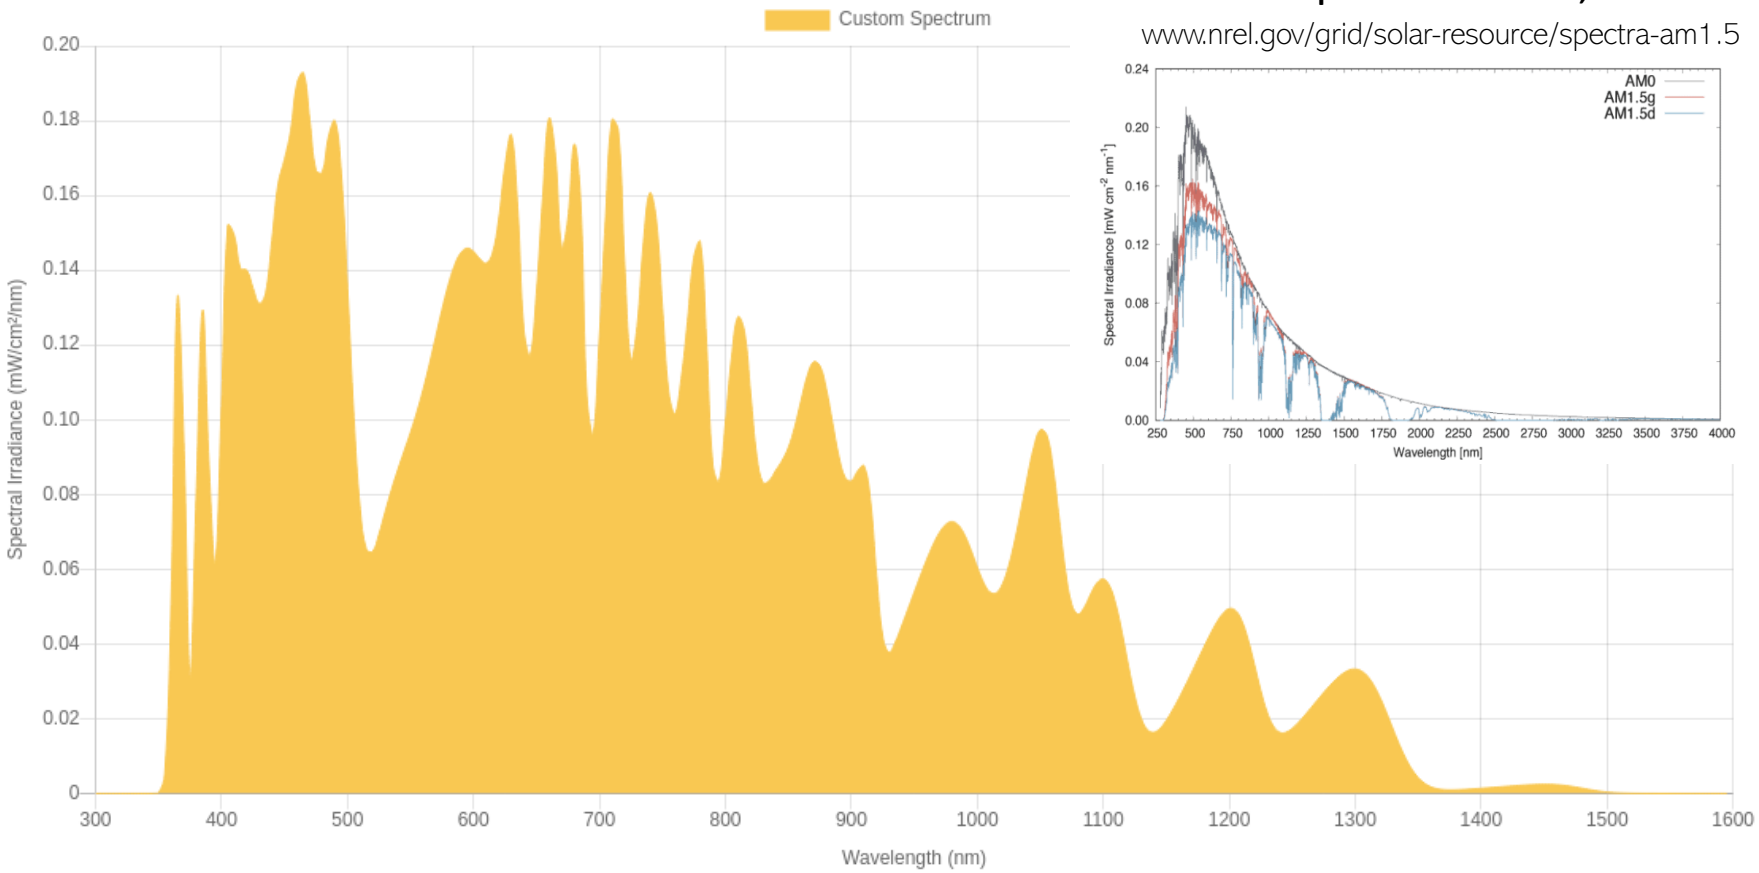

Standard spectrum of AM1.5G, 1.1 suns

www.nrel.gov/grid/solar-resource/spectra-am1.5

The spectrum of AM1.5G, 1.1 suns used in this work

www.g2voptics.com/solar-simulation

- Light on:

32 LEDs

Total radiance is 88.3mW/cm^2

Spectra: 361 - 1556 nm

AM1.5G, 1.1 Suns
(Effectively 0.9 x 1.1 Suns = 0.99 Suns)

- Light off:


Dark chamber.

- Temperature in both case:
  20.4°C to 23.5°C

Photo response assessment of TMD films on Si substrate

FreeHydroCells

0% Nb-WS_2

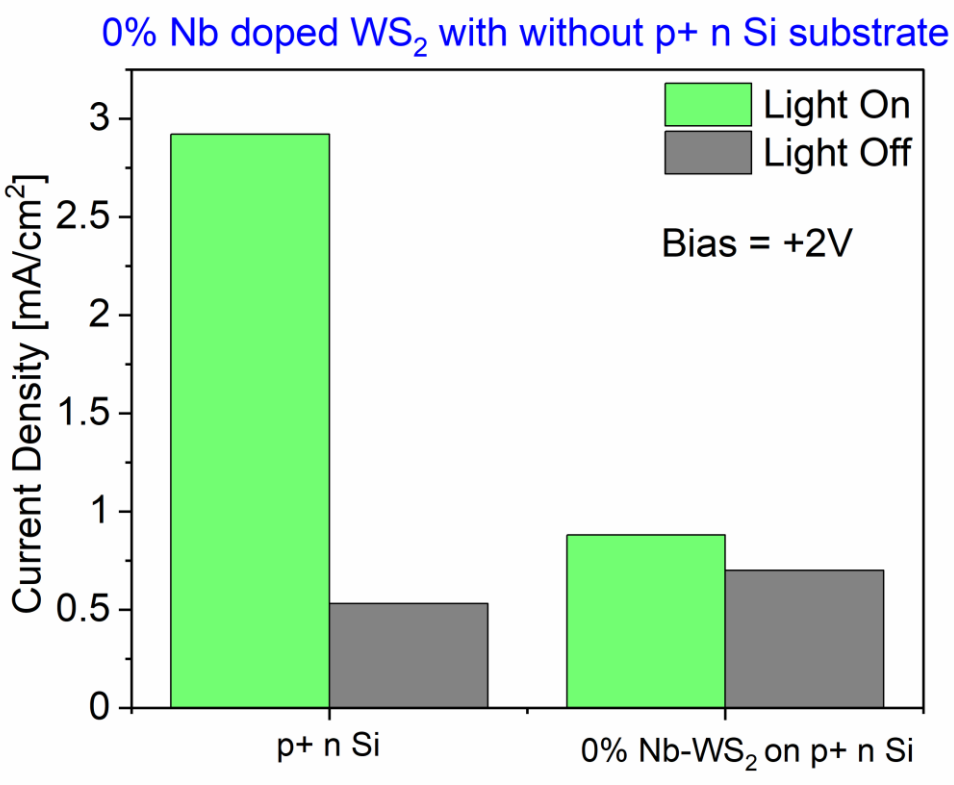

18% Re-MoS_2


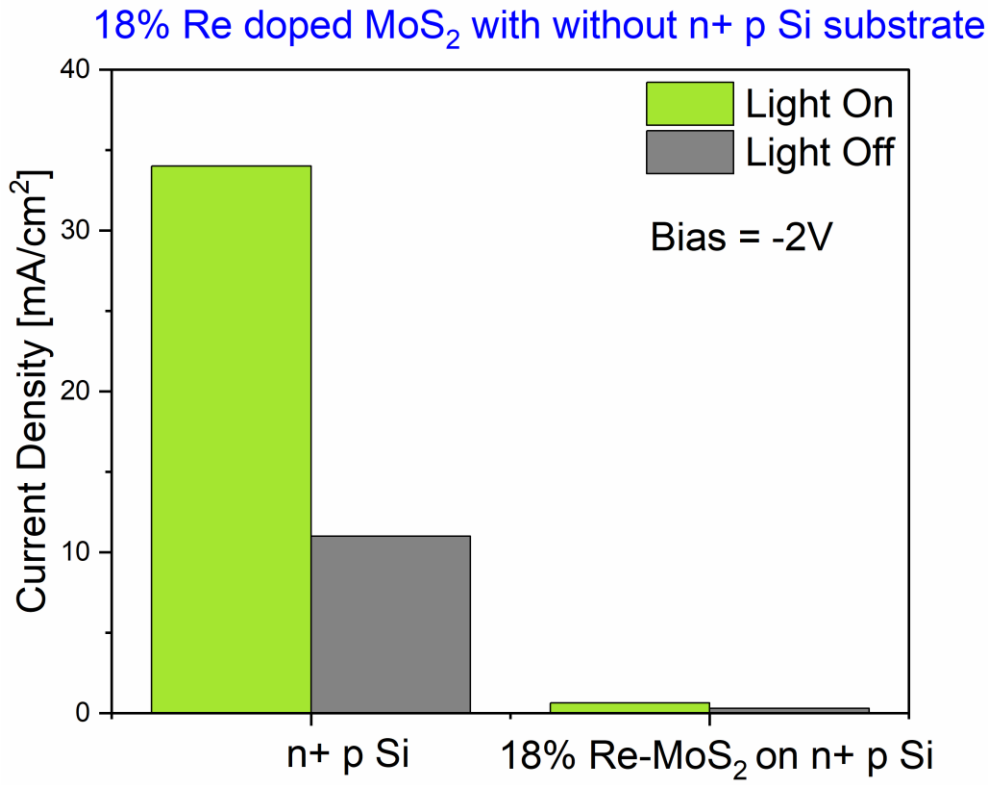


Photo response assessment of TMD films on Al_2O_3 substrate

With 7nm of TiO_2 Capping layer Nb-Doped WS_2


0% Nb-WS_2 , 2% Nb-WS_2

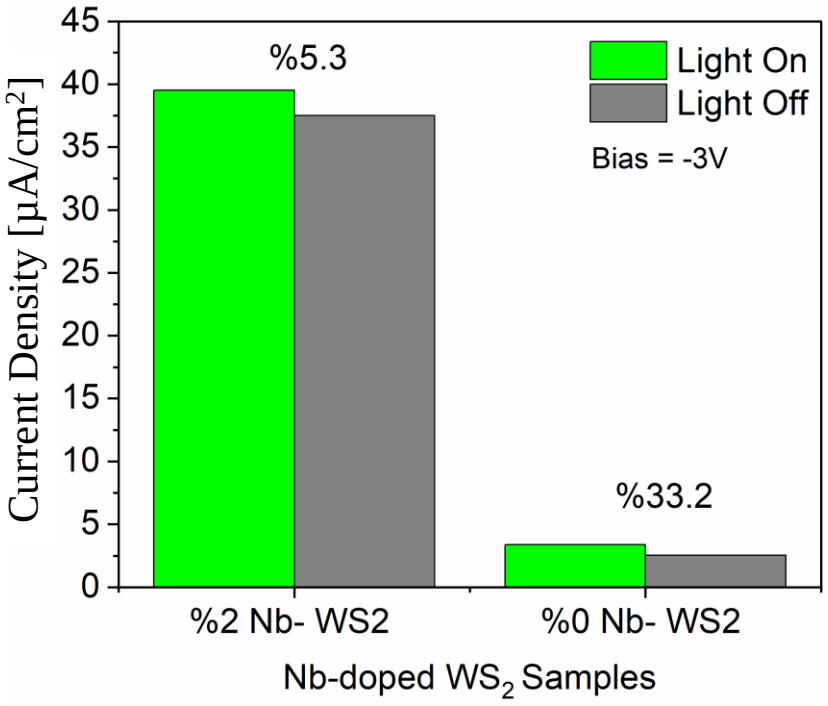

$$Photoresponse\ \%\ [PR] = \frac{I\ on - I\ off}{I\ off}\ x\ 100$$

With 7nm of TiO_2 Capping layer Re-Doped MoS_2

0% Re-MoS_2 , 5% Re-MoS_2 , 18% Re-MoS_2

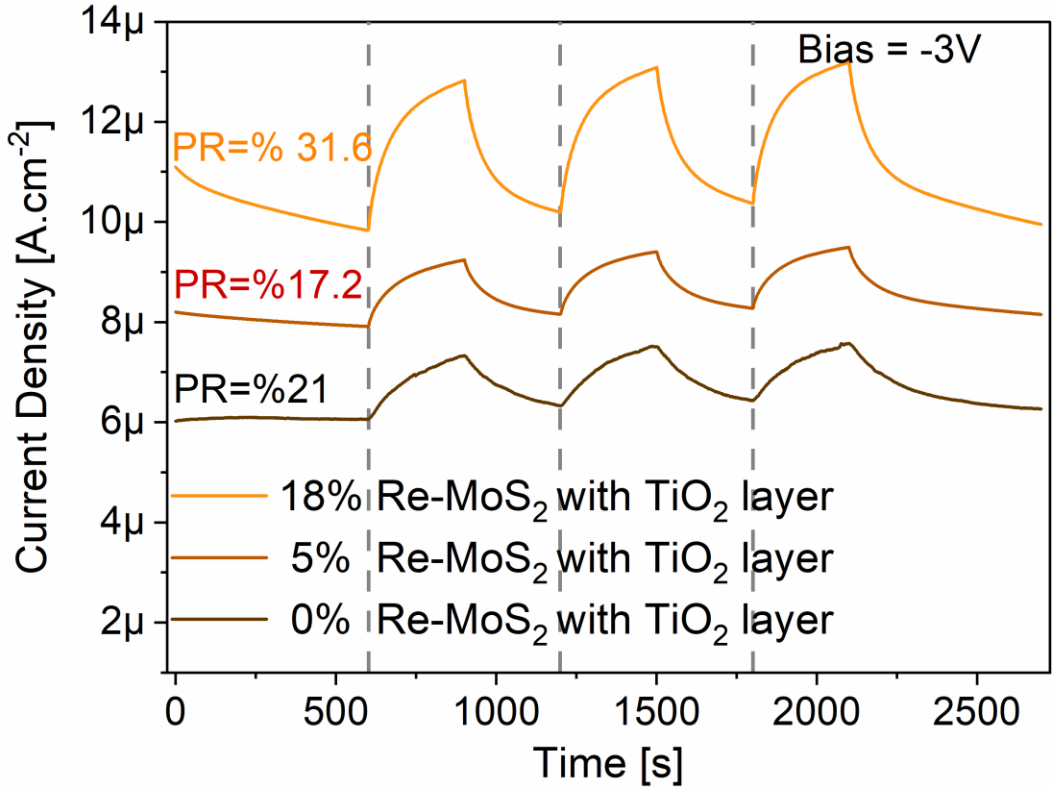


Photoelectrochemical Analysis of doped TMD films


FreeHydroCells

Re-Doped MoS_2 and WS_2 with ~ 7 – 10 nm of TiO2 Capping layer in 0.1M KOH (Ph 13)


0% Re-MoS_2

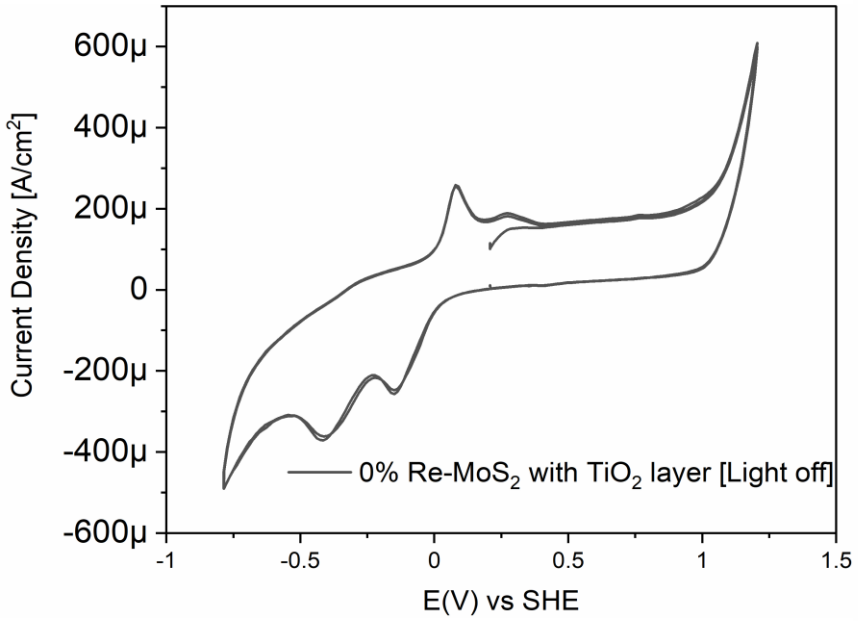

0% Re-MoS_2

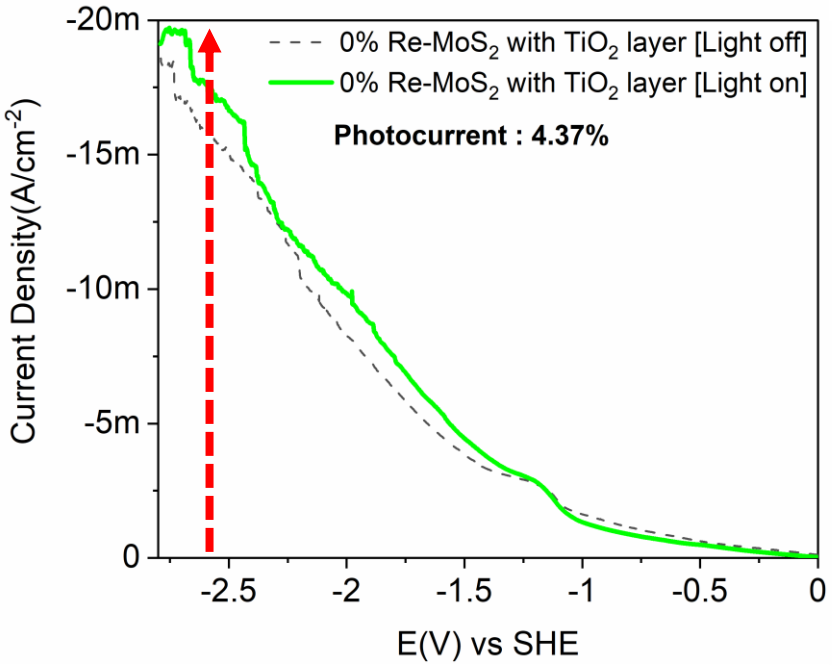


0% 5% and 18 Re-MoS_2
0% Nb-WS_2

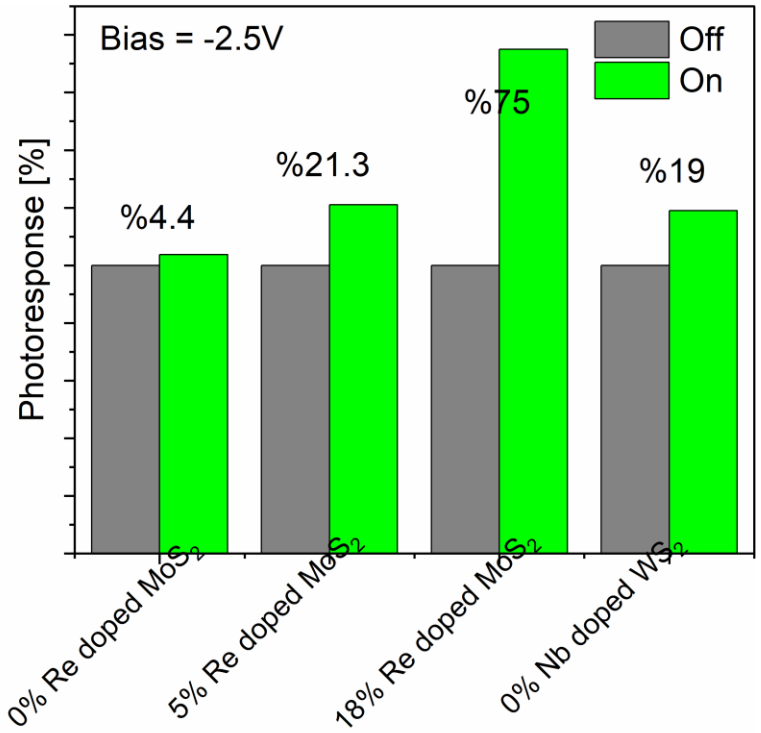


$$Photoresponse\ \%\ [PR] = \frac{I\ on - I\ off}{I\ off}\ x\ 100$$

Solar-To-Hydrogen Efficiency

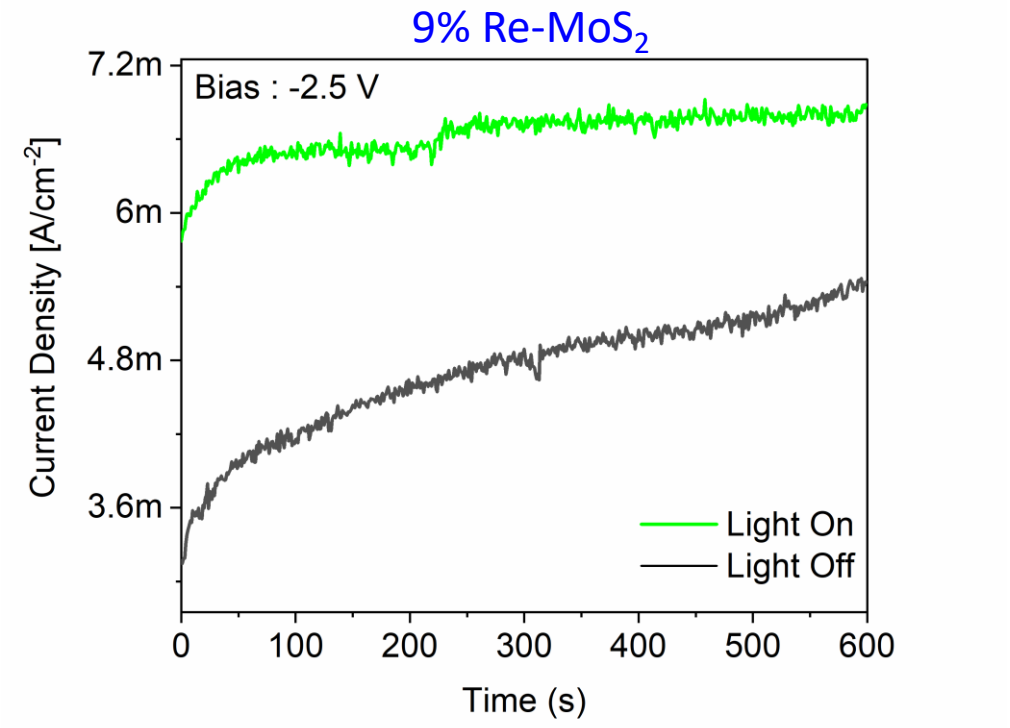

BARDS: Sonic resonance response analysis of H_2

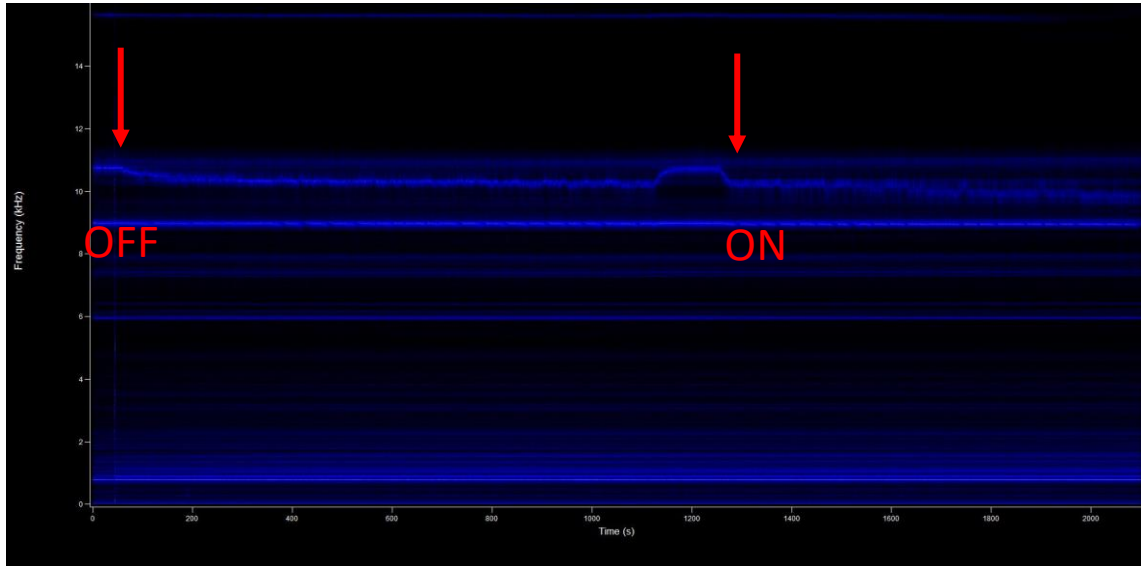

- Solar Simulator, AM1.5g 1.1 Suns (equivalent to AM1.5g 0.99 Suns)
- Photocurrent J_{sc} ~ 2.6 mA/cm^2 & H_2 ~ 59.2 nmol/s
- Estimated Solar-To-Hydrogen (STH), η_{STH} ~ **5.3 %**

Segev *et al*, J. Phys. D: Appl. Phys. 55 323003, (2022)

Alley *et al*,. Methods. 10, (2022)

Kang *et al*,. ACS Appl. Energy Mater. 2020, 3, (2000)

Talk Outline

- Introduction
- Materials' growth and formation
- Structural and physical characterisation
- Hall-effect analysis
- Photoelectric and Photoelectrochemical analysis
- Conclusions, Future Work and Acknowledgements

Conclusions

FreeHydroCells

- ✓ TMD films with introducing different amount of dopants
- ✓ Detection of photo resistance change with doping
- ✓ Detection of photocurrent in photoelectrochemical assessment with doping
- ✓ Estimated STH efficiency

Future Work

- More characterisation with the current single layer projects.
- Multilayer structure
- Band gap engineering with different layers
- Defect passivating, high absorbent capping layers

AMBER Advancing Materials for Impact · UCC University College Cork, Ireland Coláiste na hOllscoile Corcaigh · RWTH AACHEN UNIVERSITY · Consiglio Nazionale delle Ricerche · cea · AMO · BARDS A Sound Approach to Chemical Analysis · UCC ACADEMY

Free Hydro Cells

Funded by the European Union. Views and opinions expressed are however those of the author(s) only and do not necessarily reflect those of the European Union or CINEA. Neither the European Union nor the granting authority can be held responsible for them

Funded by the European Union

Thank you!

Acknowledgements:

This project work has received funding from the European Union under grant agreement No 101084261 (FreeHydroCells)

This publication has been financially supported (in part) by the Science Foundation Ireland (SFI) Centres Grant, Grant Number 12/RC/2278-P2 (AMBER)

Questions?

AMBER Advancing Materials for Impact · UCC University College Cork, Ireland Coláiste na hOllscoile Corcaigh · RWTH AACHEN UNIVERSITY · Consiglio Nazionale delle Ricerche · cea · AMO · BARDS A Sound Approach to Chemical Analysis · UCC ACADEMY

Funded by the European Union