CORA Cork Open Research Archive
Cartlann Taighde Oscailte Chorcaí

Title	Quantifying the effect of electronic conductivity on the rate-performance of nanocomposite battery electrodes
Authors	Tian, Ruiyuan;Alcala, Nolito;O'Neill, Steven;Horvath, Dominik;Coelho, João;Griffin, Aideen;Zhang, Yan;Nicolosi, Valeria;O'Dwyer, Colm;Coleman, Jonathan
Publication date	2020-01-30
Original Citation	Tian, R., Alcala, N., O'Neill, S., Horvath, D., Coelho, J., Griffin, A., Zhang, Y., Nicolosi, V., O'Dwyer, C. and Coleman, J. (2020) 'Quantifying the effect of electronic conductivity on the rate-performance of nanocomposite battery electrodes', ACS Applied Energy Materials, 3(3), pp. 2966-2974. doi: 10.1021/acsaem.0c00034
Type of publication	Article (peer-reviewed)
Link to publisher's version	https://pubs.acs.org/doi/abs/10.1021/acsaem.0c00034 - 10.1021/acsaem.0c00034
Rights	© 2020, American Chemical Society. This document is the Accepted Manuscript version of a Published Work that appeared in final form in ACS Applied Energy Materials after technical editing by the publisher. To access the final edited and published work see https://pubs.acs.org/doi/abs/10.1021/acsaem.0c00034
Download date	2026-11-08 13:36:17
Item downloaded from	https://hdl.handle.net/10468/9787

UCC
University College Cork, Ireland
Coláiste na hOllscoile Corcaigh

Supporting Information for

Quantifying the effect of electronic conductivity on the rate-performance of nanocomposite battery electrodes

Ruiyuan Tian,[1,2] Nolito Alcala,[3] Stephen JK O'Neill,[1,2] Dominik Horvath,[1,2] João Coelho,[2,4] Aideen Griffin,[1,2] Yan Zhang,[5] Valeria Nicolosi,[2,4] Colm O'Dwyer,[2,5] Jonathan N Coleman[1,2]*

[1]*School of Physics, Trinity College Dublin, Dublin 2, Ireland*

[2]*AMBER Research Center, Trinity College Dublin, Dublin 2, Ireland*

[3]*School of Physics, Technological University Dublin, City Campus, Kevin Street, D08 NF82, Ireland*

[4]*School of Chemistry, Trinity College Dublin, Dublin 2, Ireland*

[5]*School of Chemistry, University College Cork, Tyndall National Institute, and Environmental Research Institute, Cork T12 YN60, Ireland*

*colemaj@tcd.ie (Jonathan N. Coleman); Tel: +353 (0) 1 8963859.

Electrode density

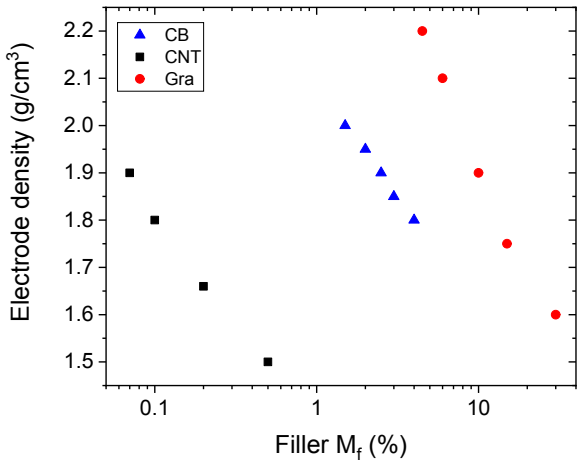


Figure S1: Electrode density versus filler content.

Galvanostatic charge discharge curves

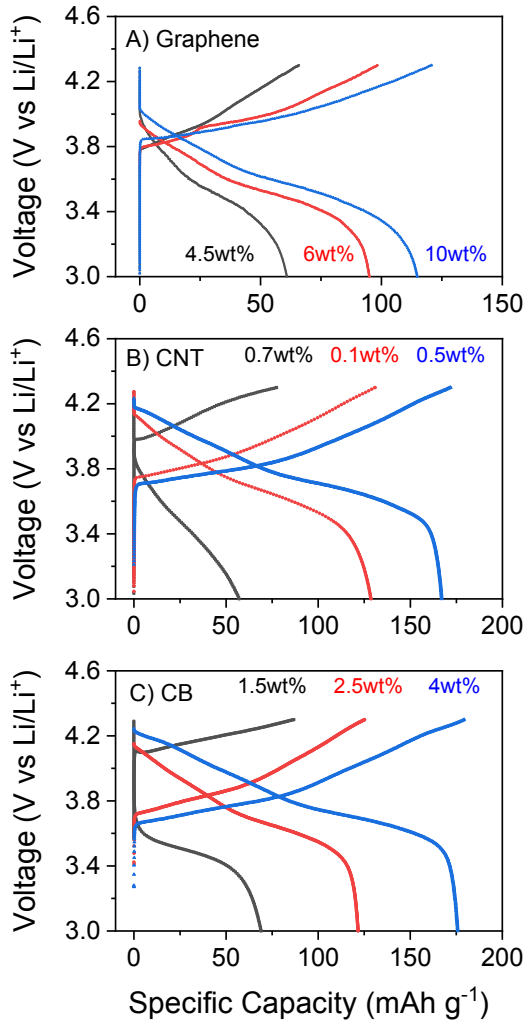


Figure S2: Second cycle charge-discharge curves for electrodes of NMC811 filled with different loadings of A) graphene, B) carbon nanotubes and C) carbon black. All measurements were performed at I/A=17 mA/g.

Calculating the curve in figure 5B

We can plot equation 6a on figure 5B as follows.

Equation 6a can be written as:

$$\frac{\tau}{L_E^2} = \frac{14Q_V}{\sigma_{OOP}} + \left[\frac{28Q_V}{2\sigma_{BL}P_E^{3/2}} + \frac{1}{D_{BL}P_E^{3/2}} + \frac{L_S}{L_E}\frac{28Q_V}{\sigma_{BL}P_S^{3/2}} + \frac{1}{L_E^2}\left(\frac{L_S^2}{D_{BL}P_S^{3/2}} + \frac{L_{AM}^2}{D_{AM}} + t_c \right) \right]$$

When plotted as τ / L_E^2 vs. Q_V / σ_{OOP} the expected slope is 14 F/mAh while the intercept is the set of terms in the square brackets. The intercept can be found when $1/\sigma_{OOP}=0$ or when $\sigma_{OOP}\to\infty$.

For illustrative purposes, we plot τ / L_E^2 vs. σ_{OOP} below. The intercept in figure 5B is the constant value of τ / L_E^2 when σ_{OOP} becomes large. To plot this, we need to estimate the relevant parameters:

$\langle Q_V \rangle$=2.1×10^8 mAh/m^3	Found using $Q_V = \rho_E Q_M$ and averaging over all samples.
σ_{BL}=0.5 S/m	Typical for LIB electrolytes[1]
D_{BL}=3×10^{-10} m^2/s	Middle of the range for common battery electrolytes[2-3]
P_E=0.6	Estimated from mean electrode density
P_S=0.4	Typical for commercial separators[4]
L_S=16 μm	Celgard 2032 separator
$\langle L_E \rangle$=97 μm	Measured mean thickness
L_{AM}=r/3~2μm	Proposed relationship between L_{AM} and particle radius[5]
D_{AM}=5×10^{-14} m^2/s	Diffusivity of Li ions in NMC111[6]
t_c=25s	Roughly middle of the range reported by[5]

Using these parameters yields the following graph which clearly shows the limiting value to be 3.5×10^{10} s/m^2.

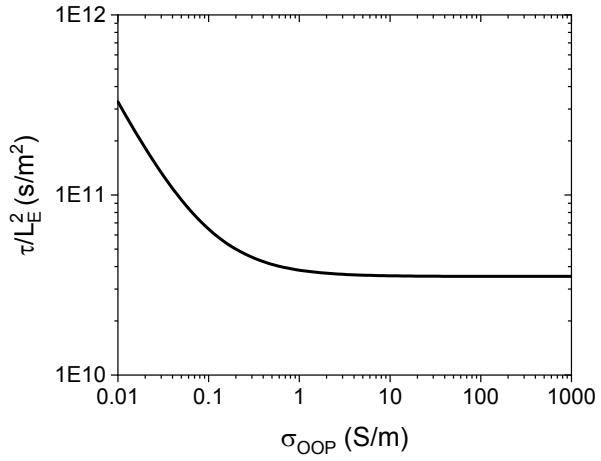


Figure S3: Calculating τ / L_E^2 versus OOP conductivity.

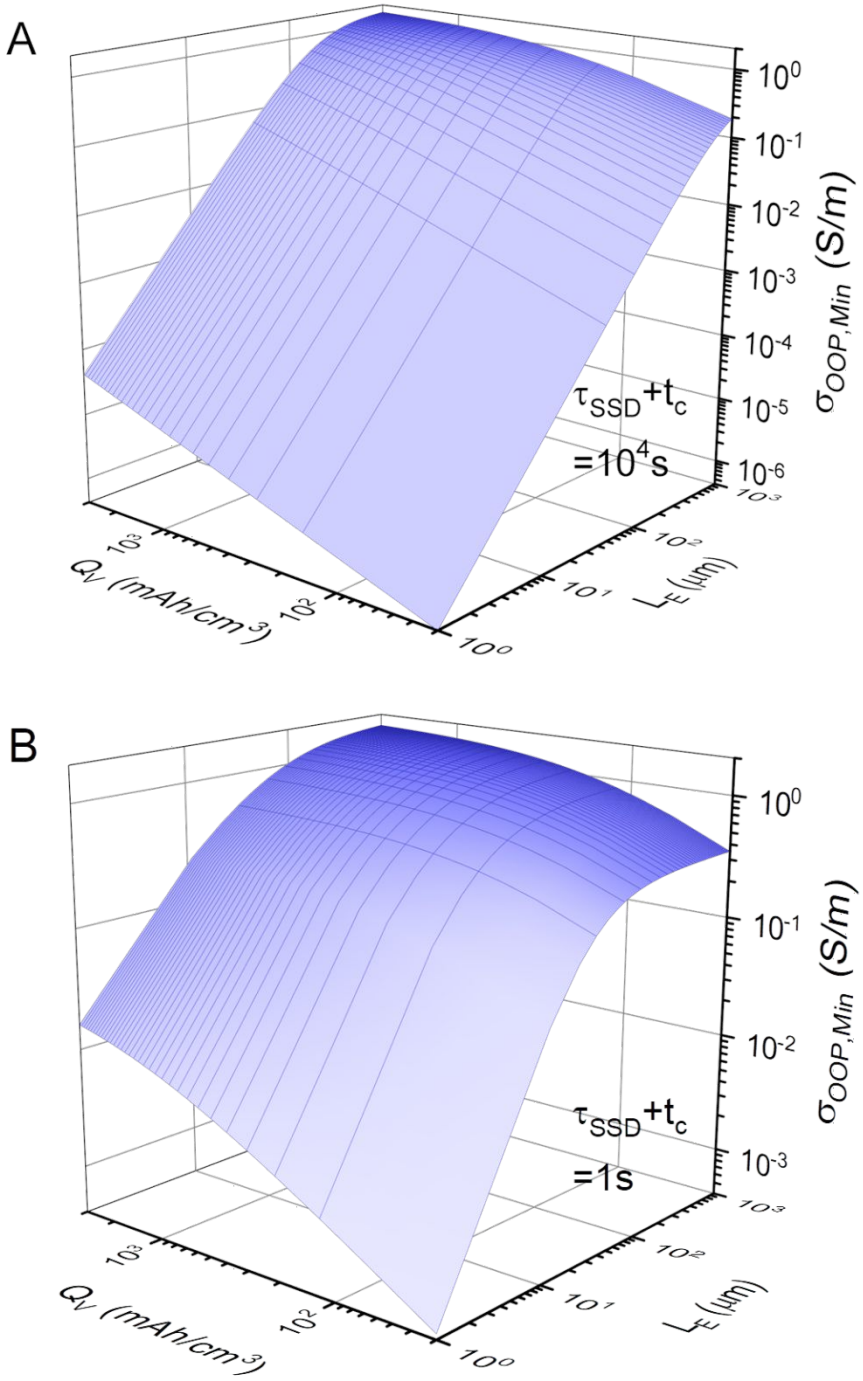


Figure S4: Critical (out-of-plane) electrode conductivity, $\sigma_{OOP,min}$, plotted as a function of electrode thickness (L_E) and low rate volumetric capacity (Q_V). The critical conductivity is that required to reduce the contribution to τ associated with the electrode resistance (first term in equation (6a)) below 10% of the sum of the other contributions to τ (i.e. the other six terms in equation (6a)). Here we calculate $\sigma_{OOP,min}$ using the following parameters: $\langle Q_V \rangle$=2.1×10^8 mAh/m^3, σ_{BL}=0.5 S/m, D_{BL}=3×10^{-10} m^2/s, P_E=0.6, P_S=0.4, L_S=16 μm, $\langle L_E \rangle$=97 μm. In A and

B, this calculation is performed for electrode materials with long (A, $\tau_{SSD}+t_c=10^4$s) and short (B, $\tau_{SSD}+t_c=1$s) combinations of solid-state diffusion and reaction times.

References in SI for publication

(1) Logan, E. R.; Tonita, E. M.; Gering, K. L.; Li, J.; Ma, X.; Beaulieu, L. Y.; Dahn, J. R. A Study of the Physical Properties of Li-Ion Battery Electrolytes Containing Esters. *J. Electrochem. Soc.* **2018,** *165* (2), A21-A30.
(2) Ehrl, A.; Landesfeind, J.; Wall, W. A.; Gasteiger, H. A. Determination of Transport Parameters in Liquid Binary Lithium Ion Battery Electrolytes I. Diffusion Coefficient. *J. Electrochem. Soc.* **2017,** *164* (4), A826-A836.
(3) Ong, M. T.; Verners, O.; Draeger, E. W.; van Duin, A. C. T.; Lordi, V.; Pask, J. E. Lithium Ion Solvation and Diffusion in Bulk Organic Electrolytes from First-Principles and Classical Reactive Molecular Dynamics. *J. Phys. Chem. B* **2015,** *119* (4), 1535-1545.
(4) Zhang, S. S. A review on the separators of liquid electrolyte Li-ion batteries. *J. Power Sources* **2007,** *164* (1), 351-364.
(5) Jiang, F. M.; Peng, P. Elucidating the Performance Limitations of Lithium-ion Batteries due to Species and Charge Transport through Five Characteristic Parameters. *Sci. Rep.* **2016,** *6*, 32639.
(6) Cabanero, M. A.; Boaretto, N.; Roder, M.; Muller, J.; Kallo, J.; Latz, A. Direct Determination of Diffusion Coefficients in Commercial Li-Ion Batteries. *J. Electrochem. Soc.* **2018,** *165* (5), A847-A855.