

Title	Role of drug adsorption onto the silica surface in drug release from mesoporous silica systems.
Authors	Ahern, Robert J.;McCarthy, Carol A.;Devine, Ken J.;Crean, Abina M.
Publication date	2017-12-08
Original Citation	McCarthy, C. A., Ahern, R. J., Devine, K. J. and Crean, A. M. (2018) 'Role of drug adsorption onto the silica surface in drug release from mesoporous silica systems', Molecular Pharmaceutics, 15(1), pp. 141-149. doi:10.1021/acs.molpharmaceut.7b00778
Type of publication	Article (peer-reviewed)
Link to publisher's version	10.1021/acs.molpharmaceut.7b00778
Rights	© 2017, American Chemical Society. This document is the Accepted Manuscript version of a Published Work that appeared in final form in Molecular Pharmaceutics, © American Chemical Society, after peer review and technical editing by the publisher. To access the final edited and published work see https://pubs.acs.org/doi/10.1021/acs.molpharmaceut.7b00778
Download date	2024-05-04 20:57:35
Item downloaded from	https://hdl.handle.net/10468/7133



UCC

University College Cork, Ireland
Coláiste na hOllscoile Corcaigh

Article

Role of drug adsorption onto the silica surface in drug release from mesoporous silica systems

Carol A McCarthy, Robert J Ahern, Ken J Devine, and Abina M. Crean

Mol. Pharmaceutics, **Just Accepted Manuscript** • DOI: 10.1021/acs.molpharmaceut.7b00778 • Publication Date (Web): 08 Dec 2017

Downloaded from <http://pubs.acs.org> on December 13, 2017

Just Accepted

“Just Accepted” manuscripts have been peer-reviewed and accepted for publication. They are posted online prior to technical editing, formatting for publication and author proofing. The American Chemical Society provides “Just Accepted” as a free service to the research community to expedite the dissemination of scientific material as soon as possible after acceptance. “Just Accepted” manuscripts appear in full in PDF format accompanied by an HTML abstract. “Just Accepted” manuscripts have been fully peer reviewed, but should not be considered the official version of record. They are accessible to all readers and citable by the Digital Object Identifier (DOI®). “Just Accepted” is an optional service offered to authors. Therefore, the “Just Accepted” Web site may not include all articles that will be published in the journal. After a manuscript is technically edited and formatted, it will be removed from the “Just Accepted” Web site and published as an ASAP article. Note that technical editing may introduce minor changes to the manuscript text and/or graphics which could affect content, and all legal disclaimers and ethical guidelines that apply to the journal pertain. ACS cannot be held responsible for errors or consequences arising from the use of information contained in these “Just Accepted” manuscripts.



ACS Publications

Molecular Pharmaceutics is published by the American Chemical Society, 1155 Sixteenth Street N.W., Washington, DC 20036

Published by American Chemical Society. Copyright © American Chemical Society. However, no copyright claim is made to original U.S. Government works, or works produced by employees of any Commonwealth realm Crown government in the course of their duties.

1
2
3 1 **TITLE PAGE**
4

5
6 2 **TITLE**
7

8 3 Role of drug adsorption onto the silica surface in drug release from mesoporous silica
9
10 4 systems
11
12

13 5 **AUTHORS**
14
15

16 6 Carol A. McCarthy ¹, Robert J. Ahern ¹, Ken J. Devine ², Abina M. Crean ^{*1}
17
18

19 7 ¹Synthesis and Solid State Pharmaceutical Centre (SSPC), School of Pharmacy, University
20
21 8 College Cork, Cork, Ireland
22
23

24 9 ²School of Pharmacy, University College Cork, Cork, Ireland
25
26

27 10 **CORRESPONDING AUTHOR**
28
29

30 11 Abina M. Crean
31

32 12 Pharmaceutics Department
33
34

35 13 School of Pharmacy
36
37

38 14 University College Cork
39
40

41 15 Cork, Ireland
42

43 16 Email: a.crean@ucc.ie
44
45

46 17 Telephone: +353 21 4901667
47
48


49 18
50

51 19
52
53

54 20
55
56
57
58
59
60

21

22 GRAPHICAL ABSTRACT

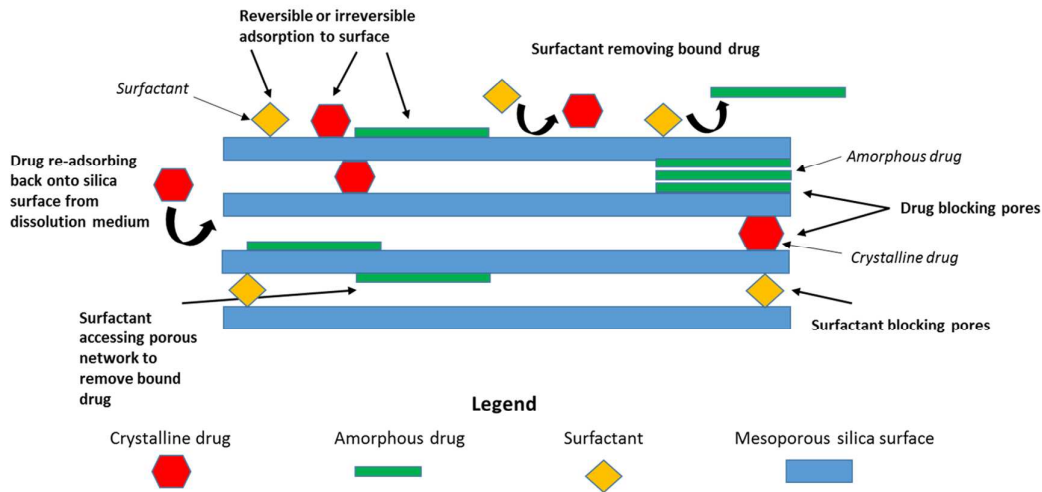

ABSTRACT

Factors contributing to incomplete drug release from a number of mesoporous silica formulations are not well understood. This study aims to address this gap in knowledge by exploring the role of drug adsorption onto silica substrates during the drug release process in dissolution media. Adsorption isotherms were generated to understand drug adsorption behaviour onto the silica surface. Two silica materials were selected (SBA-15 (mesoporous) and Aerosil®200 (non-porous)) to investigate the influence of porous architecture on the adsorption/dissolution processes. The ability of the dissolution medium to wet the silica surface, particularly the porous network, was investigated by the addition of a surfactant to the dissolution medium. The results demonstrated that a larger amount of drug was bound/m² to the non-porous surface than to the mesoporous material. Adsorption isotherms proved useful in understanding drug adsorption/release behaviour for the non-porous silica formulation. However, the quantity of drug remaining on the mesoporous silica surface after dissolution was significantly higher than the amount predicted using adsorption isotherm data. These results suggest that a fraction of loaded drug molecules were tightly bound to the silica surface or attached to sites which are inaccessible for the dissolution media. The presence of surfactant, sodium dodecyl sulphate, in the media enhanced drug release from the silica surface. This behaviour can be attributed to both the improved wetting characteristics of the media and adsorption of the surfactant to the silica surface. The findings of this study reinforce the significance of the role that silica porous architecture plays in the dissolution process and indicates that accessible surface area is an important parameter to consider for mesoporous systems in relation to drug release.

KEYWORDS

Adsorption; isotherm; dissolution; mesoporous silica; surfactant; porous architecture

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

60 **1. INTRODUCTION**

61 Loading drugs onto mesoporous silica materials has been considered as a formulation
62 strategy to improve the aqueous solubility of BCS Class II drugs ¹⁻³. The high surface area
63 and large pore volume of these silica carriers render them attractive substrates for enhancing
64 drug dissolution ⁴. Drug molecules loaded onto the silica surface exist in a stabilised
65 amorphous state which greatly enhances drug solubility and dissolution rate ⁵⁻⁷. In recent
66 years, research in this area has focused on the development of various drug loading methods
67 for these carriers ⁸⁻¹⁰ and the first *in vivo* animal studies have been conducted ¹¹⁻¹³. However,
68 there remains a gap in knowledge as regards understanding the mechanism of drug
69 dissolution from mesoporous silica formulations ³. Incomplete *in vitro* drug release from
70 these systems has been reported by many groups in the literature ^{9, 14, 15}. However, the factors
71 contributing to these observations in dissolution experiments, performed under sink
72 conditions, are not well understood. A study by Bui *et al* explored the use of mesoporous
73 silica materials as adsorbents for chemicals found in pharmaceutical wastewater ¹⁶. They
74 determined that some drug molecules could bind irreversibly onto the silica surface.
75 However, the impact of irreversible drug binding on the release of drug from mesoporous
76 silica formulations has not been considered in the literature to date.

77 The aim of this study was to elucidate the role of drug adsorption onto porous and non-porous
78 silica substrates, during drug release from these systems. Adsorption isotherms were
79 generated to understand drug adsorption onto the silica surface. This equilibrium process
80 describing drug bound to the silica surface and drug existing in solution emerged as a
81 significant factor in gentamicin release from a silica carrier in a study by Xue *et al* ¹⁷. In this
82 work, sulphamethazine (SZ) was chosen as the model drug. Sulphamethazine has the
83 potential to form amine-hydroxyl hydrogen bonds with the silica surface ¹⁷. Two silica
84 substrates were selected (SBA-15 (mesoporous) and Aerosil®200 (non-porous)) to investigate

the influence of porous architecture on the adsorption process. The extent of passive drug adsorption was quantified and compared with drug retained during dissolution experiments to determine whether isotherms can predict the extent of drug release from these formulations.

The ability of the dissolution medium to influence drug adsorption and release was considered through the addition of a surfactant to the dissolution medium. Sodium dodecyl sulphate (SDS), an anionic surfactant, was chosen as it is a common excipient added to dissolution media and formulations to improve the wetting characteristics and the solubilisation of drug molecules¹⁸. Sulphamethazine dissolution from SZ/silica systems in 0.1M HCl media was compared with drug dissolution in media containing surfactant to determine if improved dissolution media wetting capability enhances drug release from silica systems.

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

2. EXPERIMENTAL SECTION

2.1. Materials

SBA-15 was obtained from Glantreo Ltd. (Ireland). Aerosil®200 Pharma was sourced from Evonik Industries (Germany). Silica surface and pore properties were obtained from suppliers (Table 1). Sulphamethazine (SZ) and sodium dodecyl sulphate (SDS) (>98.5%) were purchased from Sigma Aldrich (Ireland). Liquid carbon dioxide was supplied by Irish Oxygen Ltd (Ireland). All other chemicals and solvents were of analytical grade or HPLC grade and purchased from Sigma-Aldrich (Ireland).

Table 1. Properties of silica materials obtained from suppliers

<i>Silica Material</i>	<i>Porosity</i>	<i>Particle Size</i> <i>(μm)</i>	<i>Surface Area</i> <i>(m²)</i>	<i>Pore Volume</i> <i>(cm³)</i>	<i>Pore Diameter</i> <i>(Å)</i>
<i>SBA-15</i>	Mesoporous	30	678.57 ± 8.23	0.64 ± 0.02	51.85 ± 0.05
<i>Aerosil®200</i>	Non-porous	12	200.00 ± 25.00	N/A	N/A

2.2. Surface Tension Measurements

Surface tension was determined experimentally using a KRUSS processor tensiometer K12 (KRUSS GmbH, Germany) with a platinum Wilhelmy plate. The plate was washed with deionised water, followed by an ethanol wash and subsequently flamed over a Bunsen burner after each measurement. All measurements were performed at 37 °C which was maintained with the HAAKE water bath (Thermo Fisher Scientific Inc., USA). Full independent replicates were performed in triplicate. Critical micellar concentrations (CMC) of SDS in deionised water and 0.1M HCl were determined by analysing changes in surface tension over the surfactant concentration range investigated.

2.3. Solubility Measurements

Solubility studies were performed in triplicate by the addition of excess sulphamethazine (SZ) to 10 ml of buffer media (0.1M HCl) using a standardised shake-flask method with a total shaking time of 48 h at 37°C. Samples (2 ml volume) were removed at 24 h and 48 h time points and centrifuged at 16,500g for 13 min using a Hermle z233M-2 fixed angle rotor centrifuge, (HERMLE Labortechnik GmbH, Germany). The supernatant was removed and centrifuged again under the same conditions. The resultant supernatant was analysed using HPLC following dilution with mobile phase.

2.4. Adsorption Studies

Sulphamethazine adsorption studies were performed in screw-capped glass vials containing 100 mg of silica (SBA-15 or Aerosil®200) in 20 ml of SZ solution at a defined concentration in buffer (0.1 M HCl, pH 1.2). Experiments were conducted under the same conditions as solubility measurements i.e. shake-flask conditions for 24 h at 37 °C. At 24 h, samples (2 ml) volume were removed and centrifuged at 16,500 g for 13 min using a Hermle z233M-2 fixed angle rotor centrifuge, (HERMLE Labortechnik GmbH, Germany). The supernatant was removed and centrifuged again under the same conditions. The resultant supernatant was analysed using HPLC following dilution with mobile phase.

Adsorption studies were also conducted under the same conditions in the presence of a surfactant (sodium dodecyl sulphate (SDS)) at two defined concentrations, 10 mM SDS and 50 mM SDS. These concentrations were chosen as they reflect the range of concentrations approved for SDS by the U.S. Food and Drug Administration (FDA) Dissolution Methods¹⁹. An isotherm was generated by plotting the concentration of drug (mM) in solution at 24 h (x-axis) versus the quantity of drug adsorbed (mmol) per gram or per m² of the silica carrier (y-

axis). Linearised forms of the Langmuir²⁰ and Freundlich²¹ isotherms were applied to the experimental data and the parameters determined are detailed in Table 2.

Table 2. Linearized forms of Langmuir and Freundlich Isotherms

Name	Linearised Form	Plot	Parameters
Langmuir	$F/B = (1/a \cdot N_t) + F/N_t$	F versus F/B	$a = \text{slope/intercept}$ $N_t = 1/\text{slope}$
Freundlich	$m \log F = \log B + a$	logF versus log B	$a = \text{intercept}$ $m = \text{slope}$

where *B* is the concentration of drug adsorbed to the silica surface, *F* is the concentration of free substrate in solution at 24 h, *N_t* is the total number of binding sites and *a* is related to the average binding affinity

2.5. Preparation of Sulphamethazine Loaded Silica Formulations

Sulphamethazine loaded silica formulations were prepared according to the method previously described by Ahern et al¹⁵. The drug and silica material was combined at a ratio of 1 mg SZ: 3 m² silica (SBA-15 or Aerosil®200) in a BC 316 high-pressure reactor (High Pressure Equipment Company, USA) and stirred using a magnetic stirring. The reactor was heated to 40 °C using heating tape and maintained at this temperature for the duration of the experiment. Temperature was monitored using a temperature monitor (Horst GmbH, Germany). The reactor cell was filled with liquid CO₂ and a high pressure pump (D Series Syringe Pump 260D, Teledyne ISCO, USA) was used to pump additional CO₂ to a final processing pressure (27.58 MPa). After 24 h, the cell was depressurised rapidly by venting the CO₂. The processed material was collected from the cell and stored in a desiccator prior to analysis.

169

170 2.6. Drug Content Quantification

171 The sulphamethazine content of the silica formulations were determined by
172 thermogravimetric analysis (TGA), using a TGA 500 instrument (TA Instruments Ltd.,
173 United Kingdom). Samples in the weight range 2–10 mg were loaded onto tared platinum
174 pans and heated from ambient temperature to 900 °C, at a heating rate of 10 °C/min under an
175 inert N₂ atmosphere. Samples were analysed in triplicate. The drug quantity was calculated
176 based on the weight loss between 100 and 900 °C, corrected for the weight loss over the same
177 temperature range for a silica reference sample ¹⁴. TGA thermograms were analysed using
178 Universal Analysis 2000 software (TA Instruments Ltd., United Kingdom). Drug-loading
179 efficiency was calculated using Equation 1:

$$180 \text{ Drug loading efficiency (\%)} = \frac{\text{Actual drug loading (mg)}}{\text{Theoretical drug loading (mg)}} * 100 \quad \text{Equation 1}$$

181 The theoretical drug-loading was based on mass fraction of drug and silica used to prepare
182 samples.

183 2.7. Dissolution Studies

184 Dissolution studies were performed in triplicate using USP II apparatus (Erweka® DT600
185 dissolution test system (ERWEKA GmbH, Germany)) in 500ml buffer (0.1M HCl, pH 1.2)
186 at 37 ± 5°C at a paddle rotation of 75 rpm. Sink conditions were employed for all dissolution
187 experiments. A fixed mass of unprocessed drug (150 mg) or a mass of drug-silica formulation
188 equivalent to 150 mg of drug was added to the dissolution medium. Samples of 4 ml volume
189 were withdrawn at 1, 5, 10, 15, 30, 60 and 120 min intervals with an additional sample taken
190 at the 24 h time point. Samples were immediately replaced with an equal volume of fresh,
191 pre-warmed medium. The withdrawn samples were centrifuged at 16,500 g for 13 min using
192 a Hermle z233M-2 fixed angle rotor centrifuge, (HERMLE Labortechnik GmbH, Germany).

193 The supernatant was removed and centrifuged again under the same conditions. The resultant
194 supernatant was analysed using HPLC following dilution with mobile phase.

195 Dissolution studies were repeated as above with the addition of surfactant (SDS) to the
196 dissolution media at two concentrations (10 mM and 50 mM).

197 **2.8. HPLC Analysis of Sulphamethazine and Sodium Dodecyl Sulphate**

198 Reversed phase high performance liquid chromatography (HPLC) was performed using an
199 Agilent 1200 series HPLC system (Agilent Technologies, USA) equipped with both a Photo
200 Diode Array Detector (DAD) and an Evaporative Light Scattering Detector (ELSD) in series.

201 To quantify drug content in adsorption and dissolution studies without surfactant a reversed-
202 phase column Kinetex C-18 column (150 mm × 4 mm) with internal pore width 2.6 µm
203 (Phenomenex Ltd., United Kingdom) was utilised. An isocratic HPLC-DAD (diode array
204 detector) technique adapted from a method by Ding et al ²² with a mobile phase consisting of
205 acetonitrile – water – acetic acid (25:75:0.05), an injection volume of 50 µL and a flow rate
206 of 1 ml.min⁻¹ at ambient temperature was employed. The detection wavelength was 265 nm.
207 The retention time for sulphamethazine was 5.9 min.

208 To quantify both drug and surfactant concentrations in adsorption and dissolution studies, a
209 HPLC-ELSD method adapted from Im *et al* ²³ was utilised. The ELSD system was operated
210 with an evaporative temperature of 80°C, a nebulizer temperature of 70 °C and a N₂ gas flow
211 rate of 1.0 L.min⁻¹. A reversed-phase column Prodigy ODS-3 column (150 mm × 4.6 mm)
212 with internal pore width 5 µm (Phenomenex Ltd., United Kingdom) was utilised. Drug and
213 surfactant were separated using a mobile phase gradient which consisted of two solutions:
214 eluent A (water (25 mM ammonium acetate)) and B (acetonitrile). The gradient program
215 started with 5% eluent B for 2 min, followed a 6 min gradient up to 95% eluent B. The
216 column was then equilibrated with starting conditions for 2 min before the next injection. The

flow rate was $1\text{ ml}\cdot\text{min}^{-1}$ with an injection volume of $10\text{ }\mu\text{L}$. Column temperature was set to 30°C . The retention time for sulphamethazine and sodium dodecyl sulphate was 5.9 min and 7.4 min, respectively.

2.9. Pore size analysis of Mesoporous Silica Systems Before and After Dissolution

Pore size analysis by nitrogen (N_2) adsorption of the mesoporous sulphamethazine-SBA-15 formulation was carried out using a Gemini VI surface area and pore size analyser (Micromeritics, USA). Aerosil®200 is a non-porous silica material so porosity analysis was not undertaken. The samples were degassed overnight at 100°C in a FlowPrep 060 sample degas system (Micromeritics, USA) prior to analysis. During analysis, liquid N_2 at -196°C maintained isothermal conditions. The mesopore volume along with mesopore width were calculated using the Barrett–Joyner–Halenda (BJH) adsorption correlation²⁴. Samples were analysed in duplicate.

2.10. Statistical Analysis

All statistical analyses were conducted using Microsoft Excel 2013 (Microsoft, USA) and GraphPad Prism (ver. 5, GraphPad Software Inc., USA). Results are expressed as mean \pm standard deviation. *In vitro* dissolution and adsorption isotherm data comparing both formulations at different time points and concentrations respectively were tested for significance using a two-tailed, independent sample *t*-test, assuming Gaussian distribution and equal variance ($p < 0.05$ was considered significant).

238 3. RESULTS

239 3.1. Sulphamethazine (SZ) Loading Efficiency

240 Sulphamethazine was loaded onto both silica substrates at a theoretical ratio of 1 mg SZ/ 3 m²
241 silica surface area. Sulphamethazine loading onto SBA-15 was 190 mg/g silica corresponding
242 to a drug loading efficiency of 75.86% (calculated using Equation 1). SZ drug loading onto
243 Aerosil®200 was 60 mg/g silica, equivalent to an 88.62% loading efficiency. These results are
244 in line with loading efficiencies previously reported using SC-CO₂ methods¹⁵.

245 3.2. Solubility Studies

246 SDS increases the solubility of some drugs above its CMC (critical micellar concentration)²⁵.
247 In this study, the CMC of SDS in both deionised water and 0.1M HCl were determined. The
248 CMC of SDS in deionised water at 37°C was 7.3 mM (0.21% w/v), while in 0.1 M HCl
249 solution at 37°C it was 0.8 mM (0.023%). Therefore, both concentrations of surfactant
250 investigated in this study (0.3% w/v and 1.44% w/v) were above the CMC in 0.1M HCl.
251 Drug solubility in each of the adsorption/dissolution media investigated are displayed in
252 Table 4. SZ solubility in 0.1 M HCl and 0.1 M HCl with 10 mM SDS (0.3% w/v) were not
253 significantly different. At the higher concentration of surfactant (50 mM SDS (1.44% w/v)),
254 SZ solubility (38.80 ± 0.40 mM) was significantly higher than in the other two media (p <
255 0.01). However, SZ solubility enhancement in the presence of both concentrations of SDS
256 was considered marginal.

257 3.3. Adsorption Studies

258 3.3.1. Sulphamethazine Adsorption onto Silica in 0.1 M HCl Medium

259 Adsorption isotherms for sulphamethazine adsorption onto SBA-15 and Aerosil®200, at the
260 24 h time point, in 0.1M HCl at 37°C, are displayed in Figure 1 as both *mmol SZ/g silica*
261 adsorbed and *mmol SZ/m² silica* adsorbed. Drug adsorption onto the Aerosil®200 non-porous

surface levelled off. In contrast, adsorption onto the mesoporous surface increased with increasing drug concentration. There was more drug bound per m^2 to the non-porous silica surface than the mesoporous SBA-15, indicating the drug cannot access the porous network in its entirety.

Adsorption data for the porous and non-porous silica systems were fitted to the Langmuir and the Freundlich adsorption models (Table 3). While both models were capable of describing the data for both silica substrates ($R^2 > 0.90$), the Langmuir model emerged as the best-fit for the adsorption of SZ onto non-porous Aerosil®200. In contrast, drug adsorption onto mesoporous SBA-15 was best described by the Freundlich model. The Langmuir model parameters were calculated for both silica substrates. The number of binding sites on the surface (N_t (mmol/ m^2)) was determined to be greater for the non-porous Aerosil®200 than SBA-15, indicating that drug molecules cannot access the full extent of the SBA-15 porous architecture. The binding affinity (designated as a (mM)) of drug to the silica surface was equivalent for both the mesoporous material and the non-porous Aerosil®200 (*adsorbed SZ mmol/ m^2 silica*). Freundlich model parameters were also calculated for both substrates and are displayed in Table 3. The heterogeneity index (m) is defined over a range of 0 to 1 with values closer to 1 describing a more homogenous system. The non-porous material exhibited the most homogenous surface of the two materials. The Freundlich equation binding affinity parameter (K_o (mM)), revealed stronger binding affinities between the drug and the non-porous surface.

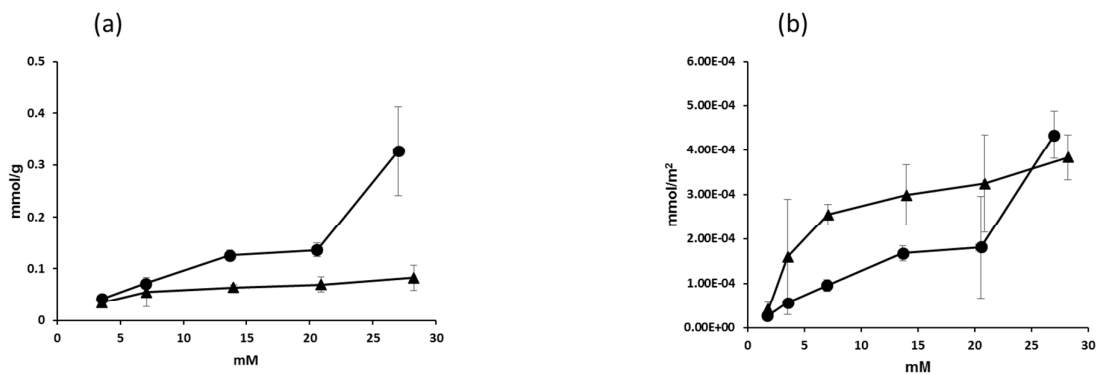


Figure 1. Adsorption isotherms for SZ adsorption ((a) mmol SZ /g silica and (b) mmol SZ/m² silica) onto SBA-15 (●) and Aerosil®200 (▲) at 24 h, 37°C in 0.1 M HCl (n=3, X and Y error bars indicate standard deviation)

Table 3. Isotherm parameters obtained by fitting sulphamethazine and sodium dodecyl sulphate adsorption data (mmol/m²) onto SBA-15 and Aerosil®200 to Langmuir and Freundlich isotherms (SDS adsorption data only produced an acceptable fit with Freundlich isotherm). Measure of fit of data to model is indicated by the R² value.

SULPHAMETHAZINE			
Langmuir Isotherm	N _t (mmol/m ²)	a (mM)	R ²
SBA-15	0.04	0.0004	0.95
Aerosil®	0.15	0.0004	0.99
Freundlich isotherm	m	K _o (mM)	R ²
SBA-15	0.50	5.66	0.98
Aerosil®	0.70	8.09	0.91
SODIUM DODECYL SULPHATE			
Freundlich isotherm	m	K _o (mM)	R ²
SBA-15	0.53	10.70	0.98
Aerosil®	0.77	6.72	0.95

3.3.2. SDS Adsorption onto Silica in 0.1 M HCl Medium

The isotherm for SDS adsorption onto both silica substrates in 0.1M HCl at 37°C is presented in Figure 2. The quantity of surfactant adsorbed onto both silica materials was similar in magnitude to the quantity of drug adsorbed under the same experimental conditions (Figure 1 (b) *versus* Figure 2). For SBA-15 a correlation of $r = 0.83$ ($p < 0.04$) between surfactant and drug adsorption was determined while the correlation of adsorption on the non-porous surface was stronger at $r = 0.88$ ($p < 0.02$). The Freundlich adsorption model emerged as the best-fit model for SDS adsorption onto both substrates ($R^2 \geq 0.95$, Table 3). The Freundlich binding affinity for the surfactant with the mesoporous SBA-15 was stronger than that of the drug molecule. This is most likely a result of the surfactant's ability to reduce interfacial tension leading to improved pore wetting and access to additional binding sites in the porous network.

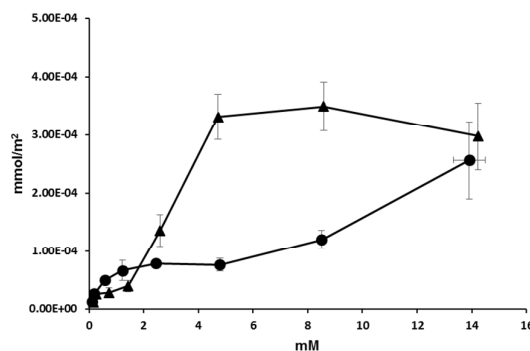


Figure 2. Adsorption isotherms for SDS adsorption (mmol SDS/m² silica) onto SBA-15 (●) and Aerosil (▲) at 24 h, 37°C in 0.1 M HCl ($n=3$, X and Y error bars indicate standard deviation)

3.3.3. Sulphamethazine Adsorption onto Silica in 0.1 M HCl/SDS Media

Adsorption isotherms for sulphamethazine adsorption ($\text{mmol SZ}/\text{m}^2\text{silica}$) onto SBA-15 and Aerosil® at 24 h in media with 0.1 M HCl (10 mM SDS) and 0.1 M HCl (50mM SDS) at 37°C are displayed in Figure 3. There is significantly less drug adsorbed onto both silica materials in the presence of surfactant at both SDS concentrations investigated. Similar to drug adsorption in 0.1M HCl media without surfactant (Figure 1), the non-porous Aerosil® adsorbed a larger fraction of drug/ m^2 than the mesoporous material. As this experiment involved a multi-component system where drug and surfactant are simultaneously adsorbing onto the silica surface, data was not fitted to the Freundlich and Langmuir adsorption models.

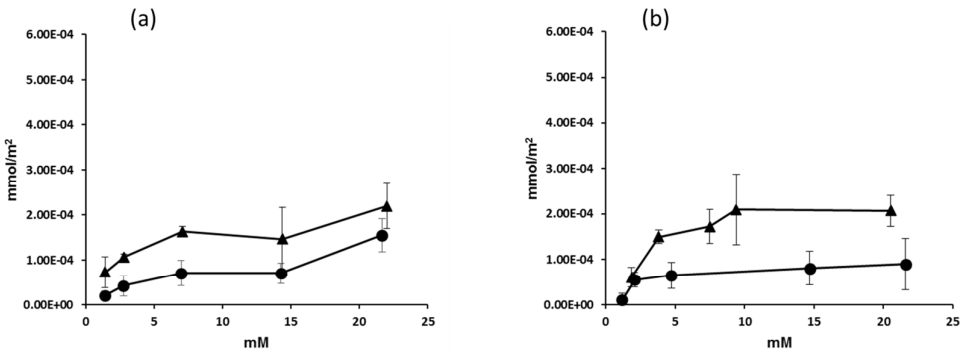


Figure 3. Adsorption isotherms for SZ adsorption ($\text{mmol SZ}/\text{m}^2\text{ silica}$) onto SBA-15 (●) and Aerosil (▲) at 24h, 37°C in (a) 0.1M HCl (10mM SDS) and (b) 0.1M HCl (50mM SDS) (n=3, X and Y error bars indicate standard deviation)

3.4. Dissolution Studies

Dissolution experiments were conducted in the same three media as used for adsorption experiments. Experiments were conducted under sink conditions and the theoretical SZ concentration following 100% release was < 4% the SZ solubility in all cases (Table 4).

Table 4. Solubility and dissolution parameters for unprocessed SZ and SZ loaded silica formulations in the three dissolution media investigated (mean ± standard deviation is provided, n=3)

Dissolution Medium	Solubility	Dissolution	Dissolution (% Cumulative Release)				
	Solubility of Drug (mM)	% Saturated Solubility assuming 100% release	Sample	5 min	10min	15 min	24 h
0.1M HCl	30.00 ± 1.80	3.60	Unprocessed SZ	25.61±4.34	51.86±5.02	82.41±5.56	97.26 ± 1.80
			SZ loaded SBA-15	74.03±7.21	76.06±7.53	74.55±6.10	79.58±2.08
			SZ loaded Aerosil®	70.10±0.35	73.47±0.83	74.17±0.38	77.21±0.01
0.1M HCl 10mM SDS	30.28 ± 0.97	3.56	Unprocessed SZ	98.65±1.04	97.77±0.40	97.10±0.18	97.55±1.02
			SZ loaded SBA-15	90.20±0.65	90.27±1.06	90.32±0.86	92.94±1.25
			SZ loaded Aerosil®	89.13±4.75	90.84±4.09	89.08±4.41	86.15±5.23
0.1M HCl 50 mM SDS	38.80 ± 0.40	2.70	Unprocessed SZ	100.93±0.94	100.11±0.80	99.22±0.94	99.71±1.06
			SZ loaded SBA-15	86.97±3.15	91.95±3.03	94.97±6.33	98.02±4.44
			SZ loaded Aerosil®	91.84±5.26	92.84±5.27	92.53±4.74	90.40±4.12

3.4.1. Sulphamethazine/Silica Systems in 0.1 M HCl Medium

Loading SZ onto porous and non-porous silica carriers significantly enhanced the drug's dissolution rate in 0.1 M HCl buffer media compared to the unprocessed SZ (Figure 4 and Table 4). At the 5 min time point, SZ release from Aerosil[®]200 and SBA-15 was significantly higher than for the unprocessed drug. However, by 15 min, unprocessed SZ dissolution had significantly exceeded drug release from both silica systems. The amount of the free drug released remained higher for the unprocessed SZ than that of the drug/silica samples for the remainder of the experiment. At 24 h, incomplete drug release was observed for both silica systems; unprocessed SZ release was significantly greater than the extent of release from drug/silica samples (Table 4). Drug release from the porous and non-porous silica carriers was not significantly different at any of the dissolution time points.

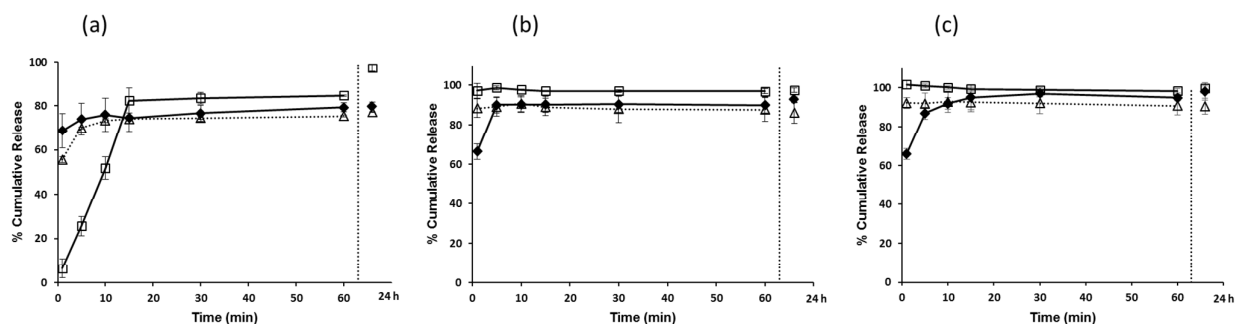


Figure 4. Dissolution profiles of SZ loaded SBA-15 (◆), Aerosil[®]200 (Δ) and unprocessed SZ (□) in (a) 0.1M HCl, (b) 0.1M HCl SDS 10mM and (c) 0.1M HCl SDS 50mM (n=3, Y error bars indicate standard deviation)

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

3.4.2. Sulphamethazine/Silica System in 0.1 M HCl/SDS Media

In vitro drug dissolution was investigated in the presence of surfactant (SDS) at the same concentrations investigated in the adsorption study (10 mM and 50 mM). The addition of the surfactant at low concentration (10 mM) significantly enhanced the rate and extent of drug release from both silica systems compared to dissolution in 0.1 M HCl media alone (Figure 4, Table 4). A further enhancement in the rate or extent of SZ release was not observed for the higher concentration of SDS (50 mM). Incomplete dissolution was observed for both porous and non-porous systems in the presence of 10 mM SDS (unprocessed drug dissolution reaches levels of 100% API release). Complete drug release was only observed for the drug/SBA-15 samples in 0.1 M HCl containing 50mM SDS.

3.5. Porosity Analysis of Recovered SBA-15 Following Dissolution

Pore size distributions of unprocessed and recovered SBA-15 samples are displayed in Figure 5. Changes in silica porosity can indicate a change in the quantity and distribution of bound molecules on the silica surface. A decrease in pore diameter and pore volume is evidence of the presence of drug/surfactant molecules in the pores or blocking the pores ²⁶. SBA-15 samples recovered after dissolution in 0.1 M HCl displayed a reduction in mesopore volume but not mesopore width. This finding supports the hypothesis that a fraction of the drug molecules remaining is distributed on the silica surface after dissolution rather than blocking pore openings. Samples exposed to media containing surfactant displayed the greatest reduction in mesopore volume and demonstrated a significant reduction in mesopore size. This suggests that SDS molecules can adsorb onto the silica surface and have the potential to deposit in the silica mesopores and block them.

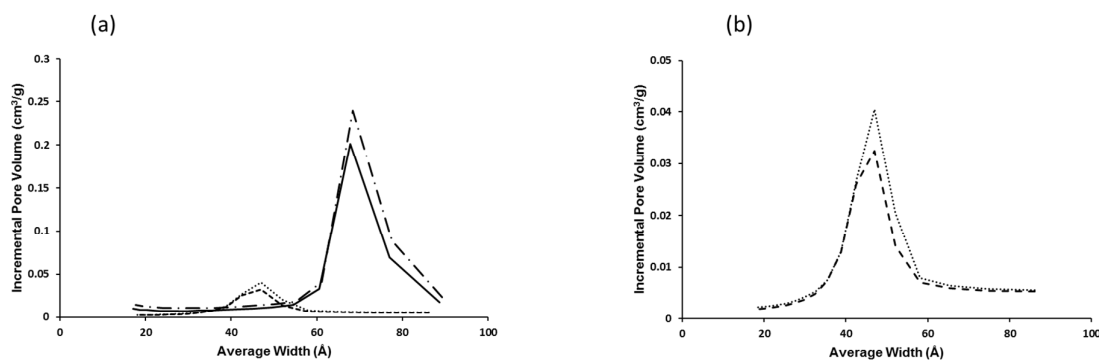


Figure 5. (a) Pore size distribution of unprocessed SBA-15 (dashed line with dot) and recovered SBA-15 samples after drug loading and dissolution in 0.1M HCl (black line), 0.1M HCl 10mM SDS (dotted line) and 0.1M HCl 50mM SDS (dashed line); (b) recovered SBA-15 samples after drug loading and dissolution in 0.1M HCl 10 mM SDS (dotted line) and in 0.1M HCl 50 mM SDS (dashed line)

3.6. Relating Dissolution Release Profiles to Adsorption Isotherms

The relationship between the quantity of SZ adsorbed on the silica surface at the end of the dissolution experiment and the estimated quantity of SZ adsorbed (calculated using the adsorption isotherm equations) was compared for the 0.1 M HCl media (Figure 6(a)). Figure 6(a) demonstrates that the quantity of drug that remains adsorbed to the mesoporous silica surface after dissolution is significantly higher than the predicted value. The amount retained per m² was considerably higher for the porous SBA-15 compared to non-porous Aerosil®. These results indicate that retention of drug molecules on the mesoporous silica surface was not simply due to an adsorption equilibrium between adsorbed drug and drug existing in solution in the dissolution media and that the porous architecture of silica influences the retention of drug on its surface.

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

In contrast to drug molecule adsorption behaviour, the quantity of SDS bound at the end of the dissolution experiment was not significantly different to the predicted values from the adsorption isotherms for the porous or non-porous systems (Figure 6 (b)).

The presence of SDS significantly reduces the amount of drug retained on the silica surface at the end the of the dissolution experiment (Figure 7). This is particularly evident for the mesoporous SBA-15. It is possible that the increased wettability of the media containing the surfactant provides enhanced access to drug binding sites, resulting in less drug retention.

Increasing the concentration of SDS does not result in a significant further reduction in drug retention. While the presence of surfactant increases the extent of SZ dissolution, incomplete release was observed in dissolution experiments for both silica substrates (except SBA-15 loaded samples in 50mM SDS). This indicates that some drug molecules are so tightly bound to particular silica binding sites that they are, in essence, ‘irreversibly bound’ under the dissolution experimental conditions.

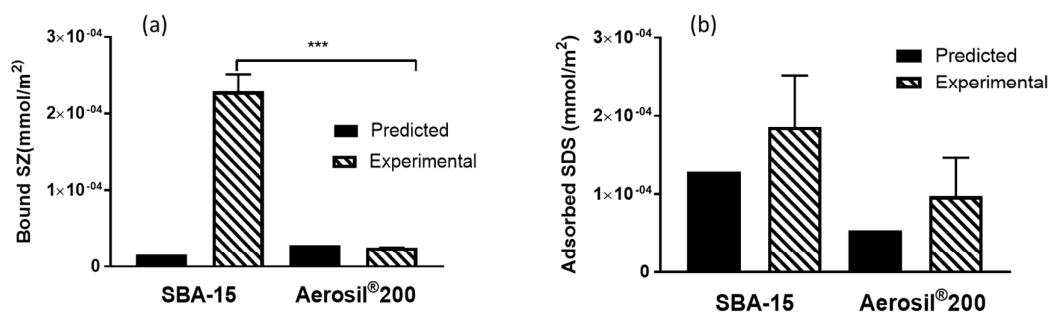


Figure 6. Comparison of (a) SZ and (b) SDS bound both predicted (from adsorption isotherm data) and experimentally determined after dissolution in 0.1M HCl (n=3, error bars indicate standard deviation, *** denotes p < 0.001)

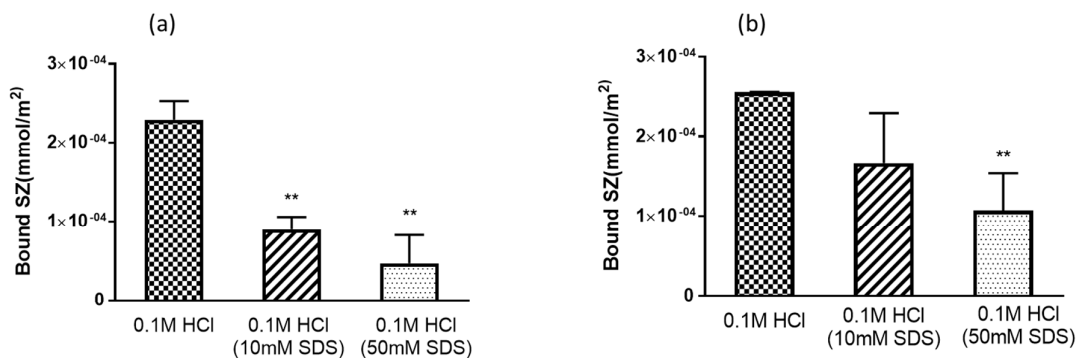


Figure 7. Comparison of the actual bound SZ fraction (mmol/m^2 silica) after dissolution in the three media investigated for (a) SBA-15 and (b) Aerosil[®] ($n=3$, error bars indicate standard deviation, ** denotes $p < 0.01$ of difference compared to amount bound in 0.1 M HCl)

443 5. DISCUSSION

444 In this study, two factors demonstrated a significant influence on drug release from silica
445 systems. The first factor was the influence of drug and surfactant adsorption onto the silica
446 surface. The second was the ability of the dissolution medium to wet the silica surface,
447 particularly the porous network of the mesoporous SBA-15.

448 Drug adsorption onto the silica surface was noted for both silica materials across all three
449 media investigated. The mesoporous material had a lower adsorbed drug fraction/m²
450 compared to the non-porous Aerosil®. This indicates that SZ molecules cannot access the
451 entirety of the mesoporous network. Mesoporous silica materials have a wide range of pore
452 sizes (between 2 – 50 nm)³. It is possible that adsorbed drug molecules could block smaller
453 pores preventing access to further drug binding sites located deeper in the porous
454 architecture. Additionally, porous binding sites may be different in terms of the number of
455 available sites/m² and/or binding affinity to those located on the surface, resulting in altered
456 drug adsorption levels compared to non-porous materials. Further evidence for this
457 hypothesis is observed in the porosity analysis which displays a reduced pore volume for the
458 drug loaded samples after dissolution in 0.1 M HCl, indicating bound drug molecules
459 remaining are occupying mesopores on the surface. This finding is interesting as it suggests
460 accessible surface area rather than specific surface area of the SBA-15 is as an important
461 parameter in drug loading and dissolution from these porous systems. Future studies should
462 examine the influence of mesoporous materials with different porous architectures on drug
463 adsorption and release from these formulations.

464 Adsorption isotherms for single component systems were fitted to the Langmuir and
465 Freundlich linearized equations. These two models have also been used successfully in other
466 studies investigating adsorption on silica substrates^{16, 27, 28}. The Langmuir model describes a

homogeneous surface which contains only one type of binding site²⁹. It emerged as the best-fit for drug binding onto the non-porous Aerosil®. In contrast, SZ adsorption onto mesoporous SBA-15 produced a Freundlich model best-fit correlation. The Freundlich model is an empirical model which describes a heterogeneous surface (a system which contains a range of binding sites with different binding affinities) and indicates that multi-layer adsorption of drug onto the porous SBA-15 surface exists³⁰. This observation agreed with a previous literature report which demonstrated that the Freundlich isotherm proved the best-fit for the absorption of a range of pharmaceuticals onto SBA-15¹⁶. The number of SZ binding sites on the surface (N_t) was lower for the mesoporous material. This is further evidence that the accessible surface area of the porous silica is an important parameter to consider for these formulations. The binding affinity (designated as a for the Langmuir isotherm and K_o for the Freundlich model) of drug to the surface is stronger for the non-porous Aerosil®. This is most likely a result of SBA-15's porous architecture as drug interactions with the surface could vary depending on the dimensions of the pores and silica surface chemistry.

The quantity of surfactant adsorbed onto both silica substrates was significantly similar in magnitude to the quantity of drug adsorbed under the same experimental conditions and concentration range (from adsorption isotherms, Figure 1(b) and Figure 2). This was determined by correlating drug and surfactant adsorption onto both silica surfaces (Section 3.3.2). Both molecules have a similar molecular mass (278.33g/mol for SZ and 288.372g/mol for SDS). SDS is an anionic surfactant and SZ has an aromatic amine functional group with a pK_a of 2.06 ± 0.30 . The isoelectric point of the silica surface has been measured as pH 2³¹. In 0.1M HCl, the results indicate that the more positively charged silica has a similar potential to attract both surfactant and drug molecules. Drug interaction with the silica surface is most likely a result of hydrogen bonding between the aromatic amine functional group and the silanol hydroxyl groups. Amine-silanol hydrogen bonding between drug molecules and the

silica surface has been reported previously in a study by Xue *et al*¹⁷. The interaction of the surfactant with the silica surface is not well understood. In this case, it is likely that the negatively charged head group interacts with the silica surface (which is slightly positively charged under these experimental conditions). It is possible that the SDS molecules adsorb in a multilayer hemi-micelle formation. This phenomenon has been described for cationic surfactant adsorption at the silica gel – water interface³². The nature of this surfactant – silica interaction requires further investigation.

The results of this study indicate that the retention of drug molecules on the mesoporous silica surface is not simply due to an equilibrium adsorption related to the concentration of drug in solution in the dissolution media. A certain fraction of the loaded drug molecules are bound very tightly or to sites which are inaccessible for the dissolution media. These findings reinforce the influence of the porous network in drug dissolution from these systems. While the quantity of loaded drug retained at the end of dissolution was greater than the predicted quantity, the amount of surfactant adsorbed was not significantly different when predicted and experimental values were compared. The surfactant was not loaded onto the silica material in the dissolution experiment. This observation indicates that the drug loading process utilised in this study (SC-CO₂ loading) is another factor to consider in determining drug adsorption/release behaviour. It has been reported in the literature that water molecules can adsorb onto silica by interacting with surface functional groups³³. It is possible that during drug loading under SC-CO₂ conditions, water that was bound to the silica surface was removed thus activating potential binding sites which would otherwise be unavailable in the mesoporous material. This could increase the bound drug fraction remaining at the end of dissolution as drug molecules are potentially more difficult to remove from these binding sites.

While both concentrations of SDS investigated were determined to be above the surfactant CMC in 0.1M HCl (0.8mM), drug solubility was only marginally enhanced in the dissolution media containing 50mM SDS. This is most likely due to the extent of incorporation of SZ (an acidic drug) into surfactant micelles which is dependent on the pK_a (acid dissociation constant) of the drug and the ionic nature of the surfactant³⁴. As the pK_a of the aromatic amine (2.06 ± 0.30) is only marginally above the pH, it is possible the drug is not fully protonated, reducing drug partitioning into anionic SDS micelles.

However, despite the marginal improvement in drug solubility, the addition of surfactant at both concentrations (10 mM and 50 mM) significantly enhanced the rate and extent of drug release from both porous and non-porous systems compared to dissolution in 0.1 M HCl alone. In this case, the improved wetting characteristics of the media in the presence of the surfactant is the most likely explanation for the improved dissolution profile. Surfactants decrease the solid/liquid surface tension³⁵ which could allow the dissolution media to access additional drug binding sites thus enhancing drug release. Superior release was observed for the non-porous Aerosil® at 1 min compared to SBA-15. This could be attributed to the time taken for the media to wet the pores. At 5 min, there is no significant difference in the extent of release between the two silica systems. This remains the case for the remainder of the experiment (24 h).

1
2
3 539
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

6. CONCLUSIONS

This study demonstrates that drug adsorption plays a role in the release of drug molecules from drug/silica systems. Adsorption isotherms proved useful for understanding drug release for non-porous silica formulations. However, adsorption behaviour does not explain the high quantity of drug retained on mesoporous formulations. The addition of sodium dodecyl sulphate to the dissolution media was shown to have a significant impact on sulphamethazine dissolution from both porous and non-porous silica systems. The study findings highlight the importance of considering drug and dissolution media interaction with the silica substrate and accessibility of dissolution media to the silica porous architecture when optimising drug release from drug/silica systems.

7. ACKNOWLEDGEMENTS

The authors would like to acknowledge Dr. Tom O' Mahony for his help with SC-CO₂ drug loading of samples. The authors also wish to acknowledge Glantreo Ltd. for supply of SBA-15 and Evonik Industries AG for supply of Aerosil[®]200. This article was funded by the Synthesis and Solid State Pharmaceutical Centre (SSPC) and Science Foundation Ireland (SFI) under grant number 12/RC/2275.

559 **8. REFERENCES**

- 560 1. Vallet-Regi, M.; Ramila, A.; Del Real, R.; Perez-Pariente, J. A new property of MCM-41: drug
561 delivery system. *Chemistry of Materials* **2001**, *13*, (2), 308-311.
- 562 2. Mellaerts, R.; Jammaer, J. A. G.; Van Speybroeck, M.; Chen, H.; Van Humbeeck, J.; Augustijns,
563 P.; Van den Mooter, G.; Martens, J. A. Physical state of poorly water soluble therapeutic molecules
564 loaded into SBA-15 ordered mesoporous silica carriers: A case study with itraconazole and
565 ibuprofen. *Langmuir* **2008**, *24*, (16), 8651-8659.
- 566 3. McCarthy, C. A.; Ahern, R. J.; Dontireddy, R.; Ryan, K. B.; Crean, A. M. Mesoporous silica
567 formulation strategies for drug dissolution enhancement: a review. *Expert opinion on drug delivery*
568 **2016**, *13*, (1), 93-108.
- 569 4. Kresge, C.; Leonowicz, M.; Roth, W.; Vartuli, J.; Beck, J. Ordered mesoporous molecular
570 sieves synthesized by a liquid-crystal template mechanism. *nature* **1992**, *359*, (6397), 710-712.
- 571 5. Azaïs, T.; Tourné-Péteilh, C.; Aussenac, F.; Baccile, N.; Coelho, C.; Devoisselle, J.-M.;
572 Babonneau, F. Solid-state NMR study of ibuprofen confined in MCM-41 material. *Chemistry of*
573 *materials* **2006**, *18*, (26), 6382-6390.
- 574 6. Charnay, C.; Bégu, S.; Tourné-Péteilh, C.; Nicole, L.; Lerner, D. A.; Devoisselle, J. M. Inclusion
575 of ibuprofen in mesoporous templated silica: drug loading and release property. *European Journal of*
576 *Pharmaceutics and Biopharmaceutics* **2004**, *57*, (3), 533-540.
- 577 7. Shen, S. C.; Ng, W. K.; Chia, L.; Dong, Y. C.; Tan, R. B. Stabilized amorphous state of
578 ibuprofen by co-spray drying with mesoporous SBA-15 to enhance dissolution properties. *Journal of*
579 *pharmaceutical sciences* **2010**, *99*, (4), 1997-2007.
- 580 8. Ahern, R. J.; Hanrahan, J. P.; Tobin, J. M.; Ryan, K. B.; Crean, A. M. Comparison of
581 fenofibrate-mesoporous silica drug-loading processes for enhanced drug delivery. *European Journal*
582 *of Pharmaceutical Sciences* **2013**, *50*, (3-4), 400-409.
- 583 9. Limnell, T.; Santos, H. A.; Mäkilä, E.; Heikkilä, T.; Salonen, J.; Murzin, D. Y.; Kumar, N.;
584 Laaksonen, T.; Peltonen, L.; Hirvonen, J. Drug delivery formulations of ordered and nonordered
585 mesoporous silica: comparison of three drug loading methods. *Journal of pharmaceutical sciences*
586 **2011**, *100*, (8), 3294-3306.
- 587 10. Waters, L. J.; Hussain, T.; Parkes, G.; Hanrahan, J. P.; Tobin, J. M. Inclusion of fenofibrate in a
588 series of mesoporous silicas using microwave irradiation. *European Journal of Pharmaceutics and*
589 *Biopharmaceutics* **2013**, *85*, (3), 936-941.
- 590 11. McCarthy, C. A.; Faisal, W.; O'Shea, J. P.; Murphy, C.; Ahern, R. J.; Ryan, K. B.; Griffin, B. T.;
591 Crean, A. M. In vitro dissolution models for the prediction of in vivo performance of an oral
592 mesoporous silica formulation. *Journal of Controlled Release* **2017**, *250*, 86-95.
- 593 12. Van Speybroeck, M.; Mellaerts, R.; Mols, R.; Thi, T. D.; Martens, J. A.; Van Humbeeck, J.;
594 Annaert, P.; Van den Mooter, G.; Augustijns, P. Enhanced absorption of the poorly soluble drug
595 fenofibrate by tuning its release rate from ordered mesoporous silica. *European Journal of*
596 *Pharmaceutical Sciences* **2010**, *41*, (5), 623-630.
- 597 13. Bukara, K.; Schueller, L.; Rosier, J.; Daems, T.; Verheyden, L.; Eelen, S.; Martens, J. A.; Van
598 den Mooter, G.; Bugarski, B.; Kiekens, F. In Vivo Performance of Fenofibrate Formulated With
599 Ordered Mesoporous Silica Versus 2-Marketed Formulations: A Comparative Bioavailability Study in
600 Beagle Dogs. *Journal of Pharmaceutical Sciences* **2016**, *105*, (8), 2381-2385.
- 601 14. Van Speybroeck, M.; Barillaro, V.; Thi, T. D.; Mellaerts, R.; Martens, J.; Van Humbeeck, J.;
602 Vermant, J.; Annaert, P.; Van den Mooter, G.; Augustijns, P. Ordered mesoporous silica material
603 SBA-15: A broad-spectrum formulation platform for poorly soluble drugs. *Journal of pharmaceutical*
604 *sciences* **2009**, *98*, (8), 2648-2658.
- 605 15. Ahern, R. J.; Crean, A. M.; Ryan, K. B. The influence of supercritical carbon dioxide (SC-CO₂)
606 processing conditions on drug loading and physicochemical properties. *International*
607 *journal of pharmaceutics* **2012**, *439*, (1), 92-99.

16. Bui, T. X.; Choi, H. Adsorptive removal of selected pharmaceuticals by mesoporous silica SBA-15. *Journal of Hazardous Materials* **2009**, *168*, (2), 602-608.
17. Xue, J. M.; Shi, M. PLGA/mesoporous silica hybrid structure for controlled drug release. *Journal of Controlled Release* **2004**, *98*, (2), 209-217.
18. Leuner, C.; Dressman, J. Improving drug solubility for oral delivery using solid dispersions. *European Journal of Pharmaceutics and Biopharmaceutics* **2000**, *50*, (1), 47-60.
19. U.S. Food and Drug Administration Dissolution Methods. <http://www.accessdata.fda.gov/scripts/cder/dissolution/> (02/03/2017),
20. Swearingen, R. A.; Chen, X.; Petersen, J. S.; Riley, K. S.; Wang, D.; Zhorov, E. Determination of the binding parameter constants of Renagel® capsules and tablets utilizing the Langmuir approximation at various pH by ion chromatography. *Journal of pharmaceutical and biomedical analysis* **2002**, *29*, (1), 195-201.
21. García-Calzón, J. A.; Díaz-García, M. E. Characterization of binding sites in molecularly imprinted polymers. *Sensors and Actuators B: Chemical* **2007**, *123*, (2), 1180-1194.
22. Ding, S.; Chen, J.; Jiang, H.; He, J.; Shi, W.; Zhao, W.; Shen, J. Application of Quantum Dot-Antibody Conjugates for Detection of Sulfamethazine Residue in Chicken Muscle Tissue. *Journal of Agricultural and Food Chemistry* **2006**, *54*, (17), 6139-6142.
23. Im, S. H.; Ryoo, J. J. Characterization of sodium laureth sulfate by reversed-phase liquid chromatography with evaporative light scattering detection and ¹H nuclear magnetic resonance spectroscopy. *Journal of Chromatography A* **2009**, *1216*, (12), 2339-2344.
24. Barrett, E. P.; Joyner, L. G.; Halenda, P. P. The determination of pore volume and area distributions in porous substances. I. Computations from nitrogen isotherms. *J. Am. chem. soc* **1951**, *73*, (1), 373-380.
25. Rangel-Yagui, C. O.; Pessoa Jr, A.; Tavares, L. C. Micellar solubilization of drugs. *J Pharm Pharm Sci* **2005**, *8*, (2), 147-163.
26. Izquierdo-Barba, I.; Martínez, Á.; Doadrio, A. L.; Pérez-Pariente, J.; Vallet-Regí, M. Release evaluation of drugs from ordered three-dimensional silica structures. *European Journal of Pharmaceutical Sciences* **2005**, *26*, (5), 365-373.
27. Andersson, J.; Rosenholm, J.; Areva, S.; Lindén, M. Influences of material characteristics on ibuprofen drug loading and release profiles from ordered micro- and mesoporous silica matrices. *Chemistry of Materials* **2004**, *16*, (21), 4160-4167.
28. Smirnova, I.; Mamic, J.; Arlt, W. Adsorption of Drugs on Silica Aerogels. *Langmuir* **2003**, *19*, (20), 8521-8525.
29. Umpleby, R. J.; Baxter, S. C.; Chen, Y.; Shah, R. N.; Shimizu, K. D. Characterization of molecularly imprinted polymers with the Langmuir-Freundlich isotherm. *Analytical chemistry* **2001**, *73*, (19), 4584-4591.
30. Umpleby, R. J.; Baxter, S. C.; Bode, M.; Berch Jr, J. K.; Shah, R. N.; Shimizu, K. D. Application of the Freundlich adsorption isotherm in the characterization of molecularly imprinted polymers. *Analytica Chimica Acta* **2001**, *435*, (1), 35-42.
31. Kosmulski, M. Positive Electrokinetic Charge of Silica in the Presence of Chlorides. *Journal of Colloid and Interface Science* **1998**, *208*, (2), 543-545.
32. Gao, Y.; Du, J.; Gu, T. Hemimicelle formation of cationic surfactants at the silica gel-water interface. *Journal of the Chemical Society, Faraday Transactions 1: Physical Chemistry in Condensed Phases* **1987**, *83*, (8), 2671-2679.
33. Vigil, G.; Xu, Z.; Steinberg, S.; Israelachvili, J. Interactions of Silica Surfaces. *Journal of Colloid and Interface Science* **1994**, *165*, (2), 367-385.
34. Park, S.-H.; Choi, H.-K. The effects of surfactants on the dissolution profiles of poorly water-soluble acidic drugs. *International Journal of Pharmaceutics* **2006**, *321*, (1-2), 35-41.
35. Rosen, M. J.; Kunjappu, J. T., *Surfactants and interfacial phenomena*. John Wiley & Sons: 2012.

