

Title	Structural and electrical analysis of the atomic layer deposition of HfO ₂ /n-In _{0.53} Ga _{0.47} As capacitors with and without an Al ₂ O ₃ interface control layer
Authors	O'Mahony, Aileen; Monaghan, Scott; Provenzano, G.; Povey, Ian M.; Nolan, M. G.; O'Connor, Éamon; Cherkaoui, Karim; Newcomb, Simon B.; Crupi, Felice; Hurley, Paul K.; Pemble, Martyn E.
Publication date	2010
Original Citation	O'Mahony, A., Monaghan, S., Provenzano, G., Povey, I. M., Nolan, M. G., O'Connor, É., Cherkaoui, K., Newcomb, S. B., Crupi, F., Hurley, P. K. and Pemble, M. E. (2010) 'Structural and electrical analysis of the atomic layer deposition of HfO ₂ /n-In _{0.53} Ga _{0.47} As capacitors with and without an Al ₂ O ₃ interface control layer', Applied Physics Letters, 97(5), pp. 052904. doi: 10.1063/1.3473773
Type of publication	Article (peer-reviewed)
Link to publisher's version	http://aip.scitation.org/doi/abs/10.1063/1.3473773 - 10.1063/1.3473773
Rights	© 2010 American Institute of Physics. This article may be downloaded for personal use only. Any other use requires prior permission of the author and AIP Publishing. The following article appeared in O'Mahony, A., Monaghan, S., Provenzano, G., Povey, I. M., Nolan, M. G., O'Connor, É., Cherkaoui, K., Newcomb, S. B., Crupi, F., Hurley, P. K. and Pemble, M. E. (2010) 'Structural and electrical analysis of the atomic layer deposition of HfO ₂ /n-In _{0.53} Ga _{0.47} As capacitors with and without an Al ₂ O ₃ interface control layer', Applied Physics Letters, 97(5), pp. 052904 and may be found at http://aip.scitation.org/doi/abs/10.1063/1.3473773
Download date	2025-05-21 05:11:37
Item downloaded from	https://hdl.handle.net/10468/4337



UCC

University College Cork, Ireland
Coláiste na hOllscoile Corcaigh

Structural and electrical analysis of the atomic layer deposition of $\text{HfO}_2/n\text{-In}_{0.53}\text{Ga}_{0.47}\text{As}$ capacitors with and without an Al_2O_3 interface control layer

A. O'Mahony¹, S. Monaghan, G. Provenzano, I. M. Povey, M. G. Nolan, É. O'Connor, K. Cherkaoui, S. B. Newcomb, F. Crupi, P. K. Hurley, and M. E. Pemble

Citation: *Appl. Phys. Lett.* **97**, 052904 (2010); doi: 10.1063/1.3473773

View online: <http://dx.doi.org/10.1063/1.3473773>

View Table of Contents: <http://aip.scitation.org/toc/apl/97/5>

Published by the [American Institute of Physics](#)

Articles you may be interested in

1-nm-capacitance-equivalent-thickness $\text{HfO}_2/\text{Al}_2\text{O}_3/\text{InGaAs}$ metal-oxide-semiconductor structure with low interface trap density and low gate leakage current density

Applied Physics Letters **100**, 132906 (2012); 10.1063/1.3698095

Electrical analysis of three-stage passivated $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$ capacitors with varying HfO_2 thicknesses and incorporating an Al_2O_3 interface control layer

Journal of Vacuum Science & Technology B, Nanotechnology and Microelectronics: Materials, Processing, Measurement, and Phenomena **29**, 01A807 (2011); 10.1116/1.3532826



CiSE magazine is an innovative blend.

The advertisement features a stylized circuit board design with various components and lines. Labels for 'COMPUTING', 'ENGINEERING', and 'SCIENCE' are placed along the circuit lines. In the bottom right corner, there is a small image of the magazine cover, which has the title 'computing SCIENCE & ENGINEERING' and the subtitle 'EXPLORING OUR SOLAR SYSTEM'.

Structural and electrical analysis of the atomic layer deposition of $\text{HfO}_2/n\text{-In}_{0.53}\text{Ga}_{0.47}\text{As}$ capacitors with and without an Al_2O_3 interface control layer

A. O'Mahony,^{1,a)} S. Monaghan,¹ G. Provenzano,^{1,2} I. M. Povey,¹ M. G. Nolan,¹ É. O'Connor,¹ K. Cherkaoui,¹ S. B. Newcomb,³ F. Crupi,² P. K. Hurley,¹ and M. E. Pemble¹

¹Tyndall National Institute, University College Cork, Lee Maltings, Prospect Row, Cork, Ireland

²Dipartimento di Elettronica, Informatica e Sistemistica, Università della Calabria, Via P. Bucci, 41C I-87036 Arcavacata di Rende (CS), Italy

³Glebe Laboratories, Glebe Scientific Ltd., Newport, County Tipperary, Ireland

(Received 30 March 2010; accepted 25 June 2010; published online 6 August 2010)

High mobility III-V substrates with high- k oxides are required for device scaling without loss of channel mobility. Interest has focused on the *self-cleaning* effect on selected III-V substrates during atomic layer deposition of Al_2O_3 . A thin (~ 1 nm) Al_2O_3 interface control layer is deposited on $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$ prior to HfO_2 growth, providing the benefit of *self-cleaning* and improving the interface quality by reducing interface state defect densities by $\sim 50\%$ while maintaining scaling trends. Significant reductions in leakage current density and increased breakdown voltage are found, indicative of a band structure improvement due to the reduction/removal of the $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$ native oxides. © 2010 American Institute of Physics. [doi:10.1063/1.3473773]

A critical technological challenge in the integration of high k -dielectrics on III-V channels is the control of the high- k /III-V interface. Although the interfacial chemistry of the high- k /Si system is similar to the SiO_2/Si system,¹ the high- k /III-V system is more complex, due to competition between the various native oxide species at the interface,² resulting in growth of a poor quality interfacial layer.^{3–6} In recent work,³ reductions in interface state defect densities (D_{it}) were achieved by pre-treatment of the $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$ surface prior to atomic layer deposition (ALD) of HfO_2 [$k \sim 16\text{--}25$, band gap (E_g) $\sim 5.8\text{--}6.0$ eV].^{7–9} The native oxides of $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$ (Ga_2O_3 , In_2O_3 , and As_2O_3) have low band gaps (3.6–4.8 eV) (Refs. 2 and 9) and k -values of 8–10 when relating the reported^{9,10} k -value for Ga_2O_3 and In_2O_3 with the approximate refractive indices ($n \sim 1.9$ for all)² through the equation $n^2 \propto \epsilon k$ and the Moss Inverse Law¹¹ for the refractive index, k -value and energy band gap. They are detrimental to the band structure of high- k /III-V devices by increasing the leakage current and creating potential wells in the native oxide layer between the high- k oxide and the substrate. The *self-cleaning* Al_2O_3 ALD process is reported to reduce or remove the III-V native oxides.^{12–15} However, devices employing Al_2O_3 ($k \sim 8.6\text{--}11.6$, $E_g \sim 8.8$ eV) (Refs. 8, 9, and 12) as the gate oxide are limited for scaling due to its low k -value.

In this work, the structural and electrical properties of Pd/ $\text{HfO}_2/n\text{-In}_{0.53}\text{Ga}_{0.47}\text{As}$ devices (HfO_2 : nominal thickness ~ 3 , ~ 4 , and ~ 5 nm) with/without an ~ 1 nm Al_2O_3 interface control layer (ICL), are examined using high resolution transmission electron microscopy (HR-TEM) and current/capacitance/conductance versus voltage measurements (JV, CV, and GV, respectively). The devices are labeled: $s1_3$, $s1_4$, $s1_5$ (e.g., sample, ~ 1 nm Al_2O_3 , ~ 5 nm HfO_2 is labeled $s1_5$). As a control, devices were fabricated without the Al_2O_3 ICL [nominal ~ 5 nm HfO_2 only (label:

$s0_5$]]. The motivation for this work is: (i) to detect any improvement in the quality and structure of the interface using the bilayer approach; (ii) to investigate if an Al_2O_3 ICL improves the electrical performance of devices by modifying the metal-oxide-semiconductor (MOS) band structure; (iii) to determine if scaling is possible with an Al_2O_3 ICL using reducing thicknesses of HfO_2 .

The ~ 2 μm n -type ($S: \sim 4 \times 10^{17}$ cm^{-3}) $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$ channels had a ~ 0.1 μm InP buffer layer ($S: \sim 2 \times 10^{18}$ cm^{-3}) on a ~ 350 μm InP substrate ($S: 3\text{--}8 \times 10^{18}$ cm^{-3}). All $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$ layers were grown by MOVPE. An *ex situ* three-stage surface pre-treatment process [HCl , NH_4OH , and $(\text{NH}_4)_2\text{S}$] was performed on the $n\text{-In}_{0.53}\text{Ga}_{0.47}\text{As}/\text{InP}$ substrates which has previously been shown to be beneficial to device performance.³ The Al_2O_3 and HfO_2 layers were deposited in a Cambridge NanoTech Fiji F200LLC ALD system, at 250 °C. The ALD of Al_2O_3 and HfO_2 employed alternating pulses of TMA [$\text{Al}(\text{CH}_3)_3$]/ H_2O and tetrakis(ethylmethylamino)hafnium (TEMAH) $\{\text{Hf}[\text{N}(\text{C}_2\text{H}_5)(\text{CH}_3)]_4\}/\text{H}_2\text{O}$, respectively. MOS structures were completed by vacuum evaporation of ~ 200 nm of Pd at a deposition rate of 2.5 Å/s using a lift-off process. No ohmic back contacts were formed.

Figures 1(a) and 1(b) present cross-sectional HR-TEM micrographs of $s1_5$ and $s0_5$, confirming the physical oxide and nominal thicknesses are in close agreement: $s1_5$ [Fig. 1(a)] has a ~ 5.3 nm HfO_2 layer, and a ~ 1.2 nm Al_2O_3 layer. $s0_5$ [Fig. 1(b)], has a ~ 4.9 nm HfO_2 layer. All oxide layers are amorphous. Comparison between Figs. 1(a) and 1(b) shows a ~ 0.7 nm native oxide layer at the high- $k/n\text{-In}_{0.53}\text{Ga}_{0.47}\text{As}$ interface when no Al_2O_3 ICL is deposited, which is indicative of an Al_2O_3 *self-cleaning* effect on the native oxide, for sample $s1_5$.

Figure 2(a) presents a cross-sectional HR-TEM micrograph of $s1_3$. The physical thicknesses of HfO_2 and Al_2O_3 are ~ 3.2 nm and ~ 1.2 nm, respectively. Figure 2(b), a plan-view HR-TEM micrograph for sample $s1_5$, reveals the epitaxial 2 μm $n\text{-In}_{0.53}\text{Ga}_{0.47}\text{As}$ layer to be defect-free,

^{a)}Electronic mail: aileen.omahony@tyndall.ie.

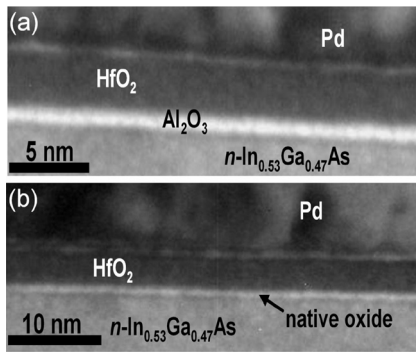


FIG. 1. Cross-sectional HR-TEM micrographs of (a) *s1_5*, with ~ 5.3 nm HfO₂ and ~ 1.1 nm Al₂O₃ and (b) *s0_5*, with ~ 4.9 nm HfO₂ and a ~ 0.7 nm native oxide layer.

with an associated negligible root mean square (rms) surface roughness of <1 nm.

Figure 3 shows (a) JV responses and (b) the measured 1 kHz CV responses, along with the simulated¹⁶ CV curves for all samples. The inset to Fig. 3(a) shows the capacitance equivalent thickness (CET) versus HR-TEM extracted HfO₂ physical thickness plot for the bilayer sample set (*s1_3*, *s1_4*, *s1_5*), with a linear fit. Figure 3(a), when assessing the bilayer sample set only, shows that leakage current density increases with reducing HfO₂ thickness, and the dielectric breakdown voltage increases with increasing HfO₂ thickness. This is expected for a dominant quantum-mechanical (QM) tunneling leakage mechanism with similar energy barrier height and shape, and for a dominant electrically-controlled oxide breakdown process.¹⁷ However, the leakage current density response for sample *s0_5* is substantially higher (approximately three orders of magnitude at 3 V) than for sample *s1_5*, showing that the absence of an Al₂O₃ ICL changes the tunneling barrier height/shape to conduction beyond a thickness-dependency regime only and introduces an additional, highly temperature-dependent (not shown), trap-assisted conduction mechanism that adds magnitude and fluctuation to the response.¹⁸ Figure 3(b) shows that the accumulation maximum capacitance at 2 V scales correctly with oxide thickness for the bilayer sample set. The simulated curves confirm that surface accumulation is achieved at 2 V for all samples.³ The accumulation maximum capacitance is greater for the measured data compared to the simulated data, showing the existence of a QM correction factor. This difference could be due to additional states inside the conduction band at the oxide/*n*-In_{0.53}Ga_{0.47}As

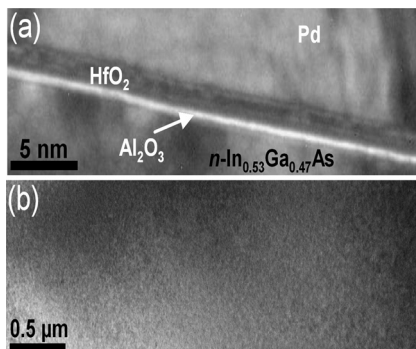


FIG. 2. HR-TEM micrographs of (a) *s1_3* (cross-sectional), with ~ 3.2 nm HfO₂ and ~ 1.2 nm Al₂O₃; (b) *s1_5* (plan-view) shows a defect free *n*-In_{0.53}Ga_{0.47}As substrate layer.

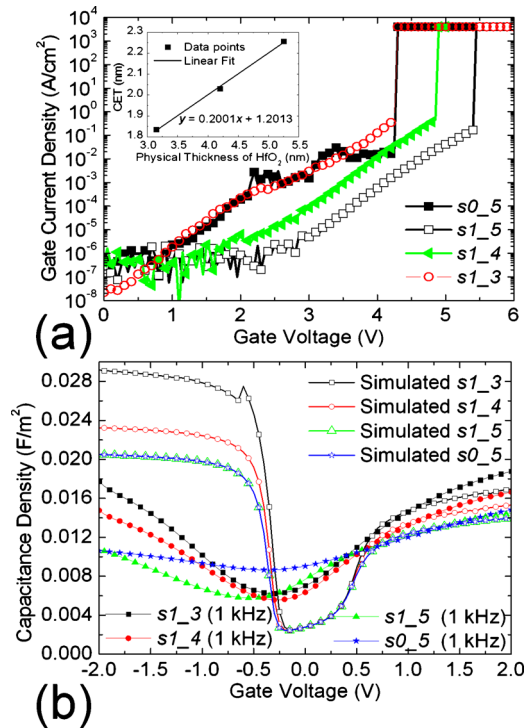


FIG. 3. (Color online) (a) JV responses for all samples, with significantly lower leakage for the *s1_5* (Al₂O₃ ICL) devices, compared to *s0_5* devices. (b) Measured and simulated (from the 1D Poisson–Schrödinger solver) 1 kHz CV responses for all samples. Inset to (a) shows the CET vs physical thickness with a linear fit.

interface,¹⁹ and/or charge quantization leading to X and L satellite valley occupation in the conduction band.²⁰ We see a similar maximum accumulation capacitance for the ~ 5 nm HfO₂ samples with/without Al₂O₃ (*s1_5* and *s0_5*, respectively), showing that the overall equivalent oxide thickness of these oxide stacks are similar. The observed variation in the maximum accumulation capacitance (~ 0.003 F/m²) for sample *s0_5* is likely due to native oxide layer thickness variation not observable by HR-TEM. Given the large difference in leakage current density between these samples (*s1_5* and *s0_5*), it is evident that the Al₂O₃ ICL substantially reduces the native oxide layer thickness while increasing the barrier height to electron tunneling from the In_{0.53}Ga_{0.47}As conduction band. The linear fit of the inset to Fig. 3(a) shows that the reduction in HfO₂ thickness for the bilayer structures produces the required scaling trend. This linear fit can be used to extract an intercept CET value, which has contributions from Al₂O₃, any underlying native oxide layer (if present), and the QM correction contribution from the *n*-In_{0.53}Ga_{0.47}As accumulation layer. HR-TEM [Figs. 1(a), 1(b), and 2(a)], in combination with the electrical results [Figs. 3(a), 3(b), 4(a), and 4(b)], indicate that no substantive underlying native oxide layer is present for the bilayer sample set. Assuming this is the case and since we can extract the contributions from Al₂O₃, we can thereby determine a QM correction factor of ~ 0.7 nm. From the slope of the linear fit we can estimate the HfO₂ *k*-value to be ~ 20 , which is within the reported range.⁷ Reasonable assumptions used were: (i) the *k*-value of both Al₂O₃ and any native oxide^{2,10,12} layer is ~ 9 and (ii) the physical thicknesses used for sample *s1_4* are nominal thicknesses proportionally corrected using HR-TEM/nominal-thickness ratios and ALD cycle ratios for other samples. The absence of an underlying native oxide

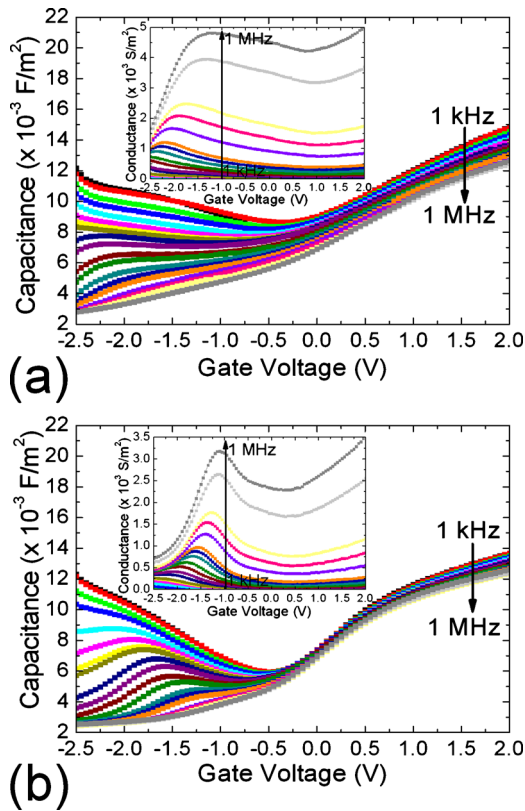


FIG. 4. (Color online) (a) and (b) show CV responses (20 frequencies; 1 kHz–1 MHz) for samples $s0_5$ and $s1_5$, respectively. The insets to (a) and (b) show the corresponding GV responses.

layer, evidenced by HR-TEM in combination with the electrical results, indicates that the Al_2O_3 is likely to be removing the native oxides via the *self-cleaning* process.

Figures 4(a) and 4(b) show the multifrequency CV responses for samples $s0_5$ and $s1_5$, respectively. The insets to Figs. 4(a) and 4(b) show the corresponding GV responses. We observe an increased D_{it} response in both the CV and GV profiles for sample $s0_5$ when compared to the equivalent response for sample $s1_5$, which includes (over the entire voltage range) an increased CV and GV stretch-out and frequency dispersion. In the voltage range -1 to 0.25 V, the absence of minority carriers is assumed, corresponding to the depletion regime. An approximation to the Conductance Method²¹ indicates that samples $s0_5$ and $s1_5$ have estimated D_{it} values of $\sim 8 \times 10^{12} \text{ cm}^{-2} \text{ eV}^{-1}$ and $\sim 4 \times 10^{12} \text{ cm}^{-2} \text{ eV}^{-1}$, respectively. Due to the absence of distinct equivalent parallel conductance (G_p/ω) peaks as observed in SiO_2/Si systems, this is derived assuming zero standard deviation in band bending using values of G_p/ω at -1 V and taken at 30 kHz. While it is noted that the G_p/ω magnitudes may be affected by the approximation conditions, and any possible minority carrier contribution, the relative difference provides a valid estimate. There is approximately a 50% reduction in D_{it} when including an Al_2O_3 ICL.

In summary, it is found that the inclusion of a thin Al_2O_3 ICL (~ 1 nm) at the $\text{HfO}_2/\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$ interface improves the structural and electrical properties of $\text{Pd}/\text{HfO}_2/n\text{-In}_{0.53}\text{Ga}_{0.47}\text{As}$ devices. The inclusion of the Al_2O_3 ICL improves the breakdown voltage and reduces leakage current densities by approximately three orders of

magnitude at 3 V by increasing the barrier height to tunneling from the $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$ conduction band into the oxide. No apparent native oxide layer is observed at the high- $k/\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$ interface when using an Al_2O_3 ICL, suggesting that the Al_2O_3 ALD process is *self-cleaning* the $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$ native oxides. Comparing the electrical performance for the bilayer samples with different HfO_2 thicknesses we find that device scaling trends can be achieved. Combining the structural and electrical results we find a QM correction factor of ~ 0.7 nm. The inclusion of an ICL causes an approximate 50% reduction in D_{it} , thereby improving the quality of the interface.

The authors thank Dan O'Connell, Tyndall National Institute, for sample processing; the ERASMUS program; Science Foundation Ireland's FORME Strategic Research Cluster (Grant No. 07/SRC/I1172); IRCSET; and Intel Ireland for the award and support (inc. Roger E. Nagle) of a scholarship to A. O'M.

- ¹P. K. Hurley, K. Cherkaoui, É. O'Connor, M. C. Lemme, H. D. B. Gottlob, M. Schmidt, S. Hall, Y. Lu, O. Buiu, B. Raeissi, J. Piscator, O. Engstrom, and S. B. Newcomb, *J. Electrochem. Soc.* **155**, G13 (2008).
- ²C. W. Wilmsen, *Physics and Chemistry of III-V Compound Semiconductor Interfaces* (Plenum, New York, 1985).
- ³É. O'Connor, S. Monaghan, R. D. Long, A. O'Mahony, I. M. Povey, K. Cherkaoui, M. E. Pemble, G. Brammertz, M. Heyns, S. B. Newcomb, V. V. Afanas'ev, and P. K. Hurley, *Appl. Phys. Lett.* **94**, 102902 (2009).
- ⁴N. Goel, P. Majhi, C. O. Chui, W. Tsai, D. Choi, and J. S. Harris, *Appl. Phys. Lett.* **89**, 163517 (2006).
- ⁵É. O'Connor, R. D. Long, K. Cherkaoui, K. K. Thomas, F. Chalvet, I. M. Povey, M. E. Pemble, P. K. Hurley, B. Brennan, G. Hughes, and S. B. Newcomb, *Appl. Phys. Lett.* **92**, 022902 (2008).
- ⁶W. Tsai, N. Goel, S. Koveshnikov, P. Majhi, and W. Wang, *Microelectron. Eng.* **86**, 1540 (2009).
- ⁷K. Kukli, J. Niinistö, A. Tamm, J. Lu, M. Ritala, M. Leskelä, M. Putkonen, L. Niinistö, F. Song, P. Williams, and P. N. Heys, *Microelectron. Eng.* **84**, 2010 (2007).
- ⁸J. Robertson and B. Falabretti, *Mater. Sci. Eng., B* **135**, 267 (2006).
- ⁹D. P. Norton, *Mater. Sci. Eng. R.* **43**, 139 (2004).
- ¹⁰M. Passlack, R. Droopad, P. Fejes, and L. Wang, *IEEE Electron Device Lett.* **30**, 2 (2009).
- ¹¹T. S. Moss, *Proc. Phys. Soc. London, Sect. B* **63**, 167 (1950).
- ¹²P. D. Ye, G. D. Wilk, B. Yang, J. Kwo, S. N. G. Chu, S. Nakahara, H.-J. L. Gossman, J. P. Mannaerts, M. Hong, K. K. Ng, and J. Bude, *Appl. Phys. Lett.* **83**, 180 (2003).
- ¹³M. M. Frank, G. D. Wilk, D. Starodub, T. Gustafsson, E. Garfunkel, Y. J. Chabal, J. Grazul, and D. A. Miller, *Appl. Phys. Lett.* **86**, 152904 (2005).
- ¹⁴C. L. Hinkle, A. M. Sonnet, E. M. Vogel, S. McDonnell, G. J. Hughes, M. Milojevic, B. Lee, F. S. Aguirre-Tostado, K. J. Choi, H. C. Kim, J. Kim, and R. M. Wallace, *Appl. Phys. Lett.* **92**, 071901 (2008).
- ¹⁵B. Brennan, M. Milojevic, H. C. Kim, P. K. Hurley, J. Kim, G. Hughes, and R. M. Wallace, *Electrochem. Solid-State Lett.* **12**, H205 (2009).
- ¹⁶Professor G. Snider, University of Notre Dame, one-dimensional (1D) Poisson-Schrödinger solver, parameters used with HR-TEM oxide thicknesses; Al_2O_3 : $k=9$, $E_g=8.8$ eV, $\Delta E_c=3.45$ eV; HfO_2 : $k=20$, $E_g=6.0$ eV, and $\Delta E_c=2.25$ eV; $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$ native oxide: $k=9$, $E_g=4.1$ eV, $\Delta E_c=1.5$ eV. InP/ $\text{In}_{0.53}\text{Ga}_{0.47}\text{As}$ thickness/doping as specified. Temperature=300 K.
- ¹⁷S. M. Sze, *Physics of Semiconductor Devices*, 2nd ed. (Wiley, New York, 1981).
- ¹⁸F. Crupi, G. Giusi, G. Iannaccone, P. Magnone, C. Pace, E. Simoen, and C. Claeys, *J. Appl. Phys.* **106**, 073710 (2009).
- ¹⁹G. Brammertz, H.-C. Lin, M. Caymax, M. Meuris, M. Heyns, and M. Passlack, *Appl. Phys. Lett.* **95**, 202109 (2009).
- ²⁰T. P. O'Regan, P. K. Hurley, B. Sorée, and M. V. Fischetti, *Appl. Phys. Lett.* **96**, 213514 (2010).
- ²¹E. H. Nicollian and J. R. Brews, *MOS Physics and Technology* (Wiley, New York, 1982).