

Title	MXene nanosheet/organics superlattice for flexible thermoelectrics
Authors	Wang, Zhiwen;Chen, Mengran;Cao, Zhining;Liang, Jia;Liu, Zhenguo;Xuan, Yuxue;Pan, Lin;Razeeb, Kafil M.;Wang, Yifeng;Wan, Chunlei;Zong, Peng-an
Publication date	2022-11-01
Original Citation	Wang, Z., Chen, M., Cao, Z., Liang, J., Liu, Z., Xuan, Y., Pan, L., Razeeb, K. M., Wang, Y., Wan, C. and Zong, P. (2022) 'MXene nanosheet/organics superlattice for flexible thermoelectrics', ACS Applied Nano Materials. doi: 10.1021/acsanm.2c03813
Type of publication	Article (peer-reviewed)
Link to publisher's version	10.1021/acsanm.2c03813
Rights	© 2022, American Chemical Society. This document is the Accepted Manuscript version of a Published Work that appeared in final form in ACS Applied Nano Materials, after technical editing by the publisher. To access the final edited and published work see: <a href="https://doi.org/10.1021/acsanm.2c03813">https://doi.org/10.1021/acsanm.2c03813</a>
Download date	2024-02-24 00:02:53
Item downloaded from	<a href="https://hdl.handle.net/10468/13883">https://hdl.handle.net/10468/13883</a>

# Supporting Information

## MXene Nanosheet/Organic Superlattice for Flexible Thermoelectrics

Zhiwen Wang<sup>a</sup>, Mengran Chen<sup>a</sup>, Zhining Cao<sup>a</sup>, Jia Liang<sup>b</sup>, Zhenguo Liu<sup>c</sup>, Yuxue Xuan<sup>c</sup>, Lin Pan<sup>a</sup>,  
Kafil M. Razeeb<sup>d</sup>, Yifeng Wang<sup>a</sup>, Chunlei Wan<sup>b</sup>, Peng-an Zong<sup>a,c,\*</sup>

<sup>a</sup> College of Materials Science and Engineering, Nanjing Tech University, Nanjing 210009, China

<sup>b</sup> State Key Laboratory of New Ceramics and Fine Processing, School of Materials Science and Engineering, Tsinghua University, Beijing 100084, China

<sup>c</sup> Key Laboratory of Flexible Electronics of Zhejiang Province, Ningbo Institute of Northwestern Polytechnical University, Ningbo 315103, China

<sup>d</sup> Micro-Nano Systems Centre, Tyndall National Institute, University College Cork, Dyke Parade, Lee Maltings, Cork T12 R5CP, Ireland

\* Corresponding Author:


Dr. Peng-an Zong ([georgepazong@gmail.com](mailto:georgepazong@gmail.com))

### Table of Contents

- S1. Process reproducibility and reliability
- S2. Setup for Seebeck coefficient measurement
- S3. Setup for electrical conductivity measurement
- S4. Molecule alignment after intercalation
- S5. Film morphology
- S6. Output voltage of the TE module
- S7. Air stability of the MXene-based films
- S8. Reproducibility of the the TE module
- S9. Air stability of the TE module

## S1. Process reproducibility and reliability


In this work, 3 batches of MX, MX SL, SL-300, SL-400 and SL-500 films were prepared. For each composition in each batch, 3 samples were cut out from different regions. As shown in Figure S1, for a specific composition, the fluctuation of  $\sigma$  and  $S$  was within 5% and 10%, respectively, in the same batch; while they increased to be within 10% and 15%, respectively, from batch to batch, implying good reproducibility and reliability of the process.

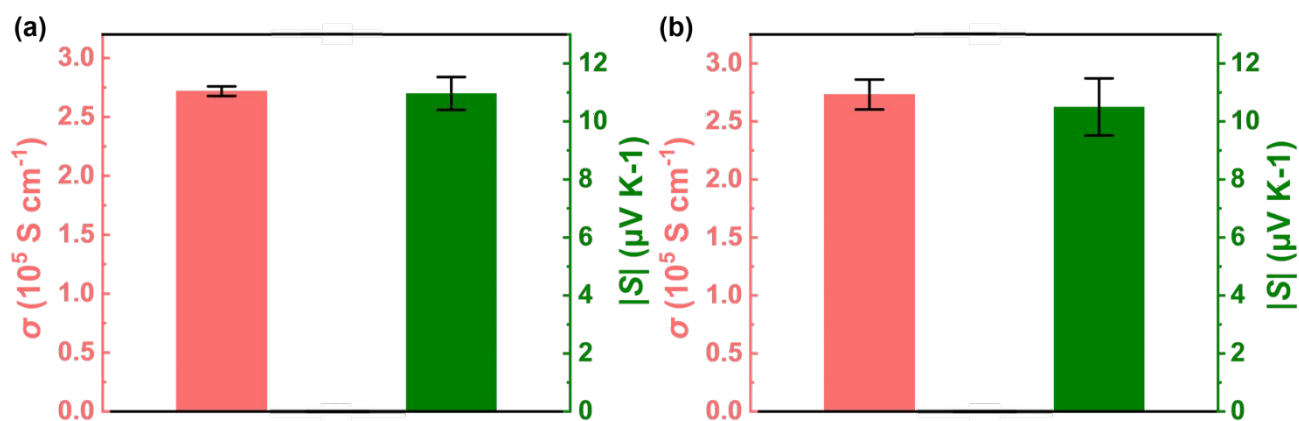

**Figure S1.** Fluctuation of the electrical conductivity,  $\sigma$  and Seebeck coefficient,  $S$  of SL-400 film (a) In different regions of the same batch, and (b) From batch to batch.

## S2. Setup for Seebeck coefficient measurement


The Seebeck coefficient was measured in ambient conditions based on a homemade apparatus. As shown in Figure S2a, the ends of the sample are placed on two reversibly installed Peltier modules and the temperature difference between the two ends of the sample is achieved by applying different current to the Peltier modules. A pair of thermocouples are pointed at the sample to collect the temperature difference ( $\Delta T$ ) and voltage difference ( $\Delta V$ ), and the distance between the probes was about 1.5 cm. Finally, a linear relationship was fitted based on the recorded  $\Delta V$  and  $\Delta T$ , and the slope of this linearity was noted as the Seebeck coefficient (Figure S2b).

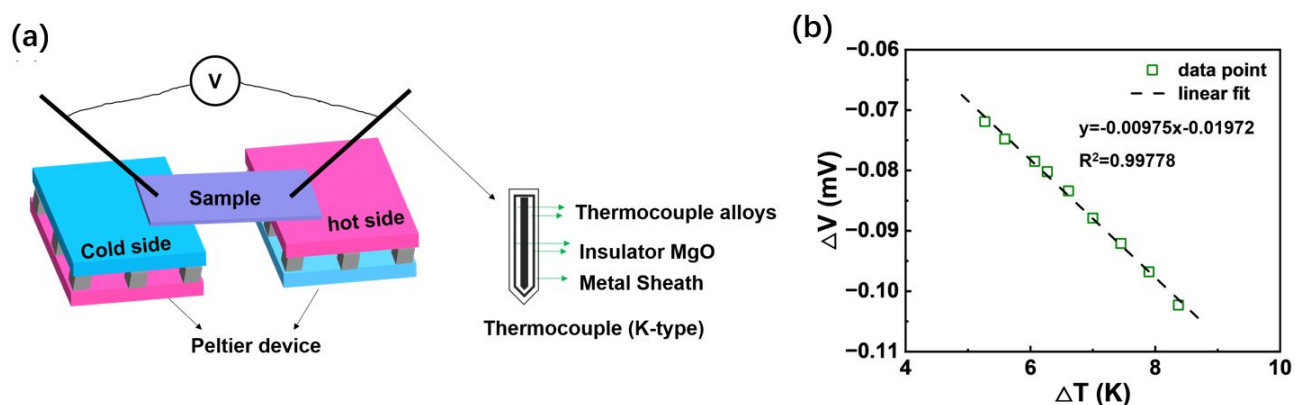

**Figure S2.** (a) Schematic of the experimental setup for the Seebeck coefficient measurement; (b) Fitting of  $\Delta V$  vs.  $\Delta T$ .


### S3. Setup for electrical conductivity measurement

As shown in Figure S3a, the electrical conductivity was measured on a commercial Hall measurement system (CH-Magnetolectricity Technology, CH-100) in ambient conditions based on the Van der Pauw method. As shown in Figure S3b, the samples were cut into squares with dimension of  $1\text{ cm} \times 1\text{ cm}$ , the 4 corners of which were contacted with four gold probes with silver serving as the contacting material. The distance between adjacent probes was about 1 cm.

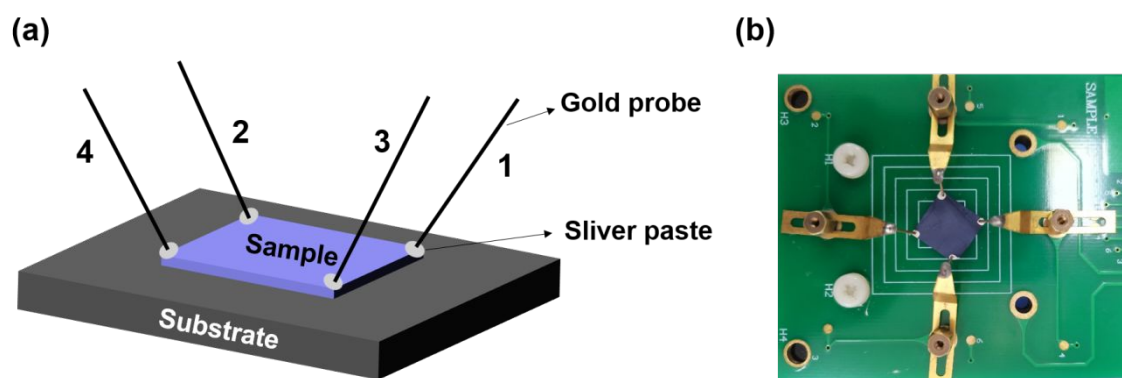


**Figure S3.** (a) Configuration for electrical conductivity measurement using the Van der Pauw method, (b) Photography of the testing configuration.

#### S4. Molecule alignment after intercalation

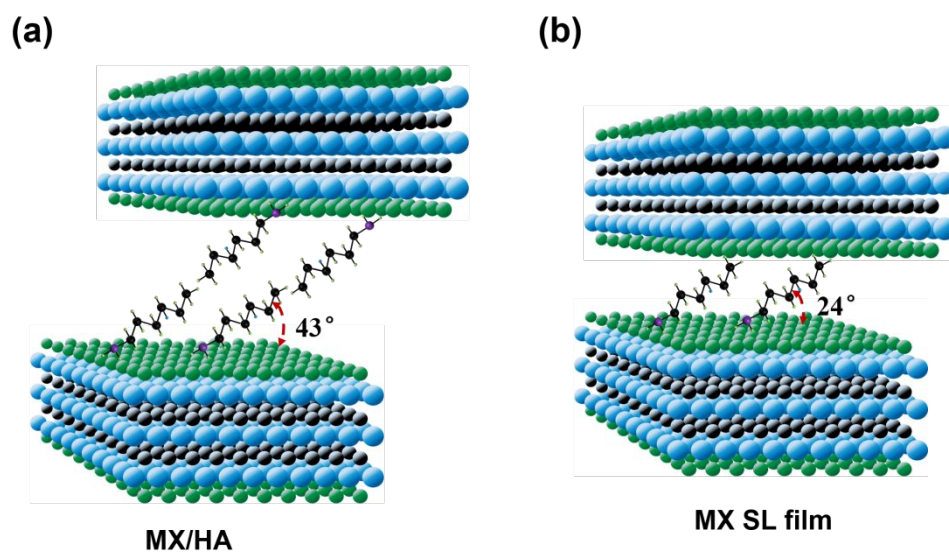


**Figure S4.** (a) Schematic microstructure of MXene/HA mixture, and (b) MXene/HA/NMF (MX SL) film.

#### S5. Film morphology

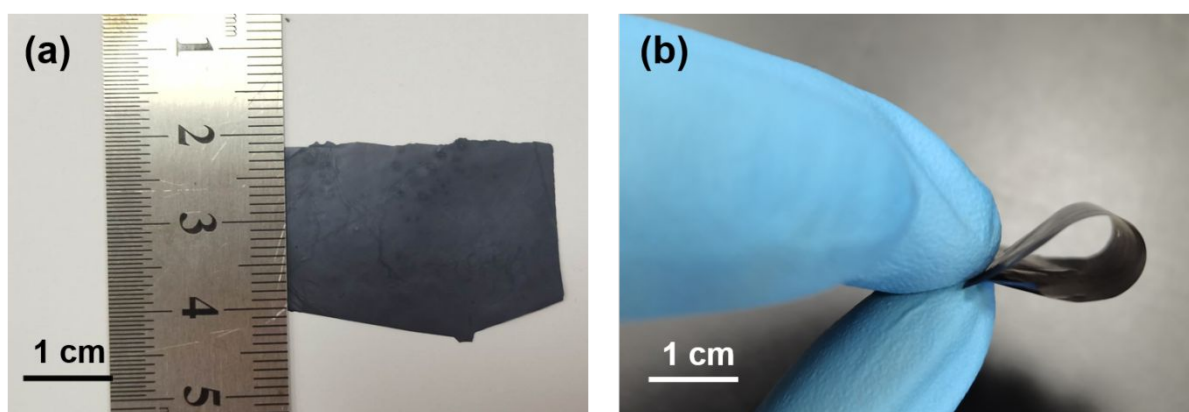


**Figure S5.** Morphology of the peeled-off MX SL film (a) At flat state, and (b) Under bending.

### S6. Output voltage of the TE module

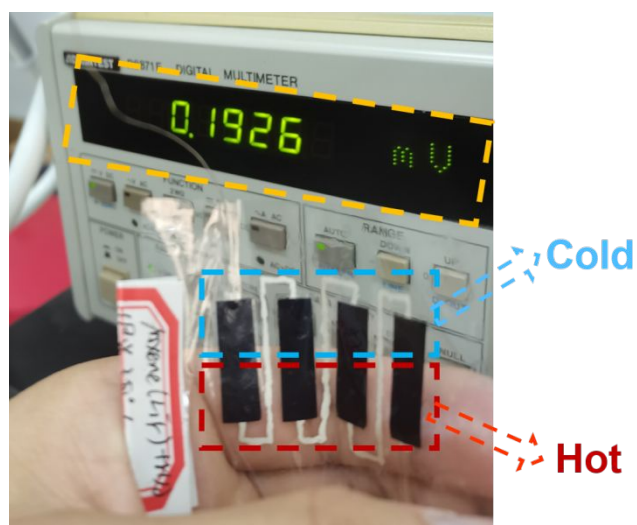

**Figure S6.** Demonstration of the voltage output of the TE module when attaching one end to finger skin.

### S7. Air stability of the MXene-based films

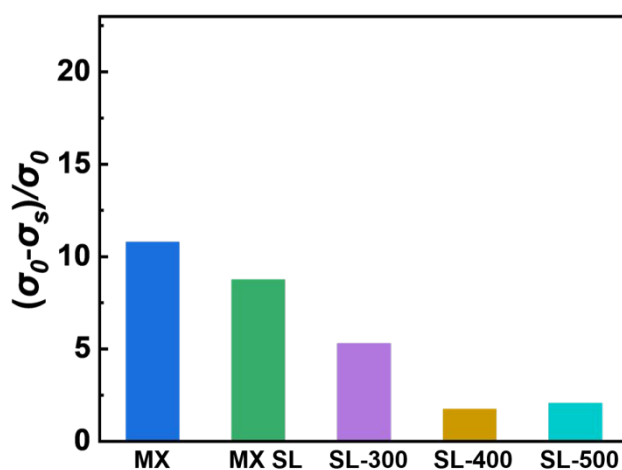


**Figure S7.** The decrease rate of electrical conductivity  $(\sigma_0 - \sigma_s) / \sigma_0$ ,  $\sigma_s$  for the exposed,  $\sigma_0$  for the original) of MX, MX SL, MX SL-300, MX SL-400 and MX SL-500 films after being exposed in air (temperature =  $\sim 26$  °C and relative humidity =  $\sim 55\%$ ) for 3 months.

## S8. Reproducibility of the TE module

**Table S1.** Performance of the TE modules based on SL-400 films of 3 batches

$\Delta T$ (K)	U (mV)			Power (nW)			Power density ( $\text{W m}^{-2}$ )		
	1st	2nd	3rd	1st	2nd	3rd	1st	2nd	3rd
<b>10</b>	0.53	0.41	0.49	2.5	2.3	2.8	0.016	0.014	0.017
<b>30</b>	1.33	1.19	1.25	20.3	16.1	23.5	0.127	0.100	0.146
<b>50</b>	2.31	2.35	2.26	58.6	63.4	55.5	0.366	0.396	0.346

## S9. Air stability of the TE module

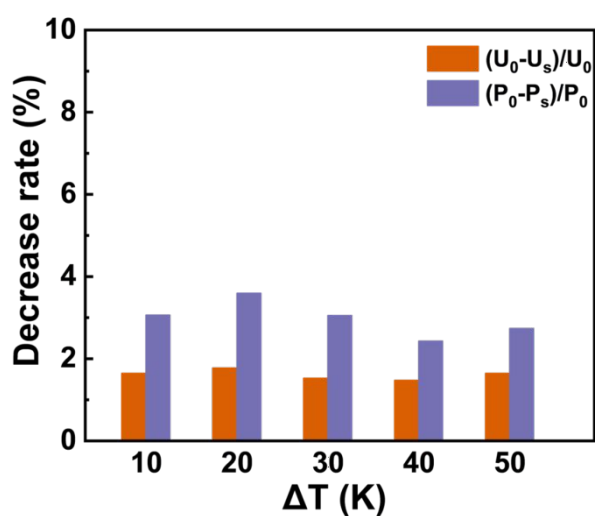

**Figure S8.** The decrease rate of output voltage ( $U_0 - U_s/U_0$ ) and power ( $P_0 - P_s/P_0$ ) of TE module (where  $U_s$ , and  $P_s$  are output voltage and power of TE module for the exposed,  $U_0$ , and  $P_0$  for the original) after being exposed in air (temperature =  $\sim 26$  °C and relative humidity =  $\sim 55\%$ ) for 3 months.